

Eneolithic copper smelting slags in the Eastern Alps: local patterns of metallurgical exploitation in the Copper Age

G. Artioli^{a,*}, I. Angelini^a, U. Tecchiati^b, A. Pedrotti^c

^a Dipartimento di Geoscienze, Università degli Studi di Padova, Padova, Italy

^b Ufficio Beni Archeologici, Provincia Autonoma di Bolzano, Bolzano/Bozen, Italy

^c Dipartimento di Filosofia, Storia e Beni Culturali, Università degli Studi di Trento, Trento, Italy

* Corresponding author. Tel. +39 0498279162, E-mail address: gilberto.artioli@unipd.it

Abstract

A number of slags of all known sites in the Italian Eastern Alps showing occurrences of copper smelting activities in the Copper Age have been characterized by lead isotope analysis. All the investigated smelting slags from Trentino (Romagnano Loc, La Vela, Gaban, Acquaviva di Besenello, Montesei di Serso) and Alto Adige/Sud Tyrol (Millan, Gudon, Bressanone Circonvallazione Ovest) have been recently characterized by thorough mineralogical, petrographical and chemical analysis and demonstrated to be the product of copper smelting activities of chalcopyrite-based mineral charges, with an immature technological extraction process referred as the “Chalcolithic” smelting process. Revision of the available radiocarbon dates show that the metallurgical activities pertaining to the analysed slags can be attributed to the third millennium BC. The lead isotope analysis indicates clearly that the mineral charge used for the smelting process was extracted from nearby mineral deposits. The detailed analysis of the spatial distribution of ores and slags allows for the first time to define the local organization of the metallurgical operations.

Keywords: copper metallurgy; Eastern Alps; smelting slags; Eneolithic; Lead isotope analysis.

1. Introduction

The Italian Eastern Alps are a well-known source of copper metal that was exploited since prehistory, possibly since Late Neolithic times. Due to the large amount of archeological evidence, especially the widespread and abundant occurrence of copper smelting slags (e.g. Cierny et al. 2004, Cierny 2008), the climax of the mining activities and copper production is currently attributed to the Recent and Final Bronze Age (Marzatico 1997, Weisgerber and Goldenberg 2004), and subsequently to Roman and Middle Age times, when large groups of German miners moved to

some of the Alpine valleys to organize and carry out the mining operations (Šebesta 2000, Zammatteo 2009). However the copper metal was circulating well before the Bronze Age, as the archeological evidence clearly shows (Pedrotti 2002: p. 213): metal objects were circulating at least from the late neolithic (Angelini et al. 2013) and a number of Copper Age sites in the Trentino and Alto Adige areas yield evidence of smelting activities in the form of metallurgical slags, tuyeres, a multitude of copper objects including the Iceman's axe, and a few occurrences of pyrotechnological installations (Perini 1989, Pedrotti 2002, Pearce 2007).

The focus of the present investigation is to characterize the isotopic signal of the known Eneolithic smelting slags and to compare the measured lead isotope ratios with the signal of the copper deposits in the Eastern Alps (Nimis et al. 2012, Artioli et al. 2013), in order to pinpoint which deposits were actually exploited in the Copper Age, and possibly outline the local organization of the metallurgical activities.

2. Slag samples: selection and characterization

The slag samples to be investigated were selected based on (1) their secure occurrence in archaeological sites dated to the 3rd millennium BC, and (2) previous results of mineralogical, petrographic, and chemical studies on the slags confirming that they are indeed the product of copper smelting activities.

Table 1 lists the sites where the investigated copper smelting slags were located together with the related archeological literature. Figure 1 shows the geographical distribution of the sites, all located in the Trentino and Alto-Adige areas.

The sites are clustered in three main areas:

- a) Millan, Gudon, and the site of Circonvallazione ovest are all located in the Isarco river valley near the city of Bressanone/Brixen
- b) Romagnano Loc and La Vela are located in proximity of the Western bank of the Adige River, whereas Gaban, and Acquaviva di Besenello are located in proximity of the Eastern banks of the river in the outskirts of the city of Trento
- c) Montesei di Serso is located in the upper Valsugana Valley near the city of Pergine, again located in the Eastern area the Adige River.

The common feature of all these sites is the location at low altitude, near the bottom of the valley, in close proximity to the river and, presumably, to the coeval settlements. The archaeological occurrences of the Trentino slags and their dates have been extensively discussed by Pearce (2007): the critical revision of the available dates indicate that the start of the metallurgical activities at

Gaban and Acquaviva can be attributed to the early 3rd millennium BC, whereas the analysed slags from the other sites cluster around the second half of the 3rd millennium BC. The recent dates obtained on the Alto Adige sites (Millan, Gudon) confirm this chronology (Angelini et al. 2013).

Table 1. List of sites yielding the investigated copper smelting slags, with the related references of previous archaeological and archaeometric work.

Locality	Area	references
Millan	Isarco Valley, Alto Adige	Tecchiati 2009, Colpani et al. 2009, Angelini et al. 2013
Gudon	Isarco Valley, Alto Adige	Colpani et al. 2009, Angelini et al. 2013
Bressanone Circonvallazione Ovest	Isarco Valley, Alto Adige	Angelini et al. 2013
Gaban	Adige Valley, Trentino	Cattoi et al. 1995, Cattoi et al. 1997, D'Amico et al. 1998, Artioli et al. 2009
La Vela	Adige Valley, Trentino	Fasani 1988, Perini 1989, Metten 2003, Artioli et al. 2009
Acquaviva di Besenello	Adige Valley, Trentino	Cattoi et al. 1995, Cattoi et al. 1997, D'Amico et al. 1998, Pedrotti 2002, Metten 2003, Artioli et al. 2009
Romagnano	Adige Valley, Trentino	Perini 1971, Perini 1989, Cattoi et al. 1995, Cattoi et al. 1997, Metten 2003, Artioli et al. 2009
Montesei di Serso	Valsugana, Trentino	Perini 1989, Metten 2003, Artioli et al. 2009

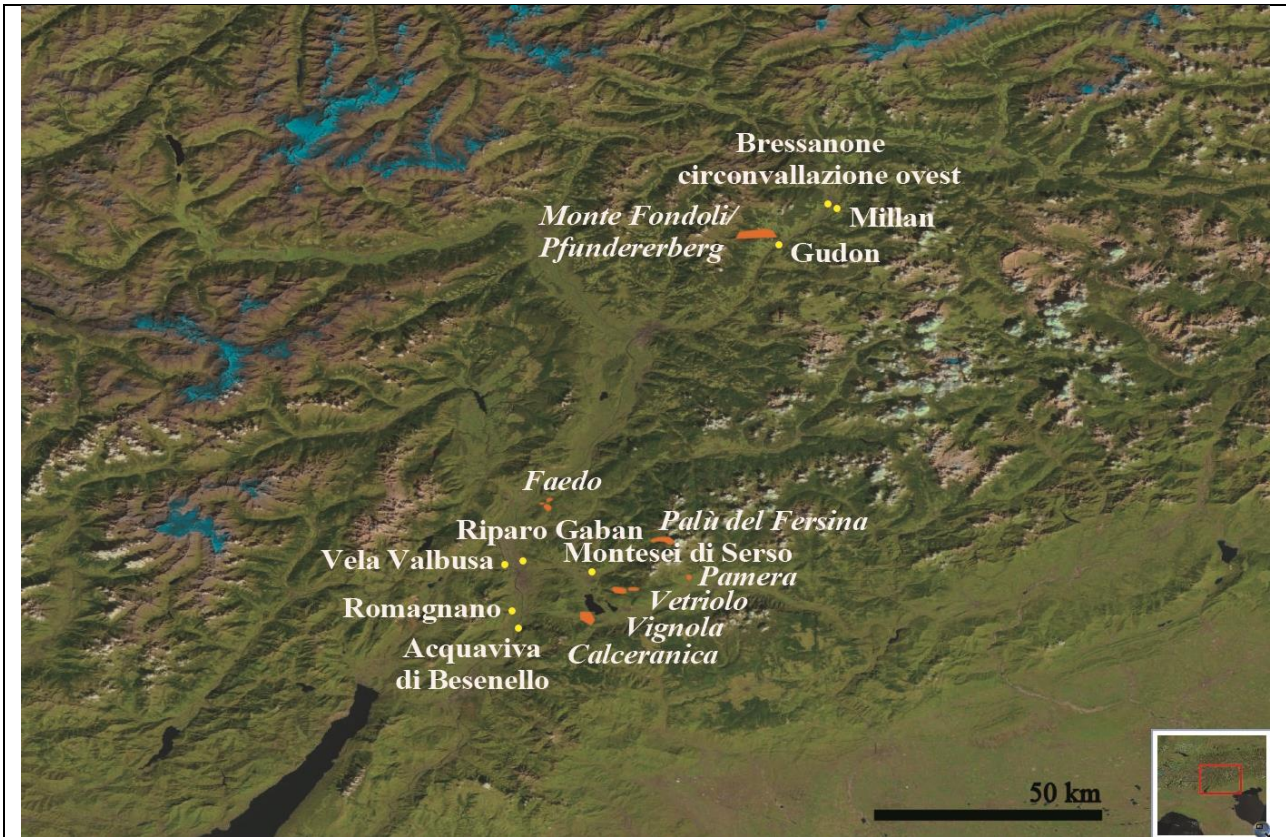


Fig. 1. Map of the location of the Eneolithic sites in the Eastern Alps showing the investigated copper smelting slags (yellow dots). Some of the nearby copper mining areas are also marked in the map (red fields, names in italics). Image courtesy of laboratoriobagolini.it/ais/.

All samples were previously thoroughly characterized by minero-petrographical and chemical analysis by X-ray powder diffraction, optical microscopy, and electron microscopy with energy dispersive spectroscopy (Artioli et al. 2009, Colpani et al. 2009). The common features of all slags are here summarized:

- Very heterogeneous and coarse texture (Figure 2)
- Presence of primary sulphide relics (chalcopyrite) with only incipient reactions (Figure 3)
- Abundant unreacted quartz
- Presence of typical slag minerals formed during smelting, especially fayalitic olivine, but also pyroxenes (see Colpani et al. 2009)
- Presence of abundant wuestite, frequently dendritic (Figure 4) or agglomerated
- Presence of copper or matte droplets, frequently intermixed with magnetite

The overall features, such as the coarse texture, the presence of wuestite and magnetite even in the same slag and the occurrence of poorly reacted sulphides indicate an incomplete process of copper extraction and poorly controlled temperature and oxygen fugacity conditions. The slags never

underwent a complete melting stage and the process of copper extraction was rather inefficient. These features altogether have been taken as evidence of a technologically non-standardized process of copper extraction, referred to as the “Chalcolithic” process (Pearce 2007, Bourgarit 2007). The observed mineralogical and textural features are compatible with the age attributed to the sites, and are totally different from those observed in the Late Bronze Age slags found in the same area (Cierny 2008, Anguilano et al. 2002, Addis et al. 2015). One copper fragment was also recovered in the Millan site amidst the large amount of smelting slags (Figure 5). Since it represents a very rare occurrence, and further evidence of the metallurgical activities, it was also analysed and compared with the slag data.



Fig. 2a

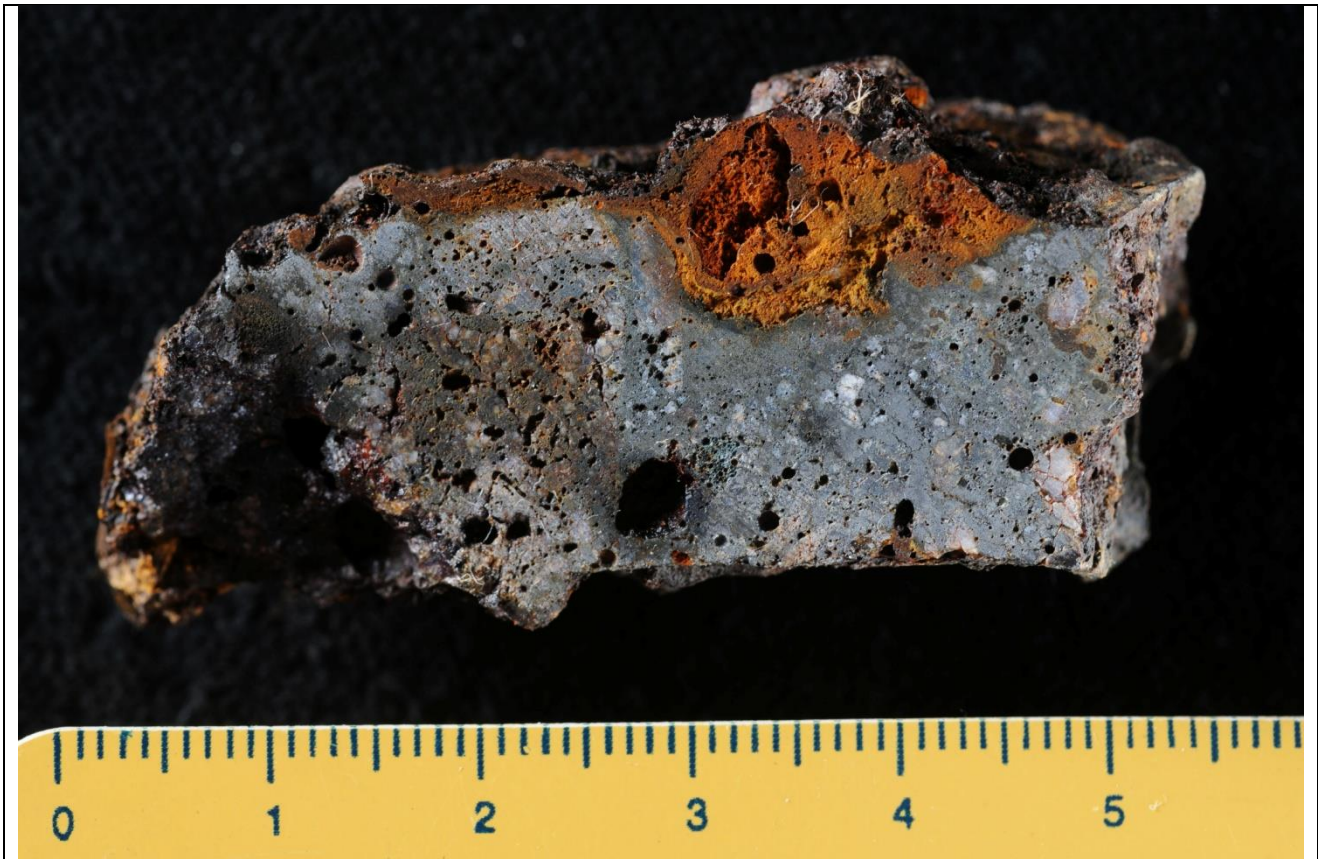


Fig. 2b

Fig. 2. Macroscopic images showing the coarse texture common of all the investigated Eneolithic slags: (a) slag sample from Riparo Gaban, Trentino (sett. IV C6); (b) slag sample from Millan, Alto Adige.

103

104

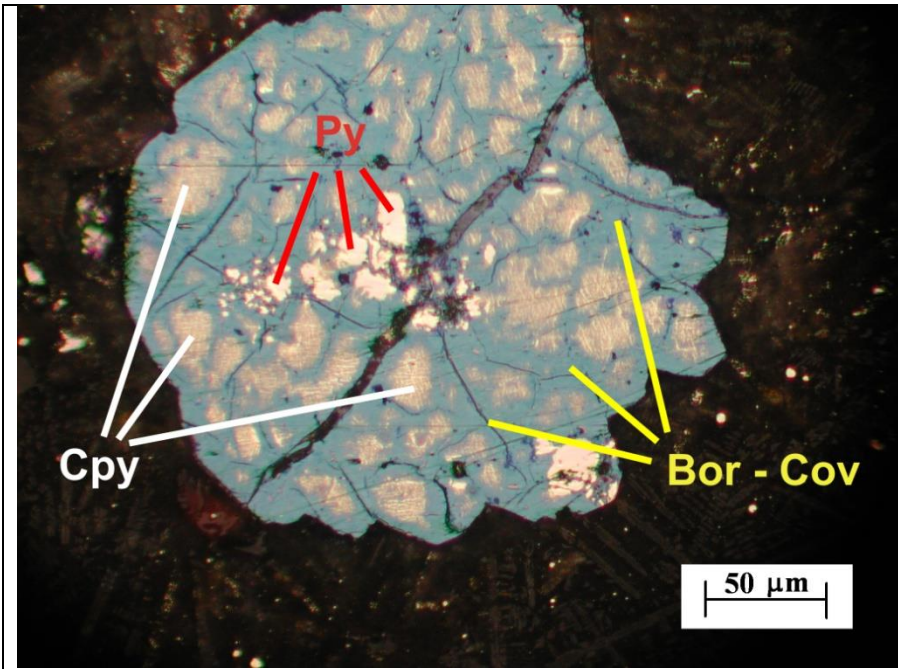


Fig. 3. Partially reacted primary sulphide in a slag sample from Riparo Gaban, Trentino (sett. IV C6). Optical microscopy, reflected light, the diameter of the sulphide grain is approximately 350 μm. Py = pyrite, Cpy = chalcopyrite, Bor-Cov = secondary sulphide of bornite-covelline composition.

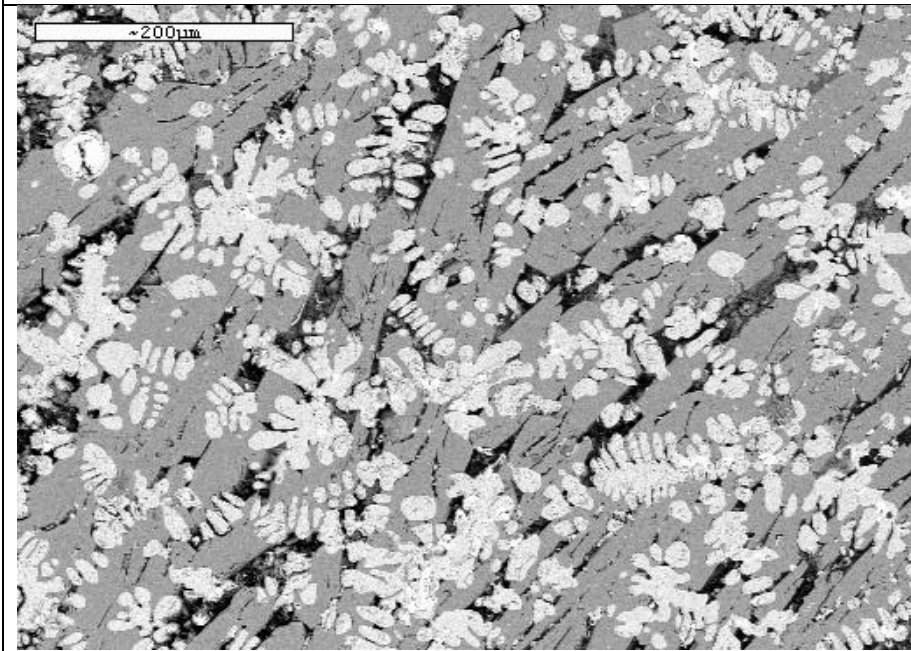


Fig. 4. Wuestite dendrites in the fayalitic matrix. Slag sample from Montesei di Serso, Trentino. Scanning electron microscopy, backscattered electron image, reference bar is 200 μm.

105
106



Fig. 5. The copper fragment found in association with the copper smelting slags at the Millan site, Alto Adige (US-15). It is one of the rare pieces of metals ever found together with the copper smelting residues.

107

108

109 3. Lead isotope measurements

110

111 The slag samples were characterized in thin section by optical microscopy under transmitted and
 112 reflected light and by X-ray powder diffraction. A portion of each sample rich in fayalite-magnetite-
 113 sulphides was gently crushed and adequate amount of fragments was separated by handpicking
 114 under a binocular microscope. For the most part the selected fragments consist of fayalite-magnetite
 115 residues with microscopic inclusions of copper and sulphidic matte. In some cases small inclusions
 116 of partially reacted sulphide ores are present.

117 The separates (10–100 mg) were dissolved in aqua regia by high-pressure microwave digestion in
 118 sealed PTFE vessels. The dissolved lead was purified using the Sr_Spec™ resin (EiChroM
 119 Industries; Horwitz et al., 1992), following the same procedure described in Villa (2009). About
 120 100 mL of Sr_Spec™ resin are filled in a 3-mm diameter hand-made PTFE column. The height to
 121 width ratio is approximately 4. The sample solution is loaded in 0.5 mL 1M HNO₃, 1.5 mL of
 122 which is also used to wash out the matrix metals, while Pb is very strongly retained on the resin. Pb
 123 is then eluted with 3 mL 0.01M HNO₃ and is ready for analysis. Lead isotope analyses were
 124 performed with a Multi-Collector-ICP-MS (Nu Plasma II) at the Institut für Geologie, University of

125 Bern (Switzerland). The sample solution was ionized by introducing it into a 9000 K plasma. All
126 elements were ionized simultaneously. Mass fractionation was monitored by adding a small
127 quantity of Tl, which has a known $^{203}\text{Tl}/^{205}\text{Tl}$ ratio, is ionized together with and fractionated
128 by the same mechanism as Pb, and does not interfere with Pb isotope measurements. Calibration
129 was carried out using the NIST SRM 981 international standard. The results are reported in Table 2.
130 Typical in-run relative uncertainties (2s) on $^{206}\text{Pb}/^{204}\text{Pb}$, $^{207}\text{Pb}/^{204}\text{Pb}$, and $^{208}\text{Pb}/^{204}\text{Pb}$ isotope
131 ratios were smaller than 0.2‰. The external reproducibility on the NIST SRM 981 reference
132 material amounted to $\pm 0.15\text{‰}$ (2s), very similar to the individual in-run precision on unknown
133 samples. Total errors reported in Table 1 were calculated by normal error propagation taking into
134 account both in-run uncertainties and dispersion of repeated measurements on NIST SRM 981
135 during the same analytical session.

136 A small fragment of the copper fragment found at Millan (sample BFO60-15, Figure 5) was also
137 analysed in Bern using the same protocols. An earlier measurement performed at the Royal
138 Holloway, University of London by Dr. Wolfgang Müller on the same object is also reported for
139 comparison purposes (Table 2).

140

141

*Table 2. Pb isotopic ratios measured on the Eneolithic copper smelting slags from Trentino and Alto Adige (Southern Italian Alps). The measurements performed on a copper fragment found in association with the Millan slags are also reported (sample BFO60-15): * measurement performed in Bern, ** measurement performed in London (courtesy of W. Müller).*

Locality	Sample	$^{206}\text{Pb}/^{204}\text{Pb}$	2σ	$^{207}\text{Pb}/^{204}\text{Pb}$	2σ	$^{208}\text{Pb}/^{204}\text{Pb}$	2σ
Bressanone	BX-A4	18,298	0,001	15,682	0,002	38,539	0,006
Bressanone	BX-P1	18,271	0,002	15,682	0,002	38,516	0,007
Millan	BFO104-18	18,270	0,002	15,688	0,003	38,531	0,008
Millan	BFO60-15*	18,265	0,001	15,690	0,002	38,540	0,007
Millan	BFO60-15**	18,279	0,003	15,693	0,002	38,545	0,005
Gudon	US12A	18,265	0,003	15,685	0,001	38,525	0,006
Gudon	US14A	18,281	0,002	15,686	0,002	38,532	0,005
Gudon	US14C -2	18,287	0,002	15,699	0,002	38,573	0,006
Gudon	US14C -1	18,276	0,003	15,687	0,003	38,533	0,004
Gudon	US14D	18,276	0,003	15,690	0,002	38,543	0,006
Gudon	US15	18,265	0,002	15,684	0,002	38,517	0,007
La Vela	LV15	18,298	0,004	15,682	0,003	38,539	0,006
La Vela	LV 18	17,936	0,002	15,642	0,002	38,141	0,006
La Vela	LV 9	17,919	0,002	15,642	0,002	38,135	0,007
La Vela	LV 5	17,909	0,003	15,643	0,003	38,130	0,008
Montesei	MS 1	18,226	0,005	15,667	0,005	38,461	0,015
Montesei	MS 3	18,262	0,007	15,686	0,006	38,523	0,014
Montesei	MS 11	18,229	0,007	15,654	0,008	38,446	0,027
Montesei	MS 11 replica	18,238	0,001	15,664	0,002	38,473	0,005
Gaban	GAB 1 (C6)	18,110	0,001	15,658	0,001	38,344	0,004
Gaban	GAB 2	17,903	0,002	15,643	0,002	38,120	0,006
Gaban	GAB 3	17,896	0,002	15,643	0,002	38,114	0,007
Romagnano	ROM 1	17,988	0,003	15,647	0,002	38,191	0,006
Romagnano	ROM 13	17,921	0,002	15,641	0,002	38,131	0,007
Acquaviva	ACQ 1	17,911	0,002	15,640	0,002	38,119	0,007
Acquaviva	ACQ 2	18,195	0,002	15,661	0,002	38,431	0,007
Acquaviva	ACQ 3	17,940	0,001	15,650	0,002	38,171	0,003

142


143

144 4. Results and discussion

145

146 The Pb isotope ratios measured on the Eneolithic copper smelting slags from Trentino and Alto
 147 Adige (Table 2) can be directly compared to the available data on copper ores from the Southern
 148 Eastern Alps (Nimis et al. 2012). The data are shown in Figures 6a and 6b.

149

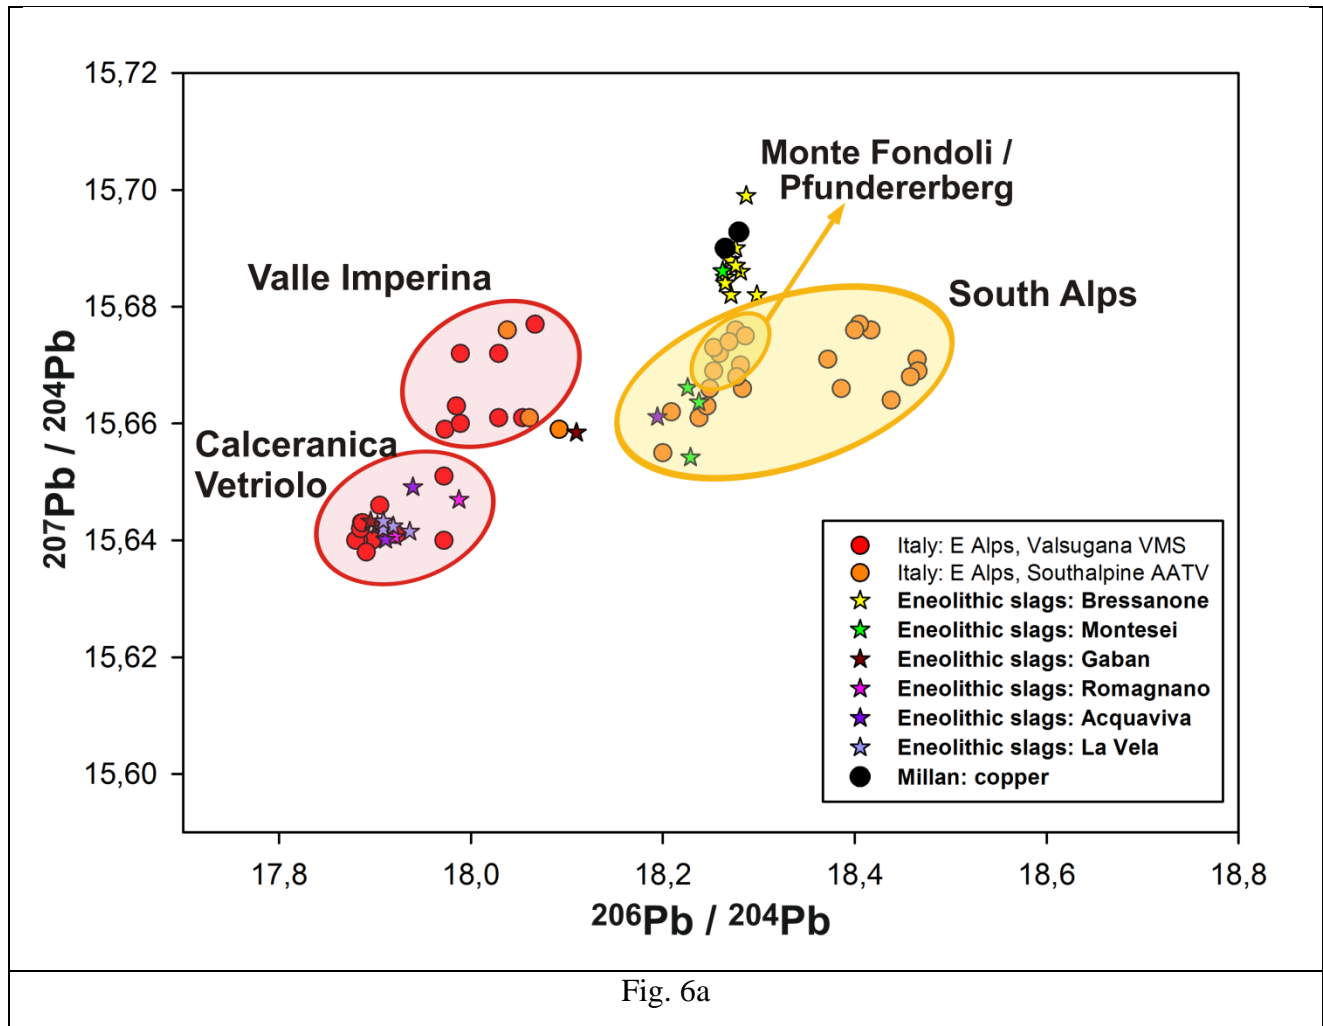

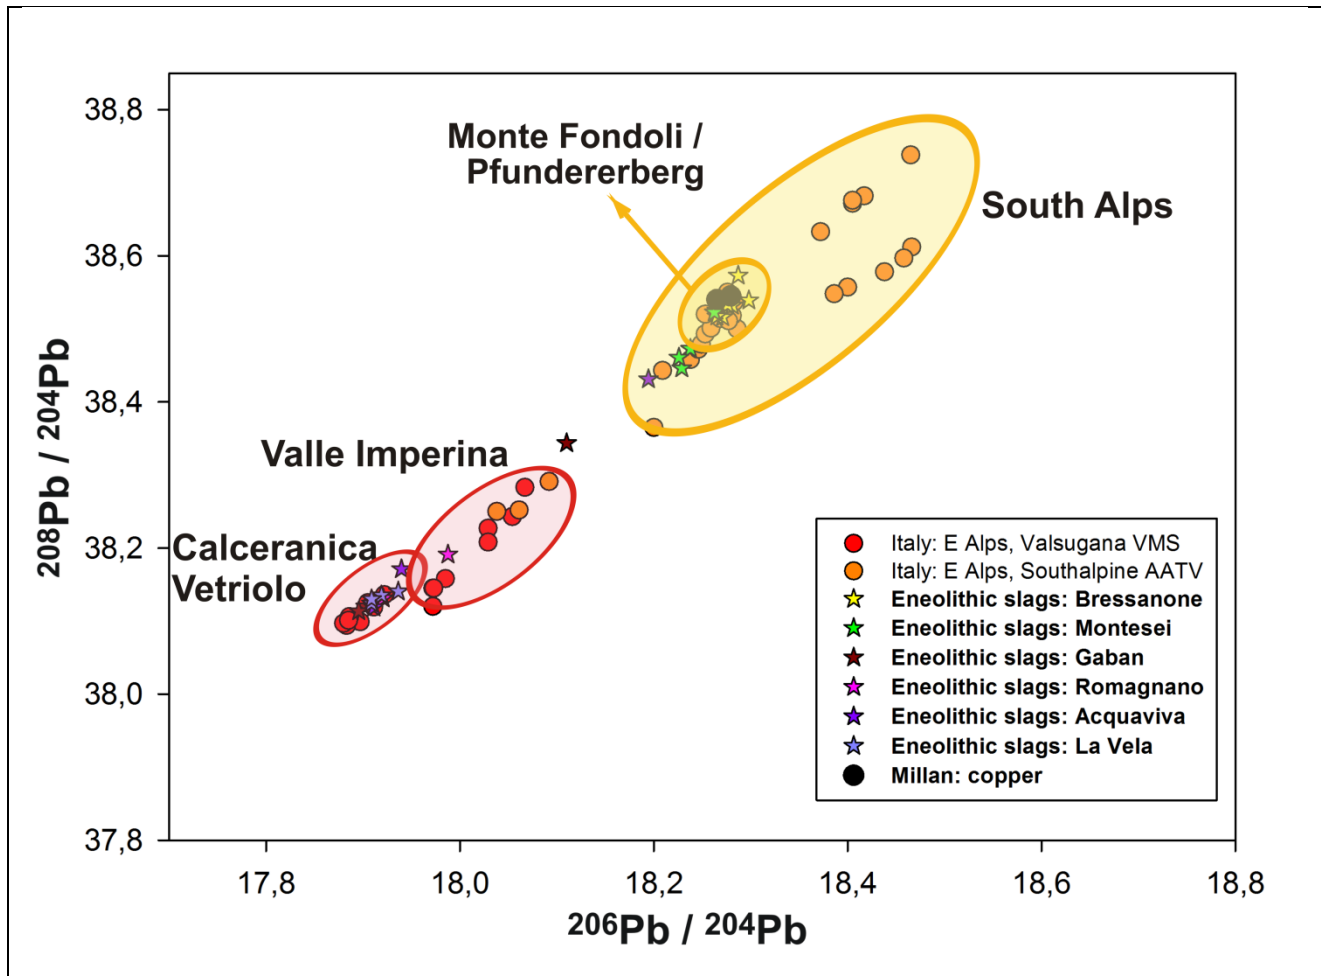


Fig. 6b

Fig. 6. Lead isotope ratios in the analysed Eneolithic copper smelting slags from Trentino and Alto Adige (stars), compared to the available data for copper ores (circles). The ore deposits have been divided into two main groups: the pre-Variscan massive ores related to the Hercinian basement and located in proximity of the Valsugana fault (red circles: valsugana VMS volcanogenic massive sulphides), the post-Variscan ores mostly constituted by polymetallic sulphides related to Permo-Triassic volcanics (orange circles: broadly labelled as Southalpine deposits from Alto Adige, Trentino, and Veneto AATV).

150

151 Apart from one slag sample from Gaban, which is located midway between the two major field of
 152 Southern Alpine copper deposits, as a first approximation all other slag data cluster in close
 153 proximity of the reported LI ore data. This is no surprise, since it is of course expected that the
 154 sulphidic ores used for metal extraction must derive from nearby sources. However, the availability
 155 of geologically and geographically well-resolved data for the ores permits a very detailed analysis
 156 of the pattern of mine exploitation in the areas around the smelting sites.

157 It can be clearly observed that the slags from Romagnano, La Vela, Gaban and Acquaviva sites, all
 158 located in the Adige Valley, show a close affinity to the ores of the Pre-Variscan massive deposits
 159 related to the Hercinian basement. These are mostly located in proximity of the Valsugana fault,

and the major mine is that of Calceranica (Figure 7). On the other hand the slags of Montesei di Serso and all the Alto Adige sites (Bressanone, Gudon, Millan) show a clear relationship to the Post-Variscan sulphide ores related to Permian and Triassic volcanics. Specifically, the Montesei slags show close affinity to the polysulphidic ores present in the Val dei Mocheni (Figure 7), whereas the Alto Adige slags are evidently related to the ores of the Monte Fondoli area, near Chiusa (Figure 8). The data obtained on the copper fragment associated to the Millan slags are also internally consistent and fit perfectly with the slags data and the Monte Fondoli ores.

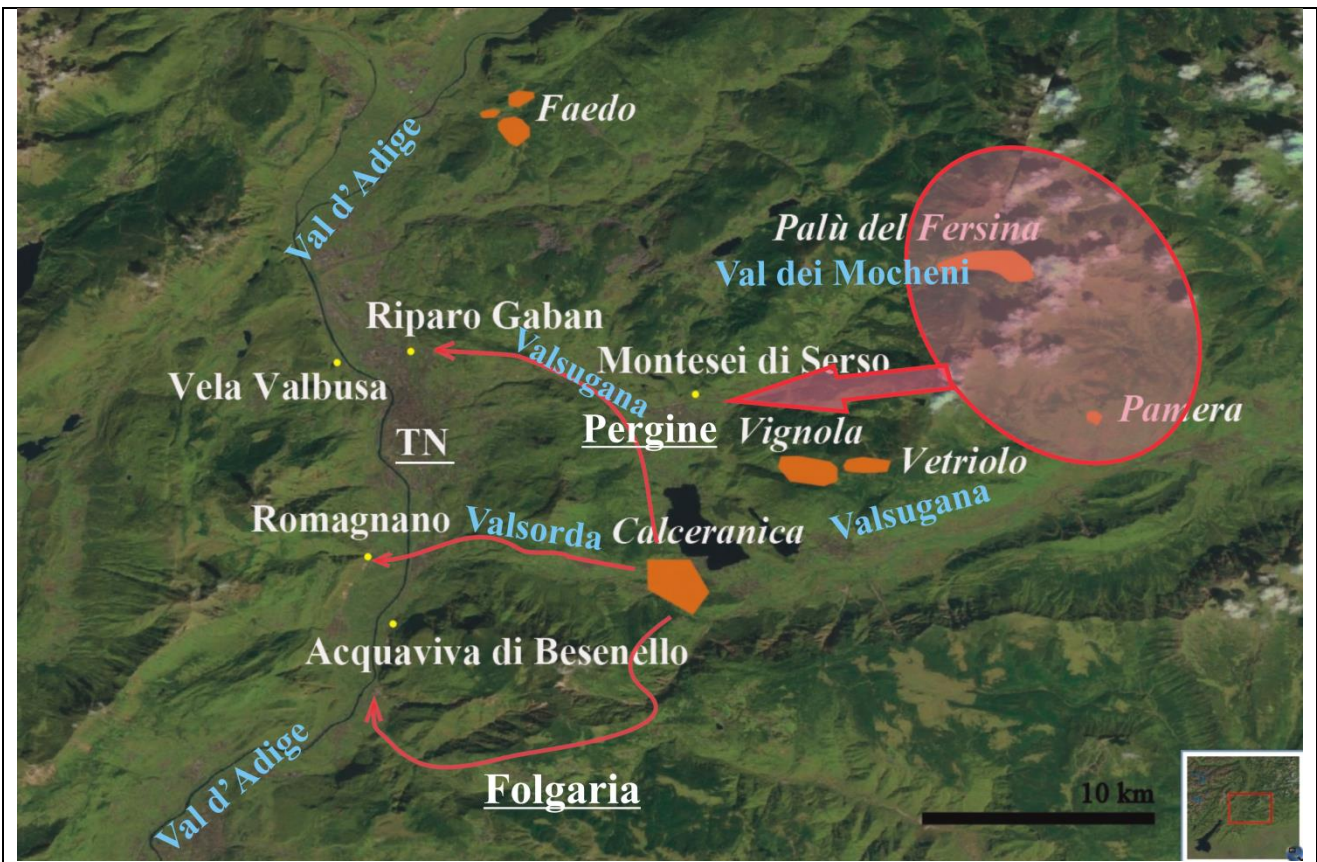


Fig. 7. Location of the occurrences of the analysed Eneolithic copper smelting slags in Trentino (yellow dots), together with the nearby ore sources matching the LI signal (orange fields, names in italics). The localities and geographical features cited in the text are reported (Town names are underlined). Image courtesy of laboratoriobagolini.it/ais/

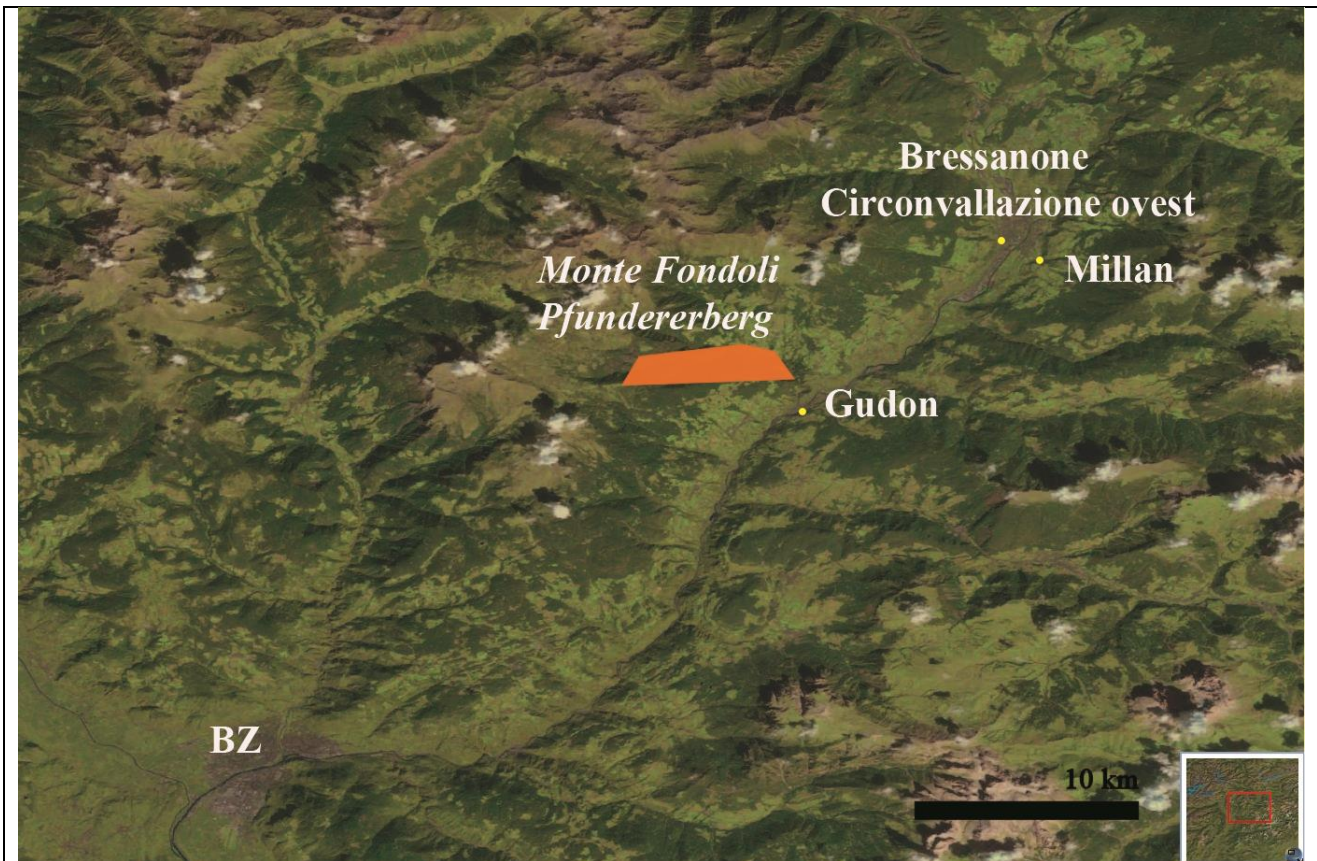


Fig. 8. Location of the occurrences of the analysed Eneolithic copper smelting slags in Alto Adige (yellow dots), together with the nearby ore source at Monte Fondoli (Pfundererberg, Chiusa) matching the LI signal (orange field, names in italics). Image courtesy of laboratoriobagolini.it/ais/

169

170

171 The data indicate that in the Alto Adige area, where only one major deposit occurs (Monte Fondoli),
 172 these ores were supplying the chalcopiritic charge for all the metallurgical activities along the
 173 Isarco Valley. Again it should be noted that all slag-producing sites are located not far from the
 174 river, at low altitude.

175 In the Trentino area, where many ore sources are available, a pattern of exploitation seem to appear:
 176 the metallurgical smelting sites located along the Adige River Valley obtained the chalcopiritic
 177 charge essentially from the mine of Calceranica, easily reachable through at least three easy routes,
 178 the road though Folgaria, the Valsorda road, and the main entrance to the Valsugana Valley, just
 179 west of Trento. Interestingly, the slag sites are located almost exactly at the outlet of these three
 180 roads into the Adige valley. Conversely the Montesei site, located near Pergine at the bottom of the
 181 Valsugana Valley, obtained the sulphidic ore exclusively from the Valle dei Mocheni, despite being
 182 conveniently located on the opposite side of the Valley with respect to the Calceranica mine. It
 183 looks that the Valsugana Valley acted as the boundary for the two independent metallurgical
 184 districts. This implies local control of the territory and of the ore resources.

It also proves interesting to compare the slag Pb isotope data with the available data on coeval objects (Fig. 9). The plots show clearly that the local ores linked to the smelting slags that were exploited for the copper production in the Southern Alps in the 3rd millennium BC are also the source for a substantial part of the circulating copper objects in the region. These include several of the objects found in the Col del Buson hoard (Angelini et al. 2011), the awl (from Cellore, Illasi) and the copper ingot (from Cisano, Bardolino) analysed by Pernicka and Salzani (2011), and the two axes from Serravalle (Tecchiati 1991). The published objects from Tyrol and Serbia show a markedly different signal, mostly related to the Serbian deposits (Höppner et al. 2005, Pernicka et al. 1993, Pernicka et al. 1997). Only one of the Italian objects (a small metal ring from the Col del Buson hoard) seems to be related to the Balkan ores.

5. Conclusions

The lead isotope analysis of the copper smelting slags from all known metallurgical sites in Trentino and Alto Adige during the 3rd millennium BC show a consistent pattern relating the sulphidic ore sources and the smelting locations. The Monte Fondoli deposit is the only source supplying the smelting sites in Alto Adige, all located along the bottom of the Isarco River Valley. In Trentino the major copper ore deposits are located along or nearby the Valsugana Valley, and the valley itself seem to represent a major geographical boundary between independently managed mining districts.

Although copper-based objects were circulating in the area well before the mid-Eneolithic, as testified by several metal finds (Pedrotti 2002, Pearce 2007), the substantial amount of slags produced during the 3rd millennium (i.e. several hundred kilograms at Milland and La Vela) indicate the start of the massive exploitation of ores in the Southern Alps and the systematic and well organized production of copper metal. Correspondingly, many of the objects circulating in the region result to be produced from Southern Alpine copper.

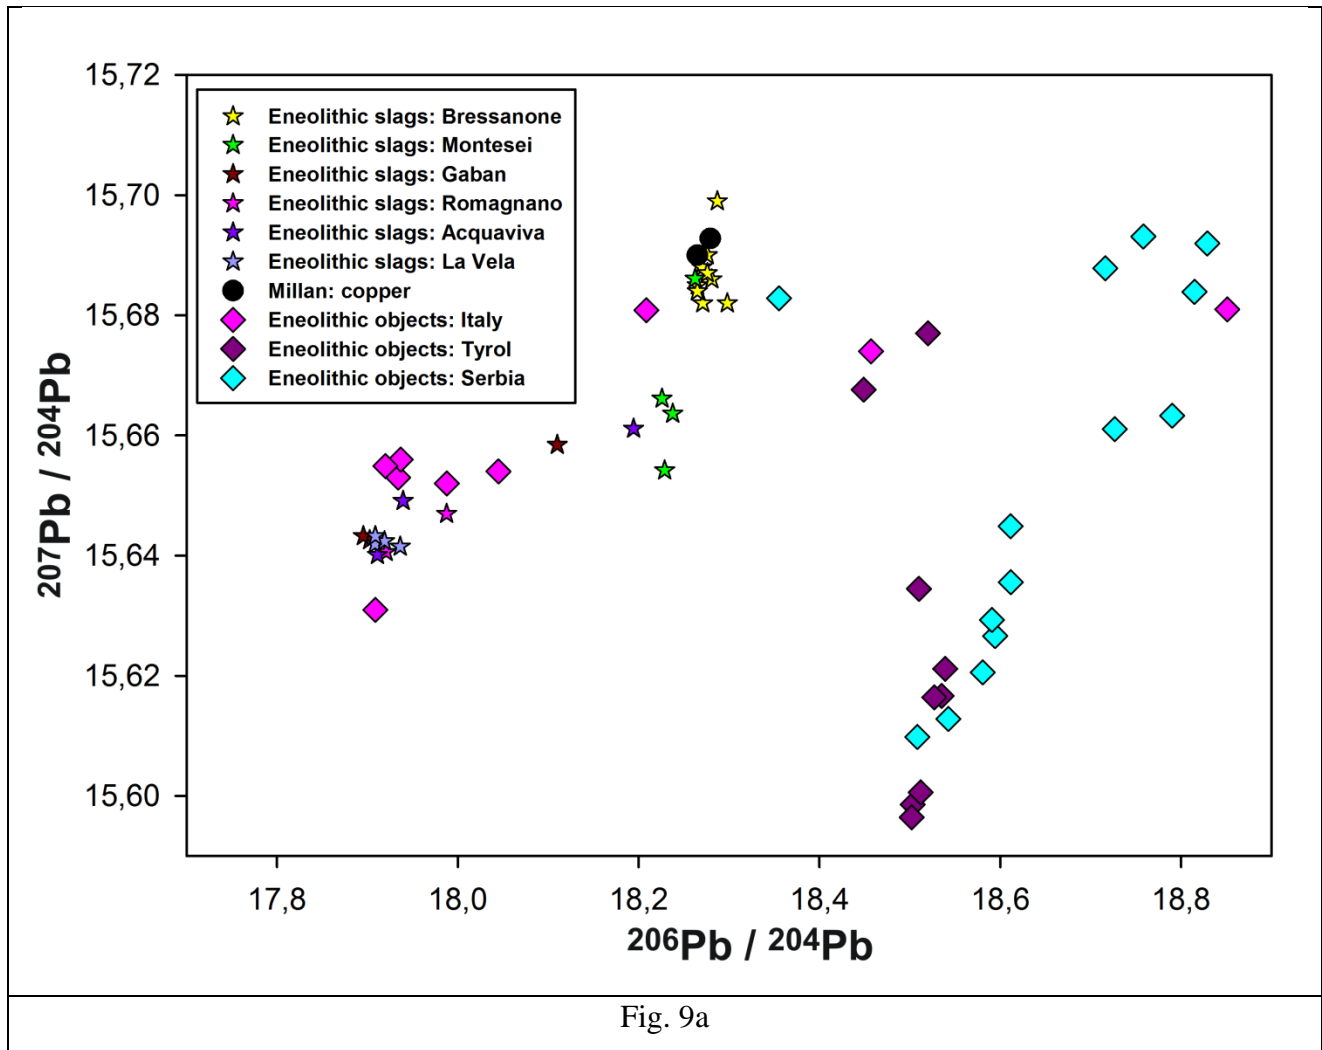


Fig. 9a

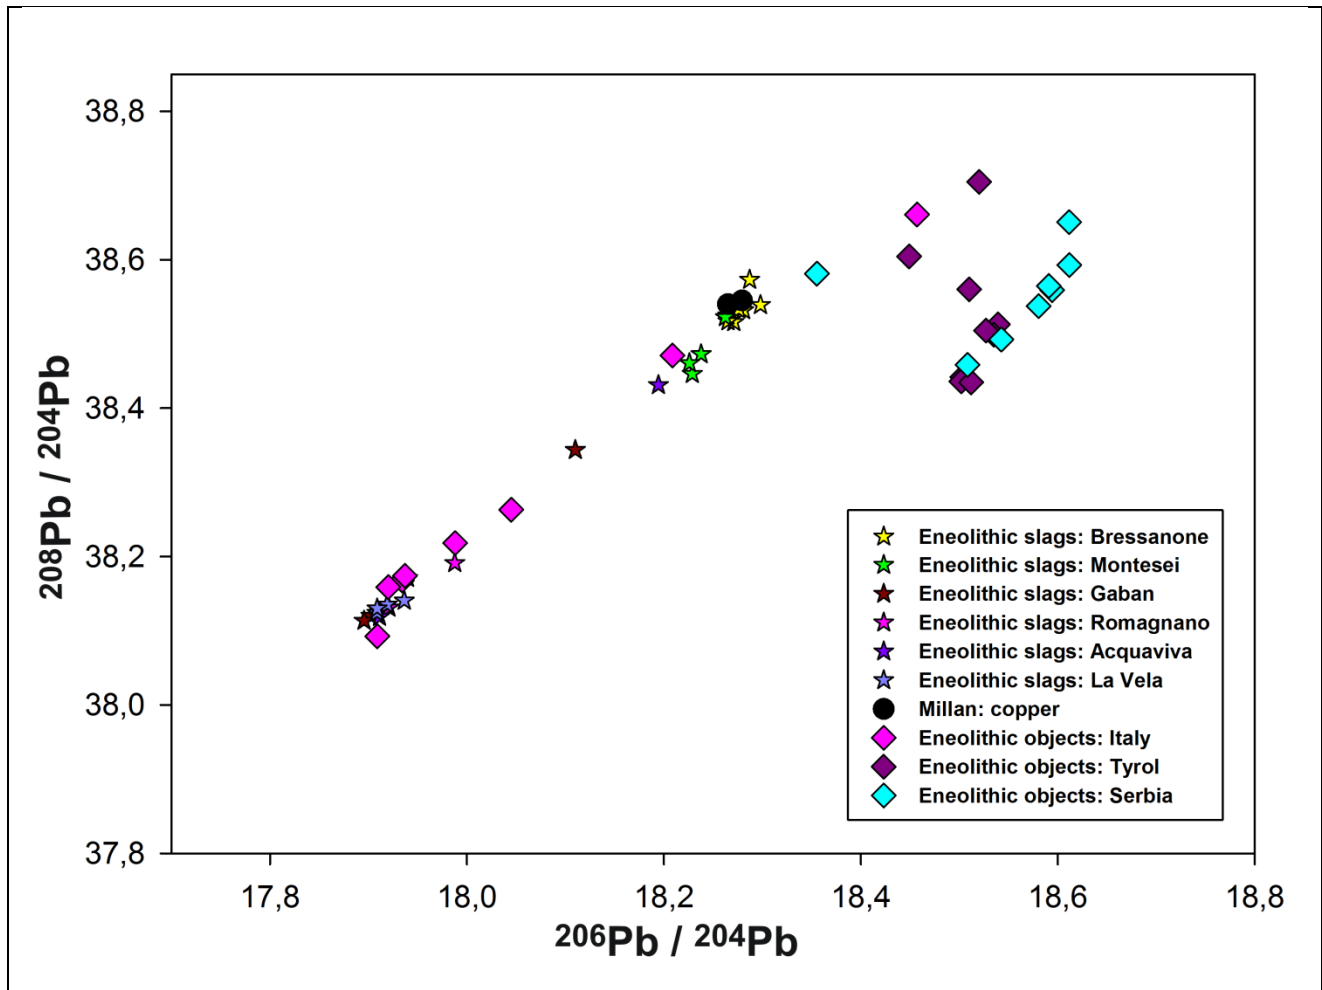


Fig. 9b

Fig. 9. Lead isotope ratios in the analysed Eneolithic copper smelting slags from Trentino and Alto Adige (stars), compared to the available data for late-Neolithic and Eneolithic objects (diamonds). The data for the objects from Northern Italy are from Angelini et al. (2011) and Pernicka and Salzani (2011). The data for the objects from Tyrol are from Höppner et al. (2005). The data for the Serbian objects are from Pernicka et al. (1993).

Acknowledgements

Ilaria Giunti, Anna Addis, and Caterina Canovaro helped at different stages in the sample preparation and MS measurements at the Institut für Geologie, Bern. The Museo di Storia Naturale, Trento kindly made the samples from Trentino available for the study. Dr. Wolfgang Müller allowed reporting of his measurement on sample BFO60-15.

References

- Addis, A., Angelini, I., Nimis, P., Artioli, G., 2015. Late Bronze Age copper smelting slags from Luserna (Trentino, Italy): interpretation of the metallurgical process. *Archaeometry*, in press, DOI: 10.1111/arc.12160
- Angelini, I., Artioli, G., Pedrotti, A., Tecchiati, U., 2013. La metallurgia dell'età del Rame dell'Italia settentrionale con particolare riferimento al Trentino e all'Alto Adige. Le risorse minerarie e i processi di produzione del metallo. In: De Marinis, R.C. (Ed.), *L'età del Rame: la Pianura Padana e le Alpi al tempo di Ötzi*. Catalogo della mostra. Compagnia della Stampa Massetti Rodella editori, Brescia, pp. 101-116.
- Angelini, I., Giunti, I., Artioli, G., 2011. Indagini archeometallurgiche su reperti dell'età del Rame della valle del Piave. *Quaderni di Archeologia del Veneto* Vol. XXVII, 107-115.
- Anguilano, L., Angelini, I., Artioli, G., Moroni, M., Baumgarten, B., Oberrauch, H., 2002. Smelting slags from Copper and Bronze Age archaeological sites in Trentino and Alto Adige. In: D'Amico, C. (Ed.), *Atti II Congresso Nazionale di Archeometria*. Bologna 29 gennaio-1 febbraio 2002, Pàtron Editore, Bologna, pp 627-638.
- Artioli, G., Angelini, I., Burger, E., Bourgarit, D., 2009. Petrographic and chemical investigation of the earliest copper smelting slags in Italy: towards a reconstruction of the beginning of copper metallurgy. *Proc. 2nd Intern. Conference "Archaeometallurgy in Europe 2007"*, Aquileia, 17-21 June 2007. *Proc. CD. Printed in the Selected Papers Volume*, AIM, Milano, pp. 12-20.
- Artioli, G., Angelini, I., Nimis, P., Addis, A., Villa, I.M., 2013. Prehistoric copper metallurgy in the Italian Eastern Alps: recent results. *Historical Metallurgy* 47, 51-59.
- Bourgarit, D., 2007. Chalcolithic copper smelting. In: La Niece, S., Hook, D., Craddock, P. (Eds) *Metals and mines. Studies in archaeometallurgy*. The British Museum—Archetype Publications, London, pp. 3–14.
- Cattoi, E., D'Amico, C., Fabris, S., 1995. Studio petroarcheometrico di scorie di fusione della fine dell'Età del Bronzo e confronti con scorie dell'Età del Rame/Bronzo Antico in Trentino. *Preistoria Alpina* 31, 125-145.
- Cattoi, E., D'Amico, C., Gasparotto, G., Girani, M., 1997. Petroarchaeometry of copper smelting slags in Trentino: provenance and process data. *Preistoria Alpina* 33, 151-154.
- Cierny, J., 2008. *Prähistorische Kupferproduktion in den südlichen Alpen: Region Trentino Orientale*, Der Anschnitt Vol. 22. Bergbau-Museum, Bochum.

- 257 Cierny, J., Marzatico, F., Perini, R., Weisgerber, G., 2004. La riduzione del rame in località Acqua
258 Fredda al passo del Redebus (Trentino) nell'età del Bronzo Recente e Finale. In:
259 Weisgerber, G., Goldenberg, G. (Eds.), 2004. Alpenkupfer – Rame delle Alpi. Der
260 Anschnitt, Vol. 17. Deutsches Bergbau Museum, Bochum. Pp. 125-154.
- 261 Colpani, F., Angelini, I., Artioli, G., Tecchiati, U., 2009. Copper smelting activities at the Millan
262 and Gudon Chalcolithic sites (Bolzano, Italy): chemical and mineralogical investigations
263 of the archaeometallurgical finds. In: Moreau, J.F., Auger, R., Chabot, J., Herzog, A.
264 (Eds.) Proc. ISA 2006, 36th Intern. Symposium on Archaeometry, Quebec City, Canada 2-
265 6 May 2006. Cahiers d'archéologie du CELAT, n. 25, Série Archéométrie, n. 7. CELAT,
266 Université Laval, Quebec, pp. 367-374.
- 267 D'Amico, C., Gasparotto, G., Pedrotti, A., 1998. Scorie eneolitiche di Gaban e Acquaviva (Trento)
268 caratteri, provenienza ed estrazione del metallo. In: D'Amico, C., Albore Livadie, C. (Eds)
269 Le Scienze della Terra e l'Archeometria. Istituto Universitario Suor Orsola Benincasa,
270 CUEN Napoli, pp. 31-38.
- 271 Fasani, L., 1988. La sepoltura e il forno di fusione de La Vela Valbusa (Trento). *Preistoria Alpina*
272 24, 165-181.
- 273 Höppner, B., Bartelheim, M., Huijsmans, M., Krauss, R., Martinek, K.P., Pernicka, E., Schwab, R.,
274 2005. Prehistoric copper production in the Inn Valley (Austria), and the earliest copper in
275 central europe. *Archaeometry* 47, 293-315.
- 276 Marzatico, F., 1997. L'industria metallurgica nel Trentino durante l'età del bronzo. In: Bernabò
277 Brea, M., Cardarelli, A., Cremaschi, M. (eds.), *Le terramare. La più antica civiltà padana*,
278 Catalogo della mostra. Electa, Milano, pp. 576-972.
- 279 Metten, B., 2003. Beitrag zur spätbronzezeitlichen Kupfermetallurgie im Trentino (Südalpen) im
280 Vergleich mit anderen prähistorischen Kupferschlacken aus dem Alpenraum. *Metalla* 10,
281 1-122.
- 282 Nimis, P., Omenetto, P., Giunti, I., Artioli, G., Angelini, I., 2012. Lead isotope systematics in
283 hydrothermal sulphide deposits from the central-eastern Southalpine (northern Italy). *Eur.*
284 *J. Miner.* 24, 23-37. DOI: 10.1127/0935-1221/2012/0024-216
- 285 Pearce, M., 2007. Bright blades and red metal. Essays on north Italian prehistoric metalwork.
286 *Accordia Specialist Studies on Italy*. Vol. 14. Accordia Research Institute, University of
287 London.
- 288 Pedrotti, A., 2002. L'età del Rame. In: Lanzinger, M., Marzatico, F., Pedrotti, A. (Eds) *Storia del*
289 *Trentino*, Vol. 1, La preistoria e la protostoria, Il Mulino, Bologna, pp. 183-254.
- 290 Perini, R., 1971. I depositi preistorici di Romagnano – Loc (Trento). *Preistoria Alpina* 7, 7-106.

- 291 Perini, R., 1989. Testimonianze di attività metallurgica dall'Eneolitico alle fasi finali dell'Età del
292 Bronzo nel Trentino. In: "Per Giuseppe Šebesta: scritti e nota bio-bibliografica per il
293 settantesimo compleanno". Biblioteca Comunale di Trento, Trento, pp. 377-404.
- 294 Pernicka, E., Begemann, F., Schmitt-Strecker, S., Wagner, G.A., 1993. Eneolithic and Early Bronze
295 Age copper artefacts from the Balkans and their relation to Serbian copper ores.
296 *Praehistorische Zeitschrift* 68, 1–54.
- 297 Pernicka, E., Salzani, P., 2011. Remarks on the analyses and future prospects. In: Aspes A. (Ed.), I
298 bronzi del Garda. Memorie del Museo Civico di Storia Naturale di Verona, Verona, pp. 89-
299 98.
- 300 Šebesta, G., 2000. La via del rame. Museo degli Usi e Costumi della Gente Trentina, S. Michele
301 all'Adige.
- 302 Tecchiati, U., 1991. *Praehistorische Bronzefunde* conservati al Museo Civico di Rovereto (Trento):
303 le asce. *Annali dei Musei Civici di Rovereto* 7, 3-36.
- 304 Tecchiati, U., 2009. Recenti ricerche sull'età del Rame in Val d'Isarco (Bolzano). Con un
305 contributo di Lorna Anguilano sulle analisi chimico-petrografiche di scorie di fusione. In:
306 Atti del 2 Congresso Internazionale «Ricerche paleontologiche nelle Alpi occidentali» in
307 ricordo di Piero Barocelli e Osvaldo Coisson, Pinerolo, 17-19 Ottobre 2003.
- 308 Villa, I.M., 2009. Lead isotopic measurements in archeological objects. *Archaeol. Anthropol. Sci.* 1,
309 149–153.
- 310 Weisgerber, G., Goldenberg, G. (Eds.), 2004. *Alpenkupfer – Rame delle Alpi. Der Anschnitt*, Vol.
311 17. Deutsches Bergbau Museum, Bochum.
- 312 Zammattéo, P., 2009. L'arte mineraria e la sua memoria in Trentino. Publistampa Edizioni, Pergine
313 Valsugana.