

ACCEPTED MANUSCRIPT • OPEN ACCESS

Multifunctional structural composites for thermal energy storage

To cite this article before publication: Giulia Fredi *et al* 2020 *Multifunct. Mater.* in press <https://doi.org/10.1088/2399-7532/abc60c>

Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2020 The Author(s). Published by IOP Publishing Ltd..

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

Everyone is permitted to use all or part of the original content in this article, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions may be required. All third party content is fully copyright protected and is not published on a gold open access basis under a CC BY licence, unless that is specifically stated in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

Multifunctional Structural Composites for Thermal Energy Storage

Giulia Fredi*, Andrea Dorigato, Luca Fambri and Alessandro Pegoretti*

University of Trento, Department of Industrial Engineering and INSTM research unit

Via Sommarive 9, 38123 Trento, Italy

* Corresponding Authors:

Giulia Fredi: giulia.fredi@unitn.it; +390461283944; <https://orcid.org/0000-0001-9987-1786>

Alessandro Pegoretti: alessandro.pegoretti@unitn.it; +390461282452; <https://orcid.org/0000-0001-9641-9735>

Abstract

This review introduces the concept of thermal energy storage (TES) and phase change materials (PCMs), with a special focus on organic solid-liquid PCMs, their confinement methods and their thermal management applications at low-medium temperatures (0-100 °C). It then investigates the approach of embedding TES and thermal management functionalities in structural materials, through the development of multifunctional polymer composites that could find applications where weight saving and temperature management are equally important. The concept of structural TES composite is presented through the description of three case studies about thermoplastic structural or semi-structural composites containing a paraffinic PCM: (i) a polyamide/glass laminate containing a microencapsulated or shape-stabilized paraffin; (ii) a polyamide-based composite reinforced with discontinuous carbon fibers and containing paraffin microcapsules, and (iii) a carbon fiber laminate with a reactive thermoplastic acrylic matrix and a microencapsulated paraffin.

Keywords: Phase change materials; thermal energy storage; multifunctional composites; thermoplastic composites; microencapsulation.

Contents

1		
2		
3		
4		
5		
6	1. Thermal energy storage (TES).....	3
7	1.1. Classification of TES technologies	4
8		
9	2. Latent heat TES and phase change materials (PCMs).....	7
10	2.1. Selection and properties of a PCM.....	8
11	2.2. Classification of PCMs	9
12	2.3. Confinement techniques for organic PCMs	12
13	2.4. Applications of PCMs for heat management	16
14		
15	3. Multifunctional composites	20
16	3.1. Structural polymer composites	21
17	3.2. Multifunctionality of polymer composites	24
18	3.3. Structural and semi-structural TES composites.....	24
19		
20	4. Thermoplastic composites for TES	28
21	4.1. Case study 1: polyamide/glass laminates containing paraffinic PCMs	28
22	4.2. Case study 2: PCM microcapsules in semi-structural carbon/polyamide composites	34
23	4.3. Case study 3: reactive thermoplastic resin as a matrix for multifunctional carbon-fiber	
24	laminates.....	44
25		
26	5. Conclusions and future perspectives	51
27		
28		
29		
30		
31		
32		
33		
34		
35		
36		
37		
38		
39		
40		
41		
42		
43		
44		
45		
46		
47		
48		
49		
50		
51		
52		
53		
54		
55		
56		
57		
58		
59		
60		

1. *Thermal energy storage (TES)*

The growing concerns about climate change, depletion of fossil fuels, and greenhouse gases emissions have recently attracted the attention of researchers, industries, and governments on technologies aimed at increasing efficiency in energy use. Since the routes of energy production based on fossil fuels have been lately undoubtedly related to environmental pollution and global warming, the research in the last decades has focused on sustainable and renewable energy sources, such solar, wind, and geothermal energy [1]. The wide diffusion of such sources is hindered by two main obstacles, namely their high initial plant cost and their intermittent nature. Although the first issue will be attenuated by technological development in the next years, the most effective answer to the second issue – i.e. source intermittency – relies in boosting energy storage technologies. The amount of solar energy varies on a daily and seasonal time scale, and the power and consistency of geothermal and wind sources can be unpredictable; therefore, renewable energy production plants must be supplemented with energy storage systems, to provide a significant and constant energy output even in the off-peak periods [1, 2]. Energy storage systems can also increase the efficiency of conventional energy sources, as they can help to decrease equipment sizes and initial and maintenance costs, to boost plant flexibility and efficiency, and to reduce the necessity of emergency power generators that would consume primary energy sources [3, 4].

Energy storage systems can be classified according to the intermediate energy form, which can be chemical, electrical, electrochemical, mechanical, or thermal [1]. Among energy storage systems, particularly interesting for some applications is thermal energy storage (TES), defined as the temporary storage of excess heat that can be used where and when needed. TES technologies can reduce the mismatch between thermal energy demand and availability, thereby contributing to a more efficient exploitation of intermittent energy sources [5]. Compared to other energy storage systems, the storage of energy in the form of heat (or cold) exhibits longer storage times and higher efficiency [1]. The cycle of a TES system, reported in Figure 1, comprises charging, storage and discharging steps.

TES technologies are currently employed for specific purposes in three main cases, namely (i) to store waste/excess heat that can be released when needed, e.g. to recover waste industrial heat [6], or in solar thermal power plants during peak periods [7]; (ii) to keep the temperature in a specific range, e.g. in buildings to store excess energy during the day and release it at nighttime [8], or for body temperature regulation through smart thermoregulating garments [9]; (iii) to temporarily store heat and prevent a temperature rise that would otherwise damage a component, as in the thermal management of electronic devices [10].



Figure 1. Typical working cycle of a TES system, showing the charging, storage and discharging steps and the variation of stored energy over time.

In some applications the desired product is the stored and released thermal energy, as in the cases (i) and (ii): these are generally referred to as examples of “thermal energy storage *properly said*”, and they normally need energy storage systems with high thermal capacity, to store as much energy as possible. In other applications, the excess heat is stored mainly to avoid a dangerous rise in temperature, as in case (iii): these are examples of “thermal management” (TM), and their main requirement is usually a well-defined energy storage rate. It is not easy to distinguish between TES *properly said* and TM. Some other classifications categorize as TES *properly said* only the case (i), while the other cases are examples of TM as they must keep temperature in an optimal range. This review discusses about TES or TM without a strict distinction, although the case studies presented in Section 4 could be more suitably employed for thermal management applications.

1.1. Classification of TES technologies

The most common classification of TES technologies is based on the way of varying the internal energy of the storage medium. Thermal energy can be stored and released through a temperature variation (*sensible heat TES*, SH-TES), an endo/exothermic phase change (*latent heat TES*, LH-TES), or a thermochemical reaction (*thermochemical heat TES*, TH-TES) [5]. The selection of a TES system over another depends on several parameters, such as the required heat storage period (hours, months, days), economic considerations, working temperature, available volume, as reported in Table 1 [11]. The following paragraphs summarize the characteristics and the governing equations of each of the three TES classes.

Table 1. Main performance parameters of sensible, latent and thermochemical heat TES technologies (adapted from [11]).

TES system	Capacity (kWh/t)	Efficiency (%)	Storage period (h, d, m)	Cost (€/kWh)
Sensible heat	10-50	50-90	d/m	0.1-10
Latent heat	50-150	75-90	h/m	10-50
Thermochemical heat	120-250	75-100	h/d	8-100

1.1.1. Sensible heat storage (SH-TES)

In SH-TES, energy is stored (and released) via an increase (or a decrease) in the temperature of the storage medium. The enthalpy variation is proportional to the temperature difference, as represented in Figure 2a. The energy stored in the system is defined by Equation (1) as

$$\Delta E = \int_{H_1}^{H_2} mdH = m(H_2 - H_1) = \int_{T_1}^{T_2} mcdT = mc(T_2 - T_1), \quad (1)$$

where ΔE is the total amount of energy stored in the storage medium (J), m is the mass of the storage medium, H_1 and H_2 the initial and final enthalpy values (J/g), c the specific heat capacity (J/(g·K)) and T_1 and T_2 the initial and final temperature (°C) [12]. An analogous equation can be written for the energy release, which results in the cooling of the storage medium. The effectiveness of a storage medium and the total amount of stored/released energy depends on the available mass and volume, while a higher specific heat capacity results in increased energy storage per unit mass [13]. The medium should also be non-toxic, not expensive, and should maintain long-term stability over repeated thermal cycles. Typical materials used as sensible heat storage media are liquids such as water, oils or molten salts, or solids such as metals or rocks [14-16].

1.1.2. Latent heat storage (LH-TES)

LH-TES involves the storage and release of heat through the phase transition of a phase change material (PCM). The vast majority of LH-TES systems are based on the melting-solidification transition, while evaporation-condensation phase changes are generally avoided, as the associated high volume variation increases the complexity of the confinement unit [12]. The variation of enthalpy in a solid-to-liquid phase transition is illustrated in Figure 2b. During an energy storage process, the medium initially behaves like an SH-TES unit and absorbs sensible heat, which increases its temperature. This behavior continues until the medium temperature reaches the phase change temperature (T_{pc}), which is maintained up to completion of the phase transition. In this step, the absorbed energy is equal to the latent heat of phase change $\Delta H_{pc} = H_f - H_s$. A further increase in absorbed energy brings a further increase in temperature: the slope of the enthalpy-temperature curve depends on the specific heat

capacity of the medium in the liquid state and can be different from the slope between T_1 and T_{pc} . The total enthalpy variation ΔE (J) of such process is defined by Equation (2), as

$$\Delta E = \int_{H_1}^{H_2} mdH = m(H_2 - H_1) = \int_{T_1}^{T_{pc}} mc_S dT + m\Delta H_{pc} + \int_{T_{pc}}^{T_2} mc_L dT, \quad (2)$$

where ΔH_{pc} is the latent heat of phase change, T_{pc} is the phase change temperature and c_S and c_L are the specific heat capacity of the solid and liquid phase, respectively [12]. Generally, the absorbed latent heat is considerably higher than the sensible heat, which implies that LH-TES systems normally require less material usage, as they can store a high amount of energy in a smaller mass and volume.

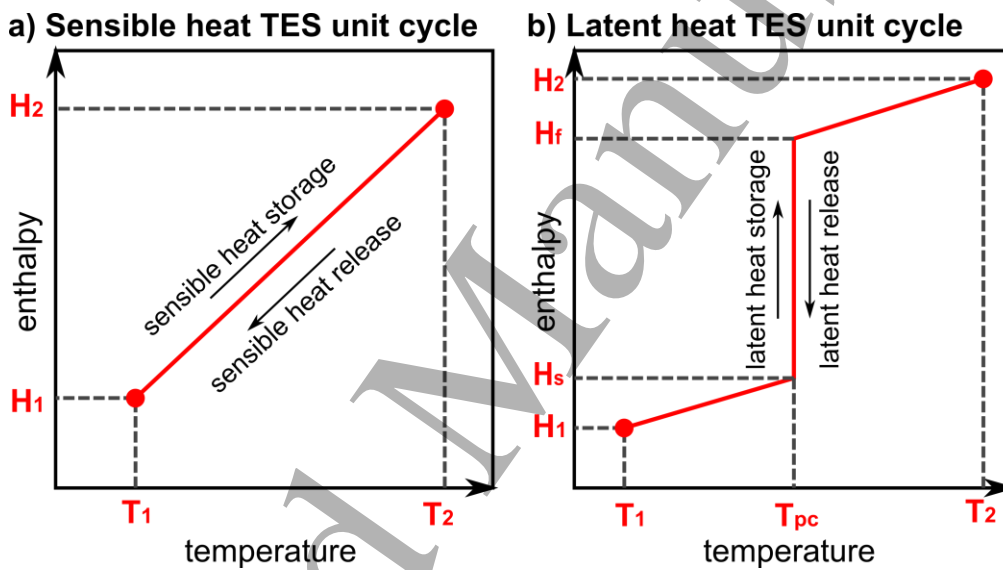


Figure 2. Variation of enthalpy of the storage medium as a function of its temperature in (a) an SH-TES unit cycle and (b) a LH-TES unit cycle (adapted from [1]).

1.1.3. Thermochemical heat storage (TH-TES)

Thermochemical heat storage refers to the techniques for storing and releasing heat through reversible endo/exothermic thermochemical reactions, as represented in Equation (3), as



During an endothermic reaction (charging), the storage medium (S_1) absorbs heat from the surrounding environment and it typically splits into two or more chemical substances (S_2 and S_3) which can be stored individually for a long time: The reverse reaction represents the discharging process, and the reaction between S_2 and S_3 releases the same amount of heat stored during the endothermic reaction. The total exchanged heat depends on the reaction enthalpy and the quantity of material.

TH-TES materials can be further classified as chemical or sorption systems. In chemical systems, a considerable amount of heat is generated from an exothermic synthesis reaction, and their working principle is properly described by the model reaction reported in Equation (3). In sorption systems, a gas (the sorbate) reacts with a sorbent, which can be solid (absorption reactions) or liquid (adsorption reactions) [17].

The energy storage density of TH-TES materials is up to ten times higher than that of SH-TES media, and approximately two times higher than that of the most common LH-TES systems [17], as illustrated in Figure 3. The considerable heat storage density and efficiency (low heat losses) are at the basis of the great potential of TH-TES systems [18]. However, the full exploitation of this potential is only possible with an efficient heat and mass transfer to and from the storage volume. Boosting transfer efficiency and coping with slow reaction kinetics are the main issues to overcome for the scale-up and commercialization of TH-TES systems [17, 19]. Hence, the technological maturity of TH-TES is lower than that of the other two classes [20, 21].

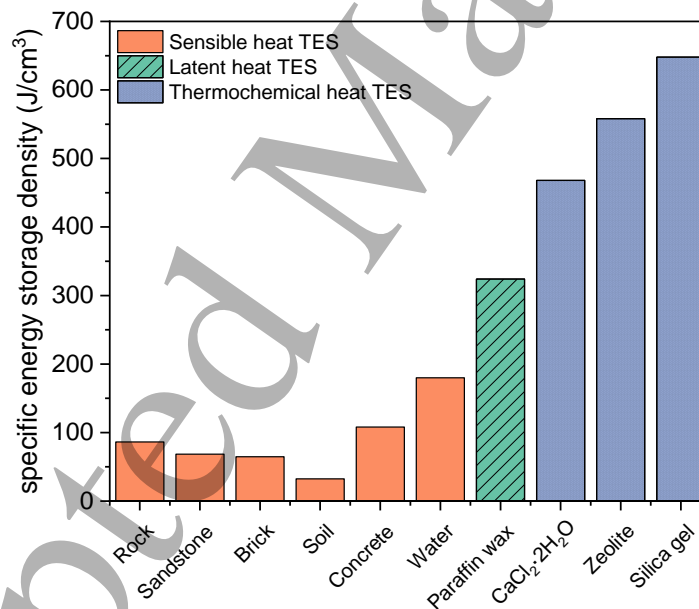


Figure 3. Comparison of specific energy storage density values of different sensible, latent and thermochemical TES media (adapted from [17]).

2. Latent heat TES and phase change materials (PCMs)

Latent heat TES has become attractive over the other TES technologies for a wide number of applications, and this stems from three main reasons. The first is that the phase change materials

(PCMs) exhibit a high energy density, which allow them to store and release a considerable amount of heat per unit mass or volume. Therefore, LH-TES systems require considerably less material compared to the traditional sensible heat storage systems, thereby increasing the system flexibility and reducing the initial and maintenance plant costs [2, 22, 23].

The second advantage is that PCMs store and release heat at nearly constant temperature, i.e. their phase change temperature (T_{pc}). During the energy storage phase, the PCM reaches the melting temperature and maintains the temperature constant over the whole melting process, regardless of the applied heat flux or small variations of the surrounding environment. Analogously, during heat release, the temperature is kept constant until the crystallization is completed. This feature is attractive in all the thermal management applications, where the temperature should be stably maintained in a certain range (e.g. indoor thermal regulation of buildings) or under a critical value (e.g. cooling of electronic devices) [24, 25].

The third advantage is represented by the technological maturity of LH-TES systems, which often makes LH-TES a preferred choice over thermochemical heat storage techniques [21]. Although TH-TES systems exceed LH-TES in energy storage density, solid-liquid PCMs are generally easier to handle and exhibit a little volume variation, thereby requiring smaller systems and less support equipment.

2.1. Selection and properties of a PCM

The number of PCMs available on the market is considerable and constantly growing. Hence, it is important to identify the key properties that make a PCM the most suitable for a specific application [26].

The primary criterion for selecting a PCM is the phase change temperature, which must be below that of the heat source but above that of the working environment. For LH-TES systems intended to avoid overheating, the most suitable PCM is the one that has the melting point just slightly below the maximum allowed temperature, as this reduces the melting rate and increases the thermal management window [27-29].

The phase change enthalpy is another very important property, as it represents the amount of energy that a PCM can store and release per unit mass or volume. A high phase change enthalpy leads to smaller system sizes, as less material is required to store a certain energy amount. PCMs with high melting enthalpy generally feature also a high specific heat capacity, which is desirable as it boosts the sensible heat stored before and after the melting temperature range, thereby enhancing the total exchanged heat [26, 30].

A suitable PCM should also feature a high thermal conductivity both in the solid and in the liquid phase, because this favors heat transfer from the source into the whole PCM mass [31, 32]. Other important qualities are the density and density variation upon phase transitions, the physical and

chemical stability over many thermal cycles, the chemical compatibility with the container, the non-corrosiveness and non-toxicity. Finally, the ideal PCM should exhibit congruent melting, negligible supercooling effect and completely reversible melting/crystallization cycles (low hysteresis) [22, 33, 34].

The PCMs currently available on the market do not match all these criteria at once, but the recent progresses in materials research and design are opening new possibilities for selecting the most suitable PCM with enhanced performance.

2.2. Classification of PCMs

The phase change materials are classified according to the type of phase transition they undergo in the TES process. As reported in Figure 4, PCMs can be subjected to a gas-liquid, solid-gas, solid-liquid or solid-solid transition. The solid-liquid PCMs are by far the most widely used, because they are cheaper and more numerous than the solid-solid PCMs and do not involve gas evolution, accompanied by a large volume variation unlike the solid-gas PCMs [12, 35]. Therefore, this review will focus on solid-liquid PCMs, which can be classified as organic PCMs, inorganic PCMs, and eutectic mixtures of organic and inorganic materials, according to the generally accepted classification [12, 36].

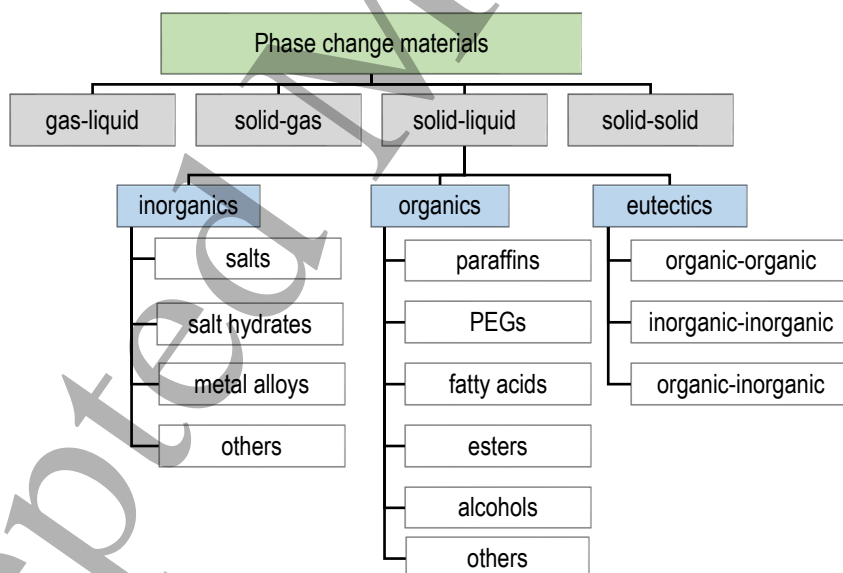


Figure 4. Classification of solid-liquid phase change materials (adapted from [34]).

2.2.1. Organic PCMs

Organic PCMs are the most widely used in the low-medium temperature range (0-100 °C) and are applied especially for the thermal management of buildings and electronic devices [24, 25]. They

comprise oligomers or polymers with a broad range of molecular weights, thus allowing a wide choice of the working temperature. Moreover, organic PCMs are generally inexpensive and easy to handle, exhibit a relatively high energy density, do not release volatile toxic substances, and are characterized by congruent melting and negligible supercooling. On the other hand, one of the main disadvantages is represented by their low thermal conductivity; this issue is addressed in different ways, namely by increasing the heat transfer area, by using highly thermally conductive containers or by adding metallic or carbon-based micro/nano-fillers [12, 37-39]. The second disadvantage of organic PCMs is related to their flammability, which is true especially for paraffin-based PCMs and derives from their hydrocarbon nature [40, 41]. However, their flash point is approx. 150-200 °C, well above their typical operating temperature range, and it increases with the molecular weight [42, 43]. Organic PCMs comprise paraffin waxes, poly(ethylene glycol)s, and fatty acids, but also other compounds such as ketones, esters, ethers, halogen derivatives, sulphur compounds and oleochemical carbonates [44].

2.2.1.1. *Paraffin waxes*

Paraffin waxes are the most diffused organic PCMs and consist in saturated hydrocarbons (*n*-alkanes) with chemical formula C_nH_{2n+2} . Paraffins embody all the aforementioned advantages of organic PCMs: they are generally cheaper and exhibit higher heat of fusion (200-240 J/g) and specific heat capacity (2.1-2.4 kJ/(kg·K)) than other organic PCMs [45]. Paraffins have a remarkable thermal stability over repeated thermal cycles (also after 1000-2000 cycles), a relatively low vapor pressure and an exiguous volume change upon phase transition [46]. Paraffins are largely available on the market with a broad range of chain lengths; those between C5 (pentane) and C15 (pentadecane) are liquid at room temperature, while those containing a higher number of carbon atoms are solid with a waxy appearance. Commercial paraffinic PCMs are mixtures of different hydrocarbons that do not exhibit phase segregation even after many thermal cycles, and the formulation is designed to match a specific transition temperature while maximizing the phase change enthalpy. Paraffins are resistant to chemical and environmental degradation, but they can manifest slow oxidation when exposed to oxygen [2], which encourages the use of sealed containers.

2.2.1.2. *Fatty acids.*

The second most popular organic solid-liquid PCM class is that of fatty acids, represented by the chemical formula $CH_3(CH_2)_{2n}COOH$ and classified as caprylic (C8), capric (C10), lauric (C12), myristyl (C14), palmitic (C16) and stearic (C18) acid, according to the number of carbon atoms. These fatty acids show high phase change enthalpies (45-210 J/g) and a wide range of melting temperatures (17°C to 70 °C). Fatty acids show high phase change enthalpies (45-210 J/g) and a wide range of melting temperatures (-5 to 70 °C) but are up to three times more expensive than paraffins and mildly corrosive

[47, 48]. Their most interesting feature is that they can be produced from bio-sources and are biodegradable, and therefore they have been the subject of extensive studies to replace paraffins for low/medium temperature applications, such as the solar energy storage and thermal management of indoor environment [45, 49].

2.2.1.3. *Poly(ethylene glycol)s (PEGs).*

Known also as poly(ethylene oxide)s (PEOs), poly(ethylene glycol)s are composed of dimethylene ether chains $\text{HO}-(\text{CH}_2\text{-O-CH}_2\text{-})_n\text{-CH}_2\text{-CH}_2\text{-OH}$ and are soluble in water and in some organic solvents, thanks to the amphiphilic nature of their chain combining hydrocarbon sequences and polar groups [44]. Also for this class of organic PCMs, the melting temperature and enthalpy increase with the molecular weight; for instance, PEG600 melts at 18.5 °C absorbing 121.1 J/g, while PEG2000 melts at 61.2 °C absorbing 176.2 J/g. PEGs are biodegradable and biocompatible and are also used in drug delivery systems [50]. This feature has expanded the use of PEG as a PCM in applications inside the human body, e.g. to subtract heat during the in-situ polymerization of acrylic bone cements and avoid overheating and damage to the surrounding biological tissues [51].

2.2.2. Inorganic PCMs

Inorganic PCMs exhibit an enthalpy per unit mass similar to their organic counterpart, but since they have a higher density, they can have a remarkably higher enthalpy per volume, thereby allowing the production of more compact TES systems [8]. Moreover, the thermal conductivity of inorganic PCMs can be considerably higher than that of their organic counterpart [24]. For these reasons, they are the preferred choice in the medium-high temperature range (100-1000 °C) and when there are no strict requirements on non-corrosiveness. Inorganic PCMs comprise several classes of materials, such as salts, salt hydrates and metal alloys [26].

2.2.2.1. *Salts and salt hydrates.*

Salts and salt hydrates have similar molecular structure, but the crystalline lattice of salt hydrates is not so closely packed and can easily host water molecules. Common salts and salt hydrates used as PCMs are NaNO_3 , KNO_3 , KOH , MgCl_2 , NaCl , $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$, $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$, and $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$, also called Glauber's Salt [26, 52]. While salts undergo a proper melting/crystallization transition, for salt hydrates the solid-liquid phase change is a dehydration-hydration process, in which the compound releases the coordinated water molecules becoming an anhydrous salt (or a lower hydrate). The vapor pressure of hydrated salts is considerably higher than that of the other solid-liquid PCMs and increases with the hydration degree; this can cause water loss and a deterioration of the TES properties. Moreover, salt

hydrates often suffer from supercooling problems. Above the dehydration temperature, the anhydrous salt may segregate and settle at the bottom of the container due to its higher density, which hinders and slows down the rehydration process. This issue is usually tackled by stirring, by adding excess water to favor solubilization of the whole mass of anhydrous salt, or by adding a thickening agent (e.g. borax, graphite) that reduces the extent of phase separation and often acts as a nucleating agent [22, 27, 53]. The phase change temperature of salts and salt hydrates ranges from 10 °C to 900 °C. However, for applications requiring a melting point up to 70-80 °C, organic PCMs are often preferred due to the lower cost, easier handling, lower vapor pressure, superior long term stability, lower supercooling and lower tendency to incongruent melting [22].

2.2.2.2. *Metal alloys.*

Metals have not been extensively investigated as PCMs so far, but they are starting to attract attention thanks to their considerable thermal conductivity and thermal stability. The most promising metallic PCMs are cesium, gallium, indium, tin and bismuth for low-temperature applications, and zinc, magnesium, and aluminum for applications at higher temperatures. Metallic PCMs cover a broad range of melting temperatures, from 30 °C of neat gallium to 660 °C of aluminum. However, PCMs with a lower transition temperature are not widely used due to their low phase change enthalpy. Conversely, high-melting metals such as Al and Mg alloys also exhibit a considerable phase change enthalpy (350-520 J/g) [7], which makes them attractive for high-temperature solar heating applications, in replacement of inorganic salts that are thermally unstable and prone to phase segregation [26].

2.2.3. **Eutectic PCMs**

Eutectic PCMs are mixtures of organic or inorganic compounds that melt and solidify congruently. They present a sharp melting point and a high phase change enthalpy, and their properties can be tailored to meet the requirements of a specific application. They are completely miscible in the molten state and freeze forming an intimate mixture of crystals [27], which accounts for a phase transition without segregation. As they are generally designed for a target application, they are usually more expensive than the other classes of PCMs [5, 12].

2.3. **Confinement techniques for organic PCMs**

Since organic solid-liquid PCMs are the most widely used materials for TES at low-medium temperatures (0-100 °C), this review will be focused on this type of TES materials. Among the major

drawbacks of organic PCMs is the need for confinement, to avoid leakage above the melting temperature. Confinement techniques can be divided into (i) encapsulation methods and (ii) shape-stabilization methods.

2.3.1. Encapsulation

Encapsulation methods involve a container that physically separates the PCM from the surrounding environment, is stable in the whole working temperature range and accommodates the phase transition and the associated volume change [54]. The containers can be of various sizes, shapes, and materials; one can talk about macro-, micro- or nano-encapsulation.

Macro-encapsulation is the simplest method of confining a PCM, as it involves the use of a box or a tank, made of a thermally conductive material (e.g. aluminum, stainless steel) that is chemically compatible with the PCM, to prevent any undesired chemical reactions [5, 43]. The container should be properly sealed to avoid the leakage also of the most fluid PCMs, and the design should always consider the volume expansion and contraction during the phase change. When the PCM is used for thermal management of buildings, the macro-capsule can be the concrete structure itself [55]. When there are no strict requirements on the strength, also thin flexible plastic (e.g. polyethylene) bags can be used, as they accommodate the volume change and do not require an ullage space [3].

On the other hand, micro- and nano-encapsulation feature microbeads with a polymeric or inorganic shell and a PCM core [43]. This confinement technique, with capsules in the micron- or sub-micron-scale range, offers two main advantages. The first is that a microencapsulated PCM is easy to handle and to embed in other materials such as gypsum and concrete by simple mixing, and it can be also added to liquids to produce PCM-enhanced heat transfer fluids [56]. The second advantage is represented by the augmented specific surface area (SSA), which increases the heat transfer surface. The capsule shells must be stable over many melting/solidification cycles and must not have any chemical interaction with the PCM.

There are several physical, physical-chemical, and chemical techniques available to produce PCM microcapsules (Table 2). Among all techniques, the most diffused, researched, and developed on industrial scale is the in-situ polymerization, which includes interfacial, suspension and emulsion polymerization [25, 57]. These techniques differ from each other mainly in terms of polarity and solubility of the monomers and the initiator. In the interfacial polymerization, the polymeric shell wall is the result of the polymerization of polar and non-polar monomers dissolved in the water and oil phase of an oil-in-water emulsion, respectively. The shell growing at the interface of the two phases becomes a barrier to diffusion and limits the reaction kinetics, thereby influencing the shell thickness and morphology. Common shell materials are polyurea, urea-formaldehyde and melamine-formaldehyde. In suspension polymerization, all the reactants are liposoluble and are dispersed in the water-based medium due to

continuous agitation and addition of surfactants. As the PCM must be the oil phase, with this technique it is difficult to encapsulate hydrophilic PCMs such as PEGs or salt hydrates. The shape and size of the resulting particles is strongly influenced by the stirring speed, amount of stabilizer, fraction of the monomer phases and relative viscosity of the droplets and the water medium. The emulsion polymerization is similar to the suspension polymerization, but the main difference is the hydrophilic nature of the initiator, which is dissolved in the water phase. Common shell materials for both these techniques are acrylic and styrenic polymers such as poly(methyl methacrylate) (PMMA), polystyrene, and styrene-divinylbenzene copolymers [58, 59].

Table 2. Advantages and disadvantages of the main microencapsulation methods (adapted from [57], with data from [60])

Technique	Advantages	Disadvantages	Particle size (μm)	Encap. ratio (%)
Physical methods				
Spray drying	- Low cost - Easy to scale-up - Versatility	- Particle agglomeration - High temperature - Uncoated particles - Difficult control of the particle size	0.1-5000	38-63
Solvent evaporation	- Low cost	- Difficult to scale-up	5-1500	
Physic-chemical methods				
Coacervation	- Versatility - Precise control of the particle size	- Difficult to scale-up - Agglomeration	2–1200	6–68
Sol-gel	- Inorganic shell with high thermal conductivity	- Difficult to bring to industrial level - Complex reactions involved	0.2–20	30–87
Chemical methods				
Interfacial polymerization	- Wide range of shell materials	- Moderate cost - Solvent handling	0.5–1000	15–88
Suspension polymerization	- Already at industrial level - Versatility		2–4000	7–75
Emulsion polymerization			0.05–5	14–67

Another interesting technique to prepare microcapsules is the sol-gel method, in which a solid shell forms through the gelation of a colloidal suspension (the “sol”). This suspension, which is often more accurately a solution, is prepared starting from a molecular precursor, such as a metal alkoxide $[\text{M}^n(\text{OR})_n]$ [61, 62]. Figure 5 illustrates the general sol-gel encapsulation route to obtain a silica (SiO_2) shell starting from tetraethyl orthosilicate (TEOS) as the molecular precursor.

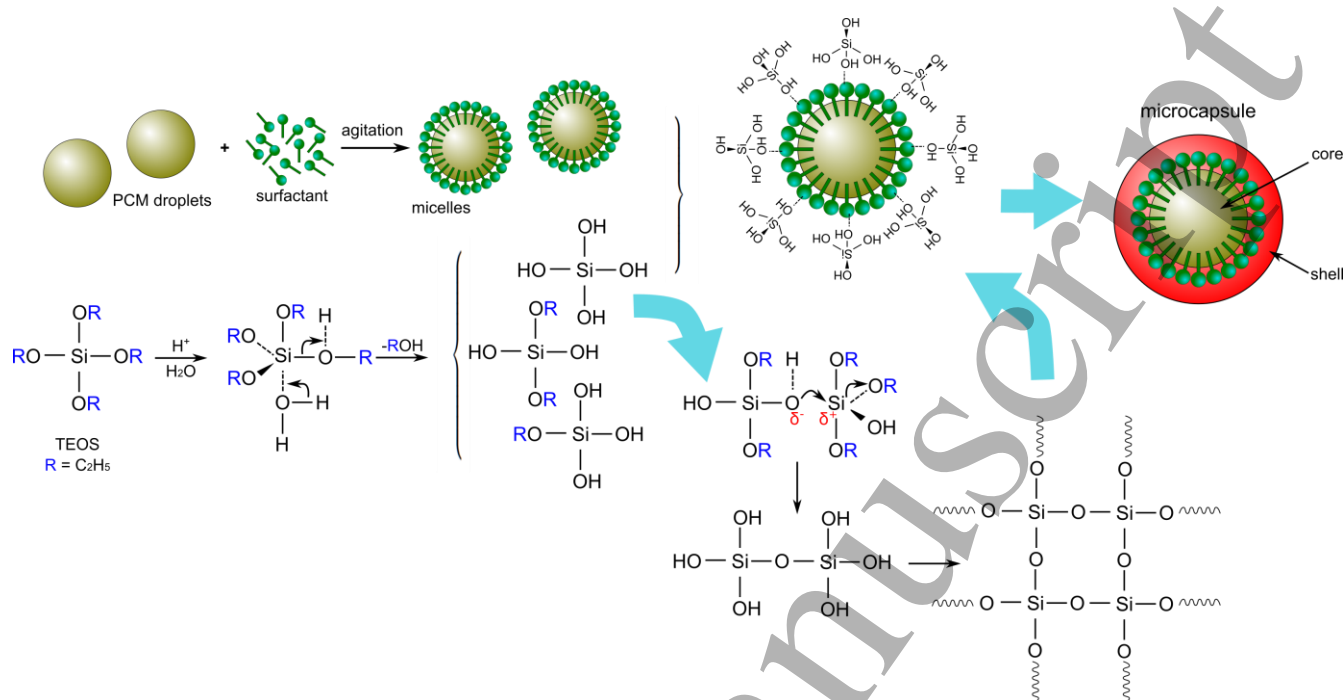


Figure 5. Encapsulation of an organic PCM via a sol-gel process starting from TEOS (adapted from [63]).

The PCM is first dispersed in an aqueous medium with the help of surfactants to form a stable oil-in-water (O/W) emulsion. The final micelle size and thus the capsule dimension are determined by the amount of PCM, the polarity of the aqueous medium and the type and concentration of surfactant. Separately, TEOS is dissolved in a water medium, e.g. a water-ethanol solution, and the pH of the solution is generally lowered to favor the hydrolysis reaction. Once hydrolysis is complete, the precursor solution is added to the PCM emulsion. Here, a controlled condensation reaction of the precursor happens around the PCM droplets, under basic conditions. The result of the condensation reaction is the formation of an extended silica network around the PCM droplet. The main advantage of sol-gel techniques is the possibility to form a ceramic (e.g. SiO_2 , TiO_2 , $CaCO_3$) shell, which is generally stronger and stiffer and exhibits a higher thermal conductivity than the polymeric shells [38]. On the other hand, pure metal oxides are usually brittle and subjected to cracks. To mitigate their fragile behavior, the molecular precursor can be chosen that contains a hydrocarbon side group, which will be present also in the final network, resulting in a hybrid organo-ceramic material. For example, organosilica shells produced from methyltriethoxysilane $CH_3Si(OCH_3)_3$ (MTES) are less brittle and more flexible than those produced from TEOS, thanks to the side methyl group that remains in the resulting network [64, 65].

2.3.2. Shape-stabilization

1
2
3 In the field of phase change materials, the term “shape-stabilization” is sometimes used as a
4 synonym of “confinement” and also includes the microencapsulation techniques [66]. However, the vast
5 majority of the dedicated literature refers to “shape-stabilization” to indicate all methods to prevent PCM
6 leakage *besides* encapsulation. Shape-stabilization techniques involve mixing the PCM with layered or
7 porous materials, inorganic nanofillers, or polymer matrices, to produce a compound without any
8 manifest leakage or exudation even when the PCM is in the molten state. Such techniques are generally
9 simpler and cheaper than microencapsulation, but the PCM is not completely isolated from the external
10 environment and some leakage may happen after several thermal cycles [67].

11
12 One of the simplest techniques to obtain a shape-stabilized PCM is the dispersion of nanoparticles,
13 such as carbon nanotubes (CNTs) [37], graphene oxide (GO) [68], expanded graphite (EG) [69, 70],
14 expanded graphite nanoplatelets (xGnPs) [71], nanoclays [53], metallic and metal oxide/nitride
15 nanofillers [72], which increase the mixture viscosity and prevent the leakage thanks to their high specific
16 surface area [66]. The shape-stabilization effect can be achieved by melt blending, vacuum
17 impregnation or grafting of the PCM chains onto the nanofillers. Moreover, the inclusion of carbon- or
18 metal-based fillers can enhance the thermal conductivity, thereby improving the energy storage rate and
19 efficiency especially of in the case of organic PCMs [28].

20
21 An analogous effect of enhanced thermal conductivity can be achieved by shape-stabilizing the
22 PCM through a highly conductive foam, where the PCM can be accommodated within the
23 interconnected porosity. Such foams are generally metallic, ceramic, or carbon-based and are
24 characterized by a high porosity, interesting mechanical properties and thermochemical stability [33].

25
26 Blending organic PCMs with polymer matrices is another diffused technique to prevent leakage
27 [12]. One of the most widely used strategies consists in combining paraffinic PCMs with polyolefins like
28 polyethylene (PE) and polypropylene (PP), due to their physical-mechanical properties and the chemical
29 compatibility with paraffins, but other commonly used polymers are acrylics, poly(vinyl chloride),
30 polyurethanes and elastomers as ethylene-propylene diene monomer (EPDM) rubbers [12, 73-75].
31 However, in many cases the satisfactory heat storage properties are accompanied by a decreasing in
32 the mechanical performance after PCM addition [73], which is noticed especially above the PCM melting
33 transition. This often leads to the conclusion that PCM-polymer blends are not suitable as load bearing
34 materials [73].

35 36 37 38 39 40 41 42 43 44 45 46 47 48 49 50 **2.4. Applications of PCMs for heat management**

51
52 Due to their ability to store a large amount of heat at a nearly constant temperature, PCMs are
53 interesting not only for pure thermal storage applications, for example in solar-thermal power plants, but
54 also for helping to keep the temperature in an optimal range. Examples of PCMs applied for thermal
55 management can be found in buildings [76], smart textiles [77], electronic devices [78], anti-icing
56
57
58
59
60

1
2
3 coatings [79], thermoregulating packaging [80], and also biomedical applications [51]. The following
4 sections report some of the most representative examples.
5
6

7 **2.4.1. Thermal management in buildings**

8
9 In the last decades, energy consumption in buildings has dramatically increased due to population
10 growth, climate change, and raised demand for thermal comfort and indoor environmental quality [81].
11 Housing and tertiary buildings account for the consumption more than 40 % of the total primary energy
12 and approximately 19 % of the overall CO₂ emissions [5, 81]. Considering the residential buildings,
13 among the energy end-uses, space heating and water heating are responsible for the largest portion of
14 total energy consumption, which is 57 % in the U.S., 71 % in China and 80 % in the E.U. [81]. Hence, it
15 is important to address and constantly improve the energy efficiency of buildings. One of the solutions
16 implemented in the last decades involves the use of PCMs in passive or active energy storage systems.
17
18
19
20
21
22

23 *2.4.1.1. Passive storage systems*

24
25 Passive storage systems include the heating/cooling technologies without an active mechanical
26 device and with little or no external energy inputs. An example of passive storage system is represented
27 by the inclusion of PCMs in wallboards, ceilings or flooring materials, which can store excess energy
28 during the day (peak hours) to release it during the night (off-peak hours), helping to regulate the
29 temperature also in extreme weather conditions [12]. As the indoor thermal comfort is generally
30 considered achieved in a temperature interval between 18 °C and 25 °C, the selected PCMs also
31 manifest phase transition in this range [82].
32
33
34
35

36
37 Even though the concept of using LH-TES in buildings has been known for decades, one of the first
38 systematic studies was performed in 1996 by Feldman and Banu [83], who fabricate PCM-enhanced
39 lab-scale gypsum wallboard samples. The PCM phase, represented by a mixture of fatty acids, was
40 introduced by impregnation (without further encapsulation or shape-stabilization), and it accounted for
41 approx. 25 % of the total wallboard weight. The authors evaluated the total TES performance of a room
42 lined with such wallboards and concluded that, after the shooting off of the heating/cooling system, the
43 room temperature could be maintained in the thermal comfort range for several hours longer than a
44 room with traditional wallboards, without impairing the air quality [84].
45
46
47
48

49
50 Particularly attractive are the technologies that allow the storage of excessive solar thermal energy,
51 in order to release heat during the night or to reduce overheating due to solar radiation in the peak
52 hours. An example of this second case is provided by Wang and Zhao [85], who proposed a
53 PCM-enhanced curtain to reduce the solar heat gain through the windows and thus the energy required
54 for cooling, especially useful for modern glass-wall buildings. Numerical investigation demonstrated that
55 the selection of the PCM with the most appropriate melting temperature plays a key role in determining
56
57
58
59
60

1
2
3 the curtain performance, and that the heat gain of the indoor space can be reduced of up to 16.2 % with
4 a PCM layer of 5 mm.
5

6 When talking about structural or rigid building elements, there are several ways of integrating PCMs.
7 Besides the aforementioned direct impregnation, other techniques are mixing microencapsulated PCMs
8 with construction materials, and adding a macroencapsulated or variously stabilized PCM as a
9 supplementary layer [24]. One of the most recent studies implementing the first approach is that of Bao
10 et al. [30], who developed a high performance PCM-enhanced cement composite for passive solar
11 buildings. The PCM phase is represented by a paraffin wax ($T_m = 28\text{ }^\circ\text{C}$) microencapsulated in polymeric
12 shells containing graphite flakes, added during microcapsule synthesis to enhance the thermal
13 conductivity. Such microencapsulated PCM was mixed with the cement matrix together with nanosilica
14 and short carbon fibers, in order to preserve the mechanical properties and further enhance the thermal
15 conductivity. There are some studies in which the PCM is added to construction materials not with the
16 purpose of indoor thermal management, but for the thermal protection of the material itself. As described
17 in the recent review by Šavija et al. [86], the insertion of a PCM in concrete can limit temperature
18 fluctuations and reduce the risk of thermally induced cracks.
19
20
21
22
23
24
25
26

27 28 2.4.1.2. *Active storage systems* 29

30 Active storage systems are used to store heat produced when the primary energy source is more
31 abundant or less expensive. In buildings, active storage systems based on PCMs store heat produced
32 by heating systems during the night, so that the energy peak is effectively reduced and shifted to
33 nighttime when the cost of electricity is lower. Lin et al. [87] developed a floor heating technology
34 integrated with shape-stabilized PCM panels. Such panels, made of paraffin with a melting temperature
35 of $52\text{ }^\circ\text{C}$ (75 wt%) and polyethylene as supporting material, were placed under a wood floor onto electric
36 heaters. Large-scale experiments proved that the system was effective in increasing the indoor
37 temperature and in keeping the temperature in an acceptable range long after the heaters were switched
38 off.
39
40
41
42
43
44
45
46
47

48 2.4.2. **Smart textiles** 49

50 The embedment of PCMs in textile fabrics leads to the production of smart textiles that help
51 regulating the body temperature and are particularly useful in situations of extreme weather conditions
52 [88]. One of the first examples of PCM-enhanced textiles was produced by NASA; nonadecane ($T_m =$
53 $32\text{ }^\circ\text{C}$) was added to garment fabrics (e.g. in the space suits) to limit the impact of the extreme
54 temperature changes to which the astronauts are subjected during space missions [89]. Later, such
55
56
57
58
59
60

1
2
3 smart thermoregulating textiles were employed to enhance the thermal comfort of mountain outdoor
4 clothing and apparel, but also of blankets, mattresses and pillow cases [12].

5
6 There are five main ways to embed a PCM in a synthetic textile: (a) mixing the PCM with the
7 melt/wet spun polymer in the form of core filament; (b) producing core-sheath fibers, in which the core
8 is composed by the PCM and the shell is the supporting polymer; (c) introducing PCM microcapsules in
9 the melt/wet spun polymer; (d) applying microencapsulated PCMs on fabrics using suitable binders or
10 coating materials; (e) adding a PCM-enriched inner layer (e.g. polyurethane foam containing PCM
11 microcapsules) [77]. Among these techniques, the first three methods are often preferred as they result
12 in versatile multifunctional polymer fibers with the PCM phase stably confined into the surrounding
13 polymer, which reduces the risk of removal during washing [90].
14
15
16
17
18

19 The embedment of PCMs in polymeric fibers is of interest to produce not only smart textiles, but
20 also multifunctional polymer filaments that can be co-woven with continuous reinforcing glass or carbon
21 fibers, to produce a multifunctional yarn containing the matrix, the reinforcement and the PCM. This is
22 an interesting route that can be explored to fabricate thermoplastic composites with TES properties.
23
24
25

26 **2.4.3. Thermal management of electronic devices**

27

28 Electronic devices are well known to be sensitive to temperature, since their performance and
29 lifetime span depend strictly on their maintenance in a precise temperature range, with a particular
30 attention to avoid overheating. As the electronic components are being equipped with increasingly
31 sophisticated electronics while their dimensions have decreased, the risk of overheating has also grown,
32 and without a proper thermal management system the heat generation and the associated temperature
33 rise may deteriorate the performance, bring critical components to failure and decrease the user-device
34 interaction comfort [78]. Overheating is among the most common causes of failure of electronic
35 components, as approximately 55 % of failures can be related to high temperature problems or poor
36 thermal management [91]. It has been shown that a decrease of 1 °C can decrease the failure rate of
37 up to 4%, and an increase of 10-20 °C can double the failure probability [91].
38
39
40
41
42
43

44 An effective thermal management system must also comply with the weight and size limitations, as
45 these design parameters are increasingly important for electronic components that must be carried
46 around, such as portable and wearable electronic devices, but also batteries and circuitry for electric
47 vehicles (EVs). Hence, PCMs are becoming an attractive alternative to more bulky solutions such as
48 the natural or forced convection (active cooling), also because electronic devices do not normally need
49 to operate continuously for long periods [10]. When the device is in a heat peak and its temperature
50 starts rising, the PCM melts and absorbs excess heat, thereby preventing an excessive temperature
51 burst (passive cooling). When the temperature starts decreasing again, the PCM crystallizes and
52 releases the heat back to the environment.
53
54
55
56
57

Pioneering experimental work of investigation on using PCMs on mobile electronic devices was carried out in 2004 by Tan and Tso [92], who assessed the efficacy of a passive cooling unit based on *n*-eicosane ($T_m = 37\text{ }^\circ\text{C}$) for the thermal management small hand-held personal computers (personal digital assistants). The PCM was contained in an aluminum case and placed under the heaters simulating the heat generation units of such a device, i.e. the processor and other integrated circuit packaging. The authors concluded that the PCM units were indispensable to keep the working temperature of the device under an acceptable threshold of $50\text{ }^\circ\text{C}$ and that the efficacy of the heat storage unit depended not only on the amount of PCM but also on its orientation, which determined the heat flux distribution in the whole device. The same concept was developed by Tomizawa et al. [93], who developed a passive cooling unit for mobile phones containing a commercial microencapsulated paraffin with a melting temperature of $32\text{ }^\circ\text{C}$. The PCM was mixed with polyethylene and molded as a sheet, which contributed to slow down the temperature increase, and this effect was more evident with thick sheets.

PCMs can be also employed for the thermal management of EV batteries, to support or replace the traditional cooling systems based on liquid/air circulation [27, 94]. The first attempts to integrate PCMs in automotive field date back to the early 2000s, when Al Hallaj and Selman [95] proposed a battery pack in which each cylindrical Li-ion cell was wrapped with a PCM layer with a melting temperature in the range $30\text{-}60\text{ }^\circ\text{C}$. The authors demonstrated experimentally and numerically that the total temperature fluctuation was considerably lower with the PCM.

Successive approaches tried to address the low thermal conductivity of PCMs and the need for improving the thermal uniformity inside the battery pack. The most promising solutions involved metal or graphite foams as shape-stabilizers and thermal conductivity enhancers [96]. More recently, Zou et al. [97] studied the introduction of various carbon based nanofillers (e.g. EG, CNTs, graphene) in a paraffin wax, to produce a shape-stabilized PCM to be employed in a 38120-type LiFeO_4 battery pack. They found that this composite PCM was able to reduce not only the maximum operating temperature, but also the temperature oscillations.

3. Multifunctional composites

A material can be labelled as multifunctional if it features a set of properties that make it capable of sustaining different types of stimuli at the same time and ready to perform different functions when required. Multifunctional materials combine properties chosen among the structural mechanical properties, like stiffness, strength and toughness, and the non-structural properties, like sensing

1
2
3 functions, optical and magnetic properties, self-healing, thermal/electrical conductivity or insulation,
4 corrosion resistance, tribological properties, and energy harvesting and storage [98-100].

5
6 Composite materials are particularly suitable to be designed as multifunctional, as they gather in
7 one material the properties of multiple phases. Composites consist of two or more distinct materials or
8 phases with remarkably different mechanical and/or physical properties, and therefore the properties of
9 the resulting material are noticeably different from those of each constituent, and the composition is
10 properly tailored to obtain the property set that best suits the specific application [101, 102].

11
12 Many natural and synthetic materials that perform multiple functions are polymer-matrix
13 composites. They combine outstanding polymer-related properties, like toughness and low density, with
14 the specific properties of the discontinuous phase(s), which can provide stiffness and strength but also
15 several non-structural functions [103]. The following Sections present a general introduction on
16 structural polymer composites and define the concept of multifunctionality in the combination of
17 structural and TES properties.

24 **3.1. Structural polymer composites**

25
26
27 Composite materials pervade our world. Besides being the most widespread material type among
28 biological materials, composites have been produced and used by mankind for thousands of years.
29 However, it is only in the last century, with the advent of high-strength synthetic fibers and the enormous
30 advances in polymer chemistry and technology, that composite materials can offer a performance
31 comparable or even superior to those of well-established structural materials [104].

32
33 Composites are generally constituted by a continuous phase, the *matrix*, and one or more
34 discontinuous phases, the *fillers*, which are generally stronger and stiffer than the matrix and therefore
35 can be also called *reinforcements* or *reinforcing agents* [105]. Composite materials can be classified
36 according to the matrix material as polymer matrix composites (PMCs), ceramic matrix composites
37 (CMCs) and metal matrix composites (MMCs). Each of these classes has a particular set of properties
38 and specific application fields, as the matrix has a strong influence on several mechanical properties of
39 the composite, such as transverse modulus and strength and the properties in shear and in
40 compression, as well as on the maximum service temperature [101].

41
42 Polymer matrix composites are the most widely used in structural and semi-structural applications
43 at low-medium temperatures (0-250 °C), due to their lightness and high specific stiffness and strength.
44 They combine a polymer matrix with one or more fillers, commonly added to improve stiffness, strength,
45 toughness, and high-temperature performance. As the mechanism of property improvement strongly
46 depends on the filler geometry, composites are generally classified according to the reinforcement type,
47 shape, and size. The reinforcement can be in the form of fibers or particles, as observable from the
48 commonly accepted classification reported in Figure 6. Continuous carbon, glass, or aramid fibers are
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 the reinforcements of election when high-end mechanical performance is required, while discontinuous
4 fibers are generally use as a reinforcement for semi-structural purposes, as the properties of
5 discontinuous-fiber polymer composites fill the property (and cost) gap between continuous fiber
6 composites and unreinforced plastics.
7
8

9 The polymer matrix can be either a thermoplastic or a thermosetting polymer. Although the vast
10 majority of high performance composites have a thermosetting (e.g. epoxy) matrix [104], thermoplastic
11 composites have received considerable attention in the last decades due to their undeniable
12 advantages. Thermoplastics are generally tougher than thermosets, and therefore they are more
13 damage tolerant and have a greater low-velocity impact resistance [106]. Moreover, they are fully
14 reacted, and thus they present a low risk of chemical hazard for the worker, who is not exposed to
15 low-molecular-weight components or by-products. Additionally, thermoplastics do not require
16 refrigeration and have an infinite shelf life. The shaping and consolidation time for thermoplastics is
17 shorter than that of the thermosets, as it takes minutes instead of hours. Nevertheless, thermoplastic
18 require high processing temperatures, in the range of 250-450 °C, considerably higher than the curing
19 temperatures for thermosets (120-175 °C), which demands for presses and tooling materials that can
20 withstand this temperature regime [106]. Due to the possibility of being remelted, thermoplastics can be
21 joined via techniques as resistance welding or ultrasonic welding. They can also be post-thermoformed,
22 which is very attractive as it suggests the possibility of producing continuous-fiber-reinforced flat boards
23 to be subsequently cut and thermoformed into the desired shape. However, since traditional continuous
24 carbon, glass or aramidic fibers have very little extensibility, this can be achieved only with very simple
25 geometries, and also the defect healing via remelting can hardly be practiced without fiber distortion
26 [101].
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

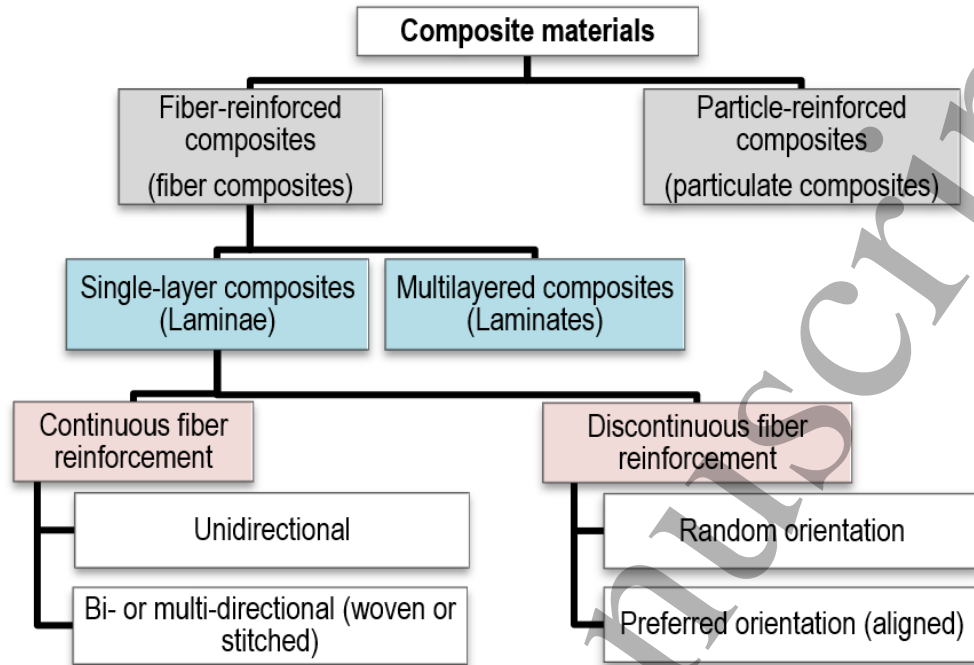


Figure 6. Classification of composite materials according to the geometry of the reinforcement (adapted from [101]).

The main advantages of structural polymer-matrix composites are (i) the possibility to be tailored for optimum strength and stiffness in the different loading directions, and (ii) the combination of low density and high strength and modulus. This latter aspect results in higher specific (i.e. normalized by density) mechanical properties than those of comparable aerospace metal alloys, which in turn allows designing lightweight structures, thereby leading to improved performance and fuel savings, especially in the automotive and aerospace industries. Other advantages of structural composites compared to lightweight metal alloys are the high fatigue life and the corrosion resistance [104]. Due to these features, structural composite materials are mainly applied in construction and transportation fields, but their application is expanding also in marine goods, sports equipment, and infrastructures.

On the other hand, among the main disadvantages of composite materials are the expensiveness of raw materials, fabrication, and assembly, as well as the higher sensitivity to temperature and moisture. Moreover, composite laminates exhibit poor strength in the out-of-plane direction where the matrix carries the primary load, but this aspect can be mitigated by orienting the reinforcement properly. Composites are also more susceptible than metals to impact damage, are prone to suffer from delamination, and can be challenging to repair.

3.2. Multifunctionality of polymer composites

Multifunctional materials combining structural and non-structural functions have enormous potential to impact future structural performance by reducing weight, volume, cost, and energy consumption while enhancing efficiency, versatility, and safety. Since they expand design possibilities and increase the material added value, they are attracting increasing interest from the industrial and academic point of view. New combinations of properties are being embedded in the next-generation of multifunctional materials, which can find applications in the automotive and aerospace industries, but also in civil engineering and in medicine [98]. However, the combination of properties of a multifunctional material should act synergistically and not parasitically. If the addition of self-sensing and self-healing capabilities to a structural material impairs its stiffness and strength excessively, the combination of properties in this material will not bring benefits at the system level [99].

When designing a multifunctional material, multifunctionality should be considered from the very early stages of the design process. Unlike natural materials, whose properties are the result of a locally random evolution process, in the synthetic engineering materials the design must start from the functions and then proceed in a specific direction. This is important because multifunctionality could be expressed at different dimension scales (at the level of the phase, the material or the structure), which must be taken into account during the design of the material and the prediction of final properties of the final component [103].

Composite materials achieve multifunctionality by gathering in one material the properties of multiple phases and at different dimension scales (from continuous fibers to nanometric fillers) [98]. Most of the recent developments in multifunctional materials tend to be polymer-matrix structural composites featuring one or more additional non-structural functions [107-114]. This strategy allows large weight savings at the system level, through the elimination or reduction in the number of multiple monofunctional constituents, and it gives better results than the conventional approach of optimizing weight and geometry of each individual subsystem [99].

3.3. Structural and semi-structural TES composites

Designing polymer composites as multifunctional can further expand the weight saving possibilities pursued when composites are selected as structural materials. The scientific literature reports multiple examples of multifunctional composites combining structural properties and a wide range of non-structural functions, which respond to a broad variety of needs in the most diverse applications.

An interesting field in which multifunctionality of polymer composites can be exploited, although not yet thoroughly investigated, is that of structural composites with thermal energy storage capability. As explained in Section 2.4, among the applications of TES materials are (i) the heat storage for

1
2
3 temperature control, for example in the buildings industry, or to produce smart textiles for body
4 temperature regulation, and (ii) the temporary storage of heat to prevent overheating, as in the cooling
5 systems for electronic devices.
6

7
8 When a TES material is used for thermal management, it is usually only an extra component added
9 to the main structure of a device. However, the resulting increase in weight and volume may be
10 unacceptable for some applications where weight and volume reduction are crucial design parameters.
11 In this case, it would be useful to have a multifunctional material that combines good mechanical
12 properties and the heat storage/management function. With such materials it would be possible to build
13 part of the structure with the “thermal battery” material, or, in other words, to design a structure that is
14 part of the thermal management system. This approach is similar to that developed for an outstanding
15 application of multifunctionality, i.e. the structural batteries, which are devices that can carry mechanical
16 load and store electrochemical energy simultaneously.
17

18
19 According to the authors’ opinion, these structural or semi-structural lightweight TES composites
20 would be attractive in four main applications:
21

- 22
23
24
25
26 1. In the transportations field, the considerable application of polymer composites in replacement of
27 traditional materials could complicate the thermal management in the indoor vehicle environment,
28 due to their different (generally lower) thermal conductivity and heat capacity. This could result in
29 an increasing difficulty in maintaining the indoor temperature in the human thermal comfort range.
30 This issue could be addressed by introducing a TES system able to store and release thermal
31 energy in the temperature range around the human comfort temperature (18-25 °C), and the overall
32 performance-to-weight ratio would be maximized if this TES material is part of the structural or semi-
33 structural components themselves. Moreover, a PCM-based material would decrease the energy
34 consumption related to the air conditioning system and the thermal conditioning system of batteries
35 and powertrain, which are the main auxiliary energy consumers in electric vehicles [115]. This
36 concept could be extended to other temperature ranges, which may be interesting for the
37 transportation of food, biomedical items, or other perishable goods.
38
39
40
41
42
43
44
45
46
47 2. In the field of portable electronics, there is an increasing tendency of enhancing the performance,
48 power and functionalities of the devices while reducing weight and volume. This trend brings issues
49 in the thermal regulation, especially in the peak power operations. Passive cooling systems based
50 on PCMs are attracting attention due to their capacity of maintaining the temperature under a certain
51 threshold value and of contrasting the momentaneous but rapid heat generation during peak power
52 operations [10]. However, in all the solutions implemented so far, the PCM is contained in an
53 additional module, while it would be advantageous to embed it directly inside the structural
54
55
56
57
58
59
60

1
2
3 components such as the phone or laptop cases. This concept can be useful for the thermal
4 management of all the electronic devices that must be carried around and need thermal
5 management; this group comprises not only mobile phones and laptops, but also the batteries of
6 electric vehicles [116]. Another interesting application in the electronics field would be the
7 production of PCM-enhanced circuit boards, traditionally made of glass fiber reinforced epoxy resin.
8
9

- 10
11
12 3. Among the main drawbacks of polymer-matrix composites, compared to metals or ceramics, are
13 the lower thermal resistance and the loss of mechanical properties with increasing temperature.
14 This can be detrimental for some applications where the composite material is subjected to external
15 heating in service, as in the case of luxury car chassis entirely made in carbon fiber composite.
16 Local overheating and loss of properties could be also determined by dynamic loading and lack of
17 heat dissipation, which can bring to premature failure by fatigue [117]. This effect, critical especially
18 for thermoplastic composites, could be limited by adding a PCM, which absorbs excess heat and
19 avoids temperature rise. This concept has been proven effective by Casado et al. [118], who
20 inserted a hydrated salt with a transition temperature of 50 °C in a polyamide-based composite
21 reinforced with glass fibers. In this case, however, the PCM was not employed as an additional
22 filler, but it was added in the gaps of the flanged plate made of the glass-reinforced polyamide.
23 Much more capillary would be the action of the PCM if it were dispersed in the whole composite
24 mass, or at least in those parts more subjected to fatigue damage.
25
26
27
28
29
30
31
32
33
34
35 4. One of the main problems of outdoor infrastructures operating in cold environments is the formation
36 and accretion of ice. Critical structures such as transmission lines, wind-driven power generators,
37 off-shore oil rigs, and means of transportation like aircrafts and ships can be damaged by the
38 excessive weight of the ice layer and the stresses induced by freeze-thaw cycles [119]. The
39 solutions implemented so far rely on heating methods, mechanical methods, or the circulation of
40 de-icing fluids underneath the surface, which are effective but extremely energy-consuming [120].
41 More recently, slippery or superhydrophobic coatings have been developed that prevent ice
42 adhesion or reduce ice shear strength, but they generally have low resistance to mechanical
43 abrasion and poor durability to the outdoor weather agents. For the structures built in polymer
44 composites, e.g. the wind turbine blades, an effective alternative could be the introduction of a PCM
45 with phase transition at approx. 0 °C in the whole composite thickness or only in the outermost
46 layers [79]. The heat released during crystallization of the PCM would help in decreasing the ice
47 accretion rate, while reducing the need for heating through an external energy supply.
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 In all these applications, PCMs are the ideal TES materials, as they work at a nearly constant
4 temperature and exhibit a high enthalpy per unit mass, thus being suitable for applications where weight
5 saving is a key factor. It is therefore fundamental to understand how the PCM addition influences the
6 mechanical properties of the host composite and how this effect varies below and above the PCM phase
7 change.
8
9

10
11 So far, this investigation has been carried out to some extent only on construction materials like
12 concrete and gypsum, in which a PCM phase is added to enhance the thermal management of indoor
13 environments while reducing the energy consumption for indoor heating/cooling. The majority of TES
14 systems integrated in walls or flooring materials are represented by organic PCMs with a phase
15 transition temperature in the range 18-25 °C, microencapsulated in polymeric shells. The
16 characterization of such PCM-enhanced construction materials generally evidences that an increase in
17 the PCM content brings an increase in thermal management properties and a decrease in power
18 consumption. On the other hand, PCM addition determines a lowering of compressive and flexural
19 properties, due to the introduction of a less mechanically strong phase. Therefore, the authors of the
20 revised papers generally conclude that it is important to select the PCM that determines the smallest
21 decrease in mechanical properties while providing the highest TES capability, and that it is fundamental
22 to identify the optimal PCM content to obtain a material with the most suitable property set for a specific
23 application [121].
24
25

26
27 The open scientific literature provides some examples of polymers containing a PCM. Organic
28 PCMs are usually introduced into polymer matrices in three ways: (i) without further stabilization
29 (formation of a blend) [73, 122-124], (ii) as PCM microcapsules [125-128], or (iii) shape-stabilized with
30 layered materials or nanofillers, which are generally carbonaceous or ceramic [129-131]. On the other
31 hand, very few cases are reported of PCM-enhanced polymers employable as structural materials.
32 Excluding the field of construction materials, there is a surprisingly limited number of publications about
33 materials designed to combine structural and TES functions. One of the first reported examples is that
34 presented by Wirtz et al. [132], who developed a sandwich structure made of a graphitic foam
35 impregnated with paraffin ($T_m = 56$ °C) as the core and carbon/epoxy laminates as the skin, intended
36 for the thermal management of electronic devices. The graphitic foam had the twofold function of
37 immobilizing the molten paraffin and enhancing the thermal conductivity, while the carbon/epoxy skins
38 increased the flexural stiffness. The literature reports several other studies on carbon foams as shape-
39 stabilizers for organic PCMs, but they are generally employed only to enhance the thermal conductivity,
40 and little attention is given to the mechanical performance [133-135].
41
42

43
44 More recently, a research group at RMIT University (Melbourne, Australia) developed a woven glass
45 fiber/epoxy laminate containing paraffin microcapsules and investigated the impact of the PCM on the
46 mechanical and thermal properties of the host laminate [136-138]. An increase in the PCM weight
47
48
49
50
51
52
53

1
2
3 fraction determined a decrease in the tensile, flexural and compressive properties, due to the
4 intervention of additional damaging mechanisms as delamination, matrix cracking, and fiber/matrix
5 debonding, and the authors indicated the weak interfacial adhesion between the capsules and the matrix
6 as one of the causes for the decrease in mechanical performance. On the other hand, the mild
7 processing conditions allowed retaining most of the initial PCM enthalpy, but thermogravimetric analysis
8 (TGA) showed that a fraction of the capsules was damaged during processing. Nevertheless, these
9 results were promising for the development of such structural TES polymer-matrix composites, which
10 exhibited a phase change enthalpy of up to 40 J/g.
11
12
13
14
15

16 Our group has recently expanded the investigation of structural and semi-structural TES
17 composites, by considering and comparing several combinations of polymer matrices, reinforcements
18 and PCMs. The research work has seen the production and characterization of epoxy/carbon
19 composites containing paraffin stabilized with carbon nanotubes (CNTs) or microencapsulated paraffin
20 [139-145], polyamide composites enhanced with a microencapsulated paraffinic PCM and reinforced
21 with continuous or discontinuous fibers [146-150], and a fully biodegradable laminate based on
22 thermoplastic starch, ultra-thin wood laminae and poly(ethylene glycol) (PEG) [151].
23
24
25
26
27
28

29 **4. Thermoplastic composites for TES**

30
31
32 Thermoplastic composites have received considerable attention in the last decades, due to some
33 advantages over their thermosetting counterpart, as explained in Section 3.1. [104, 106]. Even though
34 the use of thermoplastic composites can be advantageous for some applications, a very exiguous
35 number of examples have been reported in the literature that deal with thermoplastic structural or semi-
36 structural composites containing organic PCMs. The advantages and drawbacks of producing such
37 composites are discussed through the presentation of three case studies, which illustrate the materials
38 selection, sample preparation, and results of the characterization.
39
40
41
42
43

44 **4.1. Case study 1: polyamide/glass fiber laminates containing paraffinic PCMs**

45
46 The first case study deals with the introduction of two powder-like paraffinic PCMs in
47 polyamide12(PA12)/glass fiber(GF) bidirectional laminates [146]. The work aimed at comparing the
48 performance of two PCMs with similar phase change enthalpy (≈ 200 J/g) and temperature (≈ 43 °C)
49 when embedded in a traditional thermoplastic matrix reinforced with continuous glass fibers and at
50 studying the properties of these laminates as a function of the PCM content. The main difference
51 between the two employed PCMs is the confinement technique. The first PCM is the microencapsulated
52 paraffin MPCM43D produced by Microtek Laboratories Inc. (Dayton, OH, US), with an average capsule
53
54
55
56
57
58
59
60

1
2
3 diameter of 20 μm , from now on called MC. The second is a paraffinic PCM shape-stabilized with carbon
4 nanotubes (CNTs), prepared by adding CNTs to melted paraffin in a weight content of 15 wt%. The
5 paraffin-CNT mixture was then cryogenically grinded under liquid nitrogen and then sieved with a
6 300- μm metallic sieve to obtain a micrometric powder that can be easily mixed with a polymer matrix,
7 with an average powder size of $53 \pm 30 \mu\text{m}$, from now on called ParCNT.
8
9

10
11 PA12 was melt compounded with either MC or ParCNT in different weight percentages (15-60 wt%),
12 and the blends were hot-pressed to produce thin films for the subsequent fabrication of the laminates
13 via film stacking. Five laminates were prepared: the neat PA-GF laminate without PCM, two laminates
14 in which the matrix contained 30 wt% and 60 wt% of MC (PA-MC30-GF and PA-MC60-GF), and two
15 laminates containing the same initial fractions of ParCNT (PA-ParCNT30-GF and PA-ParCNT60-GF).
16
17

18
19 One of the most important parameters during the production process of such laminates is the
20 viscosity of the matrix, which should be low enough to allow a complete fiber wetting. The viscosity of
21 the PA/PCM blends increases with the PCM content, as shown by a sensible decrease in the melt flow
22 index (MFI) (Figure 7). For the samples with microcapsules, the MFI decreases with an increase in the
23 MC content and reaches a minimum of 5.2 g/10 min, but a more dramatic decrease is observed for the
24 samples with ParCNT. For the highest concentrations, the measurements could be performed only with
25 a mass of 5 or 10 kg, and the resulting MFI values were very low (0.7 g/10 min). This is probably due to
26 the increasing content of CNTs, which are well known to heavily increase the viscosity of molten
27 polymers [152]. This implies that, although both PCMs types decrease the fluidity of the PA, the effect
28 of the MC is less intense than that of the ParCNT, and that it is unlikely to obtain a defect-free composite
29 at elevated ParCNT contents.
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

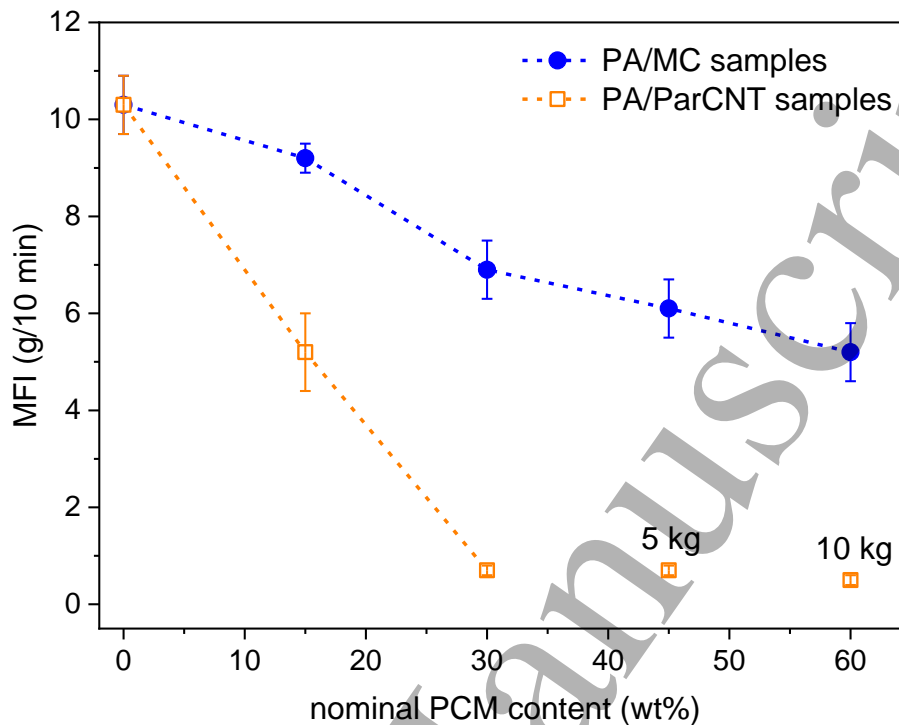


Figure 7. Melt flow index (MFI) of the PA/PCM blends as a function of the nominal PCM content (at 230 °C and 2.16 kg; single tests at 5 kg and 10 kg are also indicated) (adapted from [146]).

This is evident from the optical microscope micrographs (Figure 8) and the data of volume composition of the prepared laminates (Table 3). The MC-containing laminates are of good quality, as they contain few matrix-rich zones and the fibers are properly wetted, but the interlaminar region is thicker than that of the neat PA-GF laminate (not shown), due to the concentration of the MC phase in this region rather than among the fibers of the same yarn. The concentration of the PCM in the interlaminar region is observable also on the ParCNT-containing laminates, but for these laminates the quality appears worse; especially in the laminate PA-ParCNT60-GF, the fibers are not properly wetted, and the fabric weaving seems distorted. The worse quality of this laminate is observable also from the lower fiber volume fraction and the considerably higher porosity (Table 3), while all the other laminates show approx. the same fiber content (50-55 vol%) and void volume fraction (≈ 2 vol%).

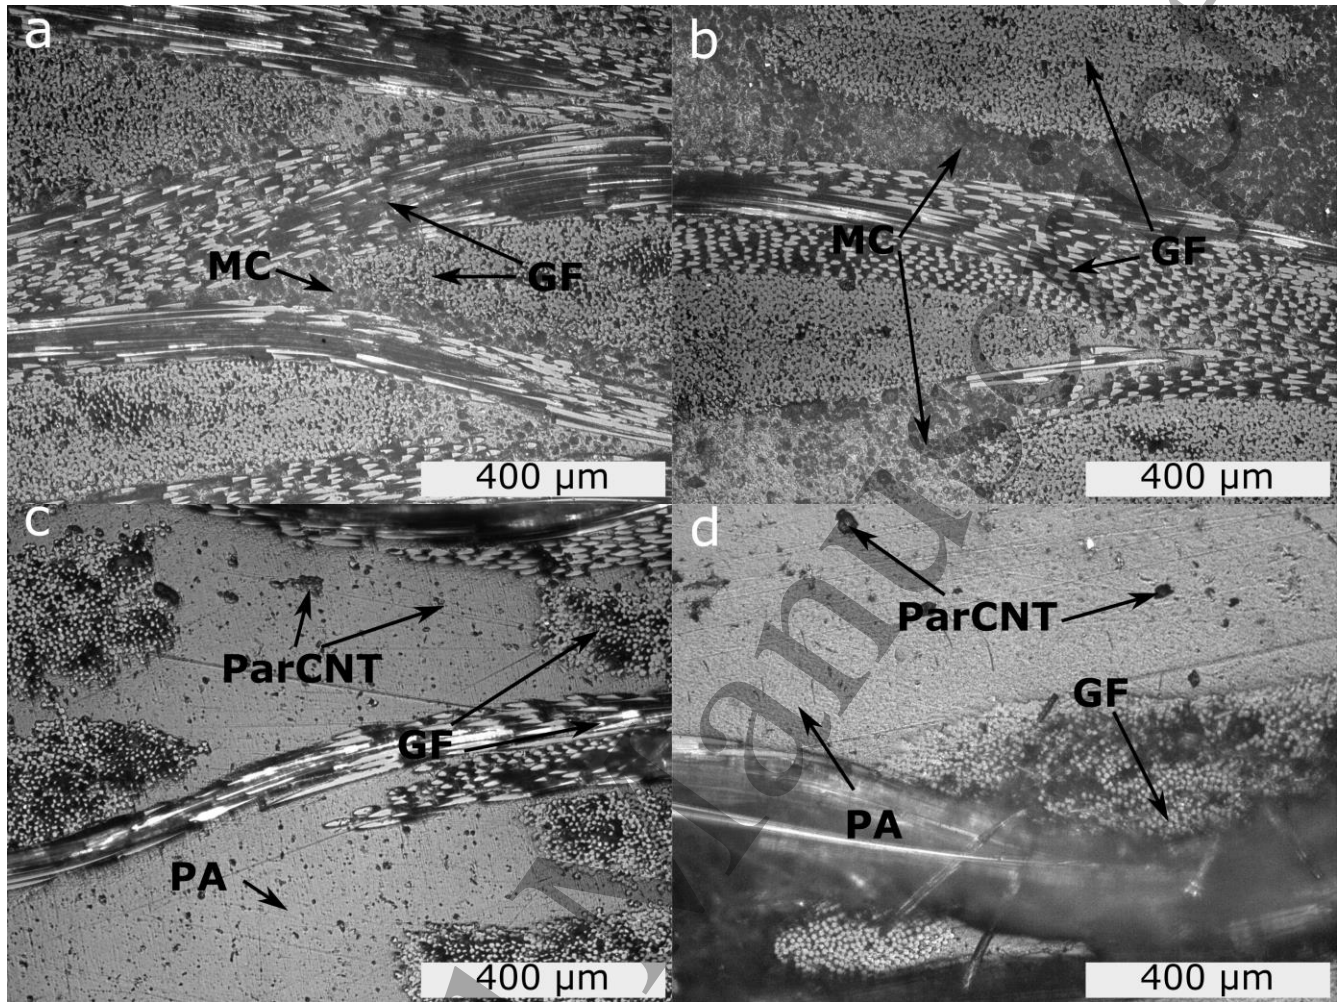


Figure 8. Optical microscope micrographs of the polished cross sections of the PA/PCM/GF laminates. (a) PA-MC30-GF; (b) PA-MC60-GF; (c) PA-ParCNT30-GF; (d) PA-ParCNT60-GF.

The most important test to assess the TES capability is differential scanning calorimetry (DSC), which allows the measurement of the total heat exchanged during the phase change of the PCM and the temperature interval in which it occurs. The DSC thermograms of the first heating scan, reported in Figure 9, show two endothermic peaks, the first at approx. 40 °C, related to the melting of the PCM, and the second at approx. 180 °C associated to the melting of the PA phase. The melting and crystallization enthalpy of the PCMs in the prepared composites are evaluated by calculating the area of the endothermal and exothermal peak, respectively. In order to evaluate the TES efficacy of composites, the results could be compared to those of the two neat investigated PCMs (MC and ParCNT), which show a transition enthalpy of approx. 200 J/g either in heating or in cooling. As reported in Table 3, the phase change enthalpy of the laminates is remarkably lower than expected by considering their nominal PCM mass fraction. This is evident from the values of relative melting and crystallization enthalpy (ΔH_m^{rel} , ΔH_c^{rel}), calculated through Equation (4a) and (4b) as

$$\Delta H_m^{rel} = \frac{\Delta H_m}{\omega_{PCM} \cdot \Delta H_m^{neat}} \quad (4a)$$

$$\Delta H_c^{rel} = \frac{\Delta H_c}{\omega_{PCM} \cdot \Delta H_c^{neat}} \quad (4b)$$

where ΔH_m and ΔH_c are the melting and crystallization enthalpy values of the PCM measured on the polymer/PCM mixtures and on the reinforced composites, ω_{PCM} is the nominal weight fraction of PCM in the sample and ΔH_m^{neat} and ΔH_c^{neat} are the melting and crystallization enthalpy values of the neat PCM. A relative phase change enthalpy close to 100 % suggests that the PCM content still present in the composite after processing is close to the nominal (initial) fraction, and that the PCM preserves its capability of melting and crystallizing also when embedded in a composite. Conversely, a low relative phase change enthalpy indicates that the PCM degrades or leaks out of the composite during processing, due to high temperatures and pressures applied or to a poor shape-stabilization. Both these phenomena occur in these composites, for which the processing conditions applied during melt compounding and hot-pressing cause a partial degradation of the PCMs. The composites with ParCNT present a much greater decrease in ΔH_m^{rel} , which does not even show a trend with the ParCNT content. This suggests that the degradation of ParCNT during the process is greater than that of MC, which support the observation that a microencapsulated PCM can be more easily incorporated in a glass fiber/PA12 laminate than a shape-stabilized one, due to the generally higher thermal stability.

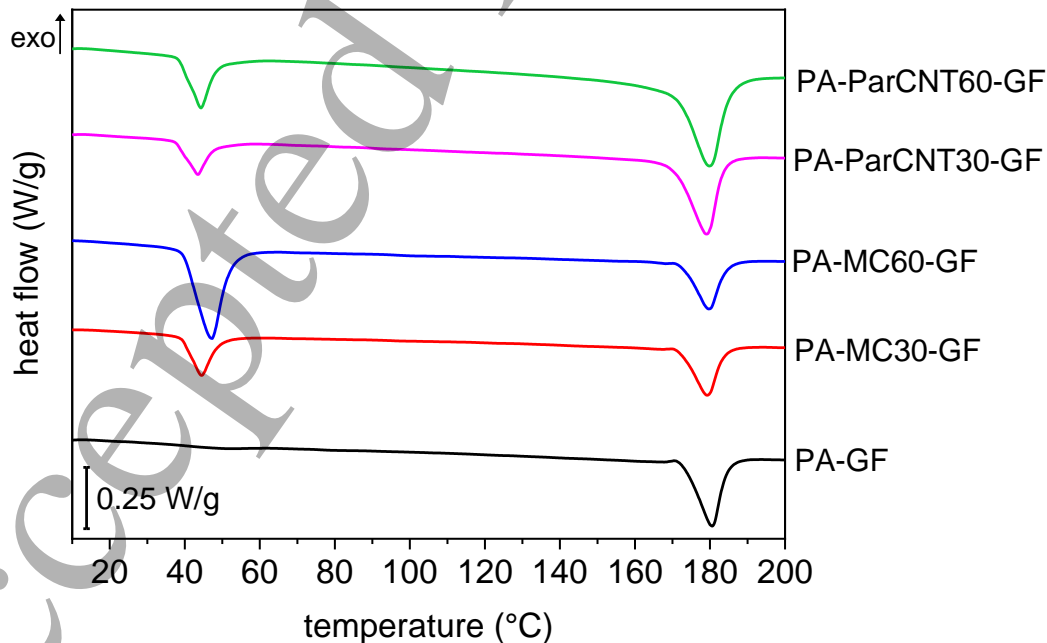


Figure 9. DSC thermograms (first heating scan) of the laminates PA/PCM/GF (10 °C/min; N₂) (data from [146]).

Table 3. Volume compositions of the PA/PCM/GF laminates and results of the DSC tests (data from [146]).

Sample	ϑ_f (vol%)	ϑ_m (vol%)	ϑ_v (vol%)	T_m (°C)	ΔH_m (J/g)	ΔH_m^{rel} (%)	T_c (°C)	ΔH_c (J/g)
MC	-	-	-	43.5	200.1	100	30.0	200.0
ParCNT	-	-	-	42.6	205.5	100	33.5	206.0
PA-GF	53.4	44.5	2.1	--	--	--	--	--
PA-MC30-GF	55.5	42.2	2.3	43.9	6.5	44.2	25.2	3.1
PA-MC60-GF	53.2	44.3	2.5	46.3	17.1	52.7	23.2	13.8
PA-ParCNT30-GF	50.5	47.7	1.8	43.0	5.3	31.9	39.7	2.0
PA-ParCNT60-GF	32.4	57.8	9.8	43.5	8.4	15.8	31.3	5.6

ϑ_f = volume fraction of fibers; ϑ_m = volume fraction of matrix (PA/PCM system); ϑ_v = volume fraction of voids; T_m = melting temperature of the PCM (°C); ΔH_m = PCM melting enthalpy (J/g); ΔH_m^{rel} = relative PCM melting enthalpy (%); T_c = crystallization temperature of the PCM (°C); ΔH_c = PCM crystallization enthalpy (J/g).

For the mechanical properties, Table 4 shows the values of tensile elastic modulus, strength, and strain at break, as well as the interlaminar shear strength (ILSS). The stress at break decreases upon PCM addition, and this effect is more evident for the laminates with ParCNT, in which also the elastic modulus is lower than that of the neat PA-GF laminate. Conversely, the elastic moduli of the laminates with MC are not significantly different from that of PA-GF, which suggests that the stiffness is mainly determined by the elastic properties of the reinforcement, and the matrix fulfils its load-transfer role properly. Also the strain at break is not negatively affected by the PCM addition. Therefore, it can be concluded that the addition of PCM microcapsules influences the mechanical properties of the host laminate only marginally, while a sensible decrease in the mechanical performance can be appreciated with ParCNT addition. In previous works, the elastic modulus of microcapsules was evaluated as 28 MPa [153, 154], while the modulus, strength and strain at break of ParCNT are approx. 1.5 GPa, 5.5 MPa, and 0.7 % [139].

Table 4. Main results of the mechanical investigation of the PA/PCM/GF laminates (tensile tests and short-beam shear tests) (data from [146]).

Sample	E (GPa)	σ_b (MPa)	ε_b (%)	ILSS (MPa)
PA-GF	13.1 ± 0.3	160 ± 29	2.7 ± 0.3	11.2 ± 1.7
PA-MC30-GF	12.7 ± 0.9	124 ± 18	3.0 ± 0.4	9.8 ± 1.7
PA-MC60-GF	13.3 ± 0.7	114 ± 10	3.0 ± 0.7	9.4 ± 2.1
PA-ParCNT30-GF	9.9 ± 0.4	92 ± 9	3.5 ± 0.1	6.7 ± 0.3
PA-ParCNT60-GF	6.5 ± 0.1	56 ± 15	3.5 ± 1.1	5.5 ± 1.8

1
2
3 E = elastic modulus (GPa); σ_b = stress at break, corresponding also to the maximum stress σ_{MAX} (MPa); ϵ_b = strain at break,
4 corresponding also to the strain at the maximum stress ϵ_{MAX} (%); ILSS = interlaminar shear strength.

5
6 A similar observation can be made for the interlaminar shear strength. The laminates with MC do
7 not perform significantly differently from the laminate without PCM, while the ILSS of the of the laminates
8 with ParCNT sharply decreases with an increase in the PCM content. This can be attributed to the
9 noticeable porosity and the lower mechanical properties of the matrices with ParCNT. In conclusion, the
10 microencapsulated PCM is more suitable to produce laminates in combination with PA and GF, since it
11 exercises a lower influence on the matrix viscosity, has a greater thermal stability, and impacts the
12 mechanical properties of the laminates marginally. However, due to the processing-related PCM
13 degradation, the losses in TES capability are massive.

14
15 Two strategies can be adopted to try to produce thermoplastic composites while limiting the PCM
16 degradation, which are presented in Par. 4.2 and Par. 4.3, respectively. The first strategy consists in
17 employing discontinuous fibers instead of a continuous fiber fabric. In this way, the composites can be
18 produced by melt compounding followed by a single hot-pressing step, which allows avoiding one
19 processing step necessary for the production of GF laminates. The second strategy involves a reactive
20 thermoplastic resin, which is provided as a low viscosity precursor and can be processed at room
21 temperature similarly to a thermosetting resin, thereby drastically reducing the risk of thermo-mechanical
22 degradation. As this second strategy nowadays is not implementable with traditional thermoplastics, an
23 additional approach can be considered that involves the production of commingled yarns containing
24 PCM-enhanced thermoplastic filaments and continuous reinforcing fibers. This strategy not only allows
25 the production of a component made of traditional thermoplastic laminate in fewer processing steps, but
26 it also shifts the multifunctionality from the composite level to the yarn level. This approach was
27 investigated by our group through the production of polypropylene filaments containing paraffin
28 microcapsules [155].

29 30 31 32 33 34 35 36 37 38 39 40 41 42 **4.2. Case study 2: PCM microcapsules in semi-structural carbon/polyamide composites**

43
44 The present case study deals with the preparation of discontinuous-fiber composites having the
45 same PA12 matrix and the same microencapsulated PCM described in Par. 4.1, but reinforced with
46 discontinuous carbon fibers of two different lengths, i.e. 6 mm and 100 μ m and denoted as carbon fibers
47 “long” (CFL) and carbon fibers “short” (CFS), respectively. PA was mixed with MC and either CFL or
48 CFS in different weight concentrations, and the composites were prepared by melt compounding and
49 hot-pressing. The samples are denoted as PA-MCx-CFLy or PA-MCx-CFSy, where x is the nominal MC
50 weight fraction with respect to the total PA-MC mass and y is the weight fraction of either CLF or CFS
51 with respect to the total mass of the composite.

Figure 10 shows the scanning electron microscopy (SEM) micrographs of the cryofracture surface of some selected compositions. The processing parameters successfully produce a homogeneous distribution of both the carbon fibers and the microcapsules in the matrix. The core-shell structure of this PCM is clearly observable especially in that acquired at higher magnification (Figure 10b). The microcapsule indicated with a dashed blue arrow shows both the thin polymer shell and the paraffinic core. The irregular morphology and the voids of the core indicate a certain aptitude of the capsules to accommodate the volume variation during the phase change and avoid the shell rupture [57]. In other cases (solid red arrow), the shell is still partly observable, but the core has been almost completely removed. The adhesion between the shell and the PA matrix is fairly good, even though some debonding is observable. The same considerations can be made for the samples containing both capsules and fibers, as appreciable from the micrograph of the sample PA-MC50-CFL20 (Figure 10c-d). However, the fracture surface of this sample looks irregular, which may indicate the presence of voids and defects within the composite. This could stem from the considerably high amount of fillers (MC and CFL) and the high viscosity during compounding, which could have prevented a proper molding of the composite during the hot-pressing step.

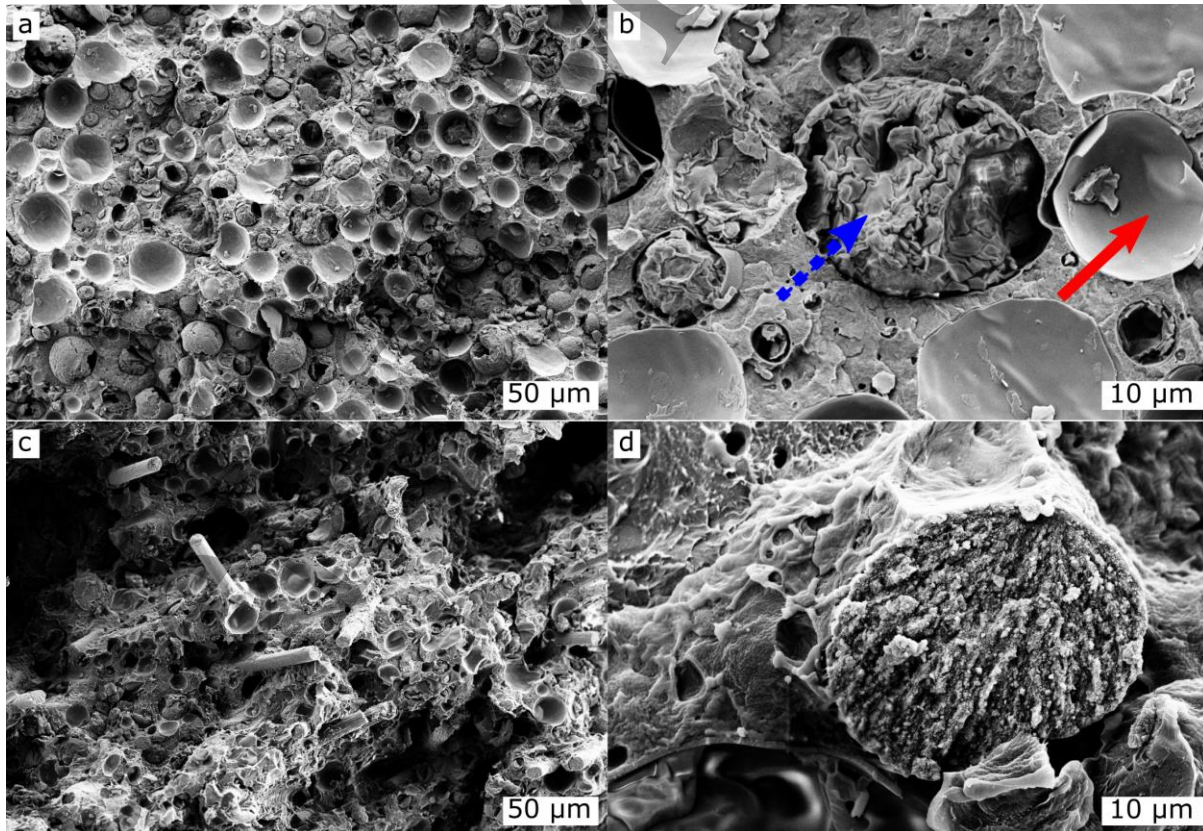


Figure 10. SEM micrographs of the cryofracture surface of some selected compositions: (a,b) PA-MC50; (c,d) PA-MC50-CFL20.

1
2
3 The results of the DSC analysis are shown in Figure 11, which reports representative thermograms
4 of the first heating scan and the cooling scan for some selected compositions, i.e. the samples PA-MCx-
5 CFS20. The main results of the DSC analysis of all the samples are summarized in Table 5. As found
6 for the PA-based samples described in Par. 4.1, the melting and crystallization peaks of MC are found
7 at approx. 43 °C on heating and 30 °C on cooling, respectively, while the signals at higher temperature
8 are related to the phase transition of PA. The melting/crystallization temperatures of the PCM (T_m , T_c),
9 regarded also in this case as the peak temperatures of the endo/exothermic signals, do not vary
10 significantly with the carbon fiber content, and the phase change enthalpy (ΔH_m , ΔH_c) increases with
11 the weight fraction of MC. The value of ΔH_m^{rel} , calculated through Equation (4a), is generally below
12 100 %, and it decreases as the MC content increases. However, these values are mostly higher than
13 those calculated for the samples presented in Par. 4.1, which highlights that applying milder processing
14 conditions and avoiding one hot-pressing step is helpful to preserve shell integrity and minimize PCM
15 degradation.

16
17 Nevertheless, some degradation and leakage are still present, as indicated by values of ΔH_m^{rel} lower
18 than 100 %. The decrease in ΔH_m^{rel} is more evident with at higher MC and carbon fiber fraction. This is
19 linked to the higher melt viscosity and the consequently higher shear stresses to which the capsules are
20 subjected during compounding, which damages the thin capsule shell and causes the leakage and
21 degradation of the paraffinic core. Additionally, ΔH_m^{rel} is lower for samples containing CFL compared to
22 those with CFS, which can be related to the higher viscosity and higher shear stresses obtained while
23 compounding mixtures containing CFL.

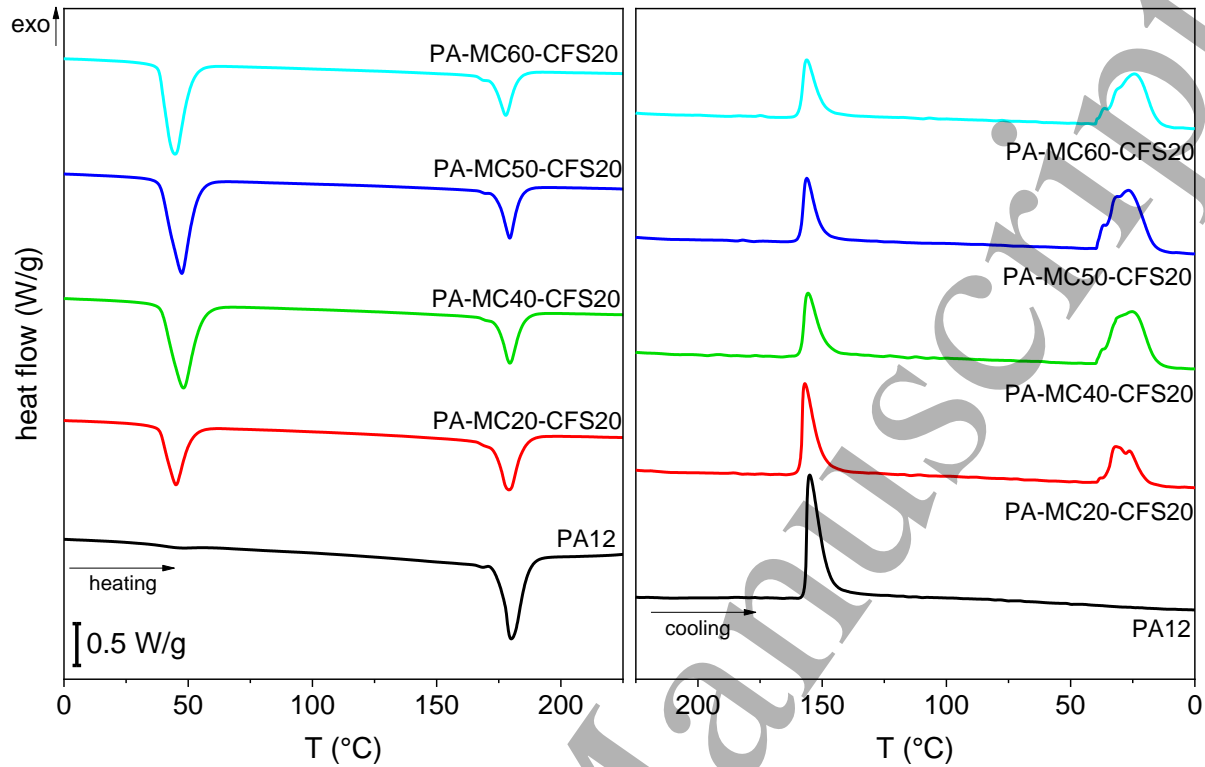


Figure 11. DSC thermograms (heating scan and cooling scan) of the samples PA-MC_x-CFS20 (10 °C/min; N₂ flow = 100 ml/min) (data from [148]).

Table 5. Results of the DSC tests on the samples PA-MC_x-CFL and PA-MC_x-CFS (data from [148]).

Sample	T_m (°C)	ΔH_m (J/g)	ΔH_m^{rel} (%)	T_c (°C)	ΔH_c (J/g)
MC	44.1	220.1	100	30.2	208.2
PA-MC20	46.2	44.5	101.1	26.7	38.1
PA-MC40	47.3	91.8	104.3	26.4	84.1
PA-MC50	49.9	100.8	91.6	25.3	93.8
PA-MC60	47.8	116.6	88.3	24.1	108.9
PA-MC20-CFL20	45.5	33.0	93.8	31.5	27.9
PA-MC40-CFL20	45.8	28.9	41.1	31.4	23.8
PA-MC50-CFL20	46.6	46.9	53.3	26.1	40.9
PA-MC60-CFL20	45.8	44.5	42.1	30.2	37.6
PA-MC20-CFS20	45	33.3	94.6	31.7	28.8
PA-MC40-CFS20	48.1	58.8	83.5	25.2	54.3
PA-MC50-CFS20	47.5	60.4	61.0	26.6	57.7
PA-MC60-CFS20	44.8	54.6	51.7	24.5	51.4

T_m = melting temperature of the PCM (°C); ΔH_m = PCM melting enthalpy (J/g); ΔH_m^{rel} = relative PCM melting enthalpy (%); T_c = crystallization temperature of the PCM (°C); ΔH_c = PCM crystallization enthalpy (J/g).

1
2
3 This agrees with the results of the dynamic rheological tests, performed with a parallel plate
4 rotational rheometer (Figure 12). The viscosity increases upon filler addition, but the MC increase the
5 viscosity significantly only at very high concentrations. On the other hand, the samples containing both
6 MC and carbon fibers show more clearly phenomena such as the viscosity increase, the yield stress
7 rise at low shear rates and the anticipation of the shear thinning region. Moreover, the viscosity is higher
8 for the samples containing CFL than for those containing the same amount of CFS. This suggests that
9 the CFL produce a higher viscosity rise also in the melt compounding process, thereby intensifying the
10 shear stress, microcapsule damage and paraffin degradation. This is in good agreement with DSC
11 results, which highlight a higher PCM experimental weight fraction and enthalpy in the samples
12 containing CFS. However, the difference in the measured viscosity seems too small to justify such
13 discrepancies in the DSC results. It should be considered, though, that the samples analyzed by
14 dynamic shear rheometry have been subjected to melt compounding and hot pressing, which can
15 significantly shorten the fiber length. As fibers with a higher aspect ratio are generally more influent on
16 the polymer melt viscosity, it is reasonable to hypothesize that the shear stresses in the melt
17 compounder are higher at the beginning of the compounding stage, which causes an even more
18 extensive MC damage.

19
20 The greater PCM degradation in CFL-containing composites can be also appreciated from
21 thermogravimetric analysis (TGA). As observable from Figure 13, the addition of carbon fibers delays
22 the beginning of thermal degradation of the neat PA, whilst the addition of MC shifts the thermograms
23 to lower temperatures. The mass loss associated to MC degradation, between 200 °C and 400 °C, is
24 less than expected by considering the nominal MC weight fraction. This is in good agreement with the
25 DSC results, where the phase change enthalpy is less than expected due to some leakage and
26 degradation of PCM. This effect is more evident for the CFL-containing samples than for the samples
27 reinforced with CFS, which agrees with the results of the rheological tests and confirms that the greater
28 increase in viscosity induced by CFL is responsible for the greater capsule breakage and paraffin
29 degradation.



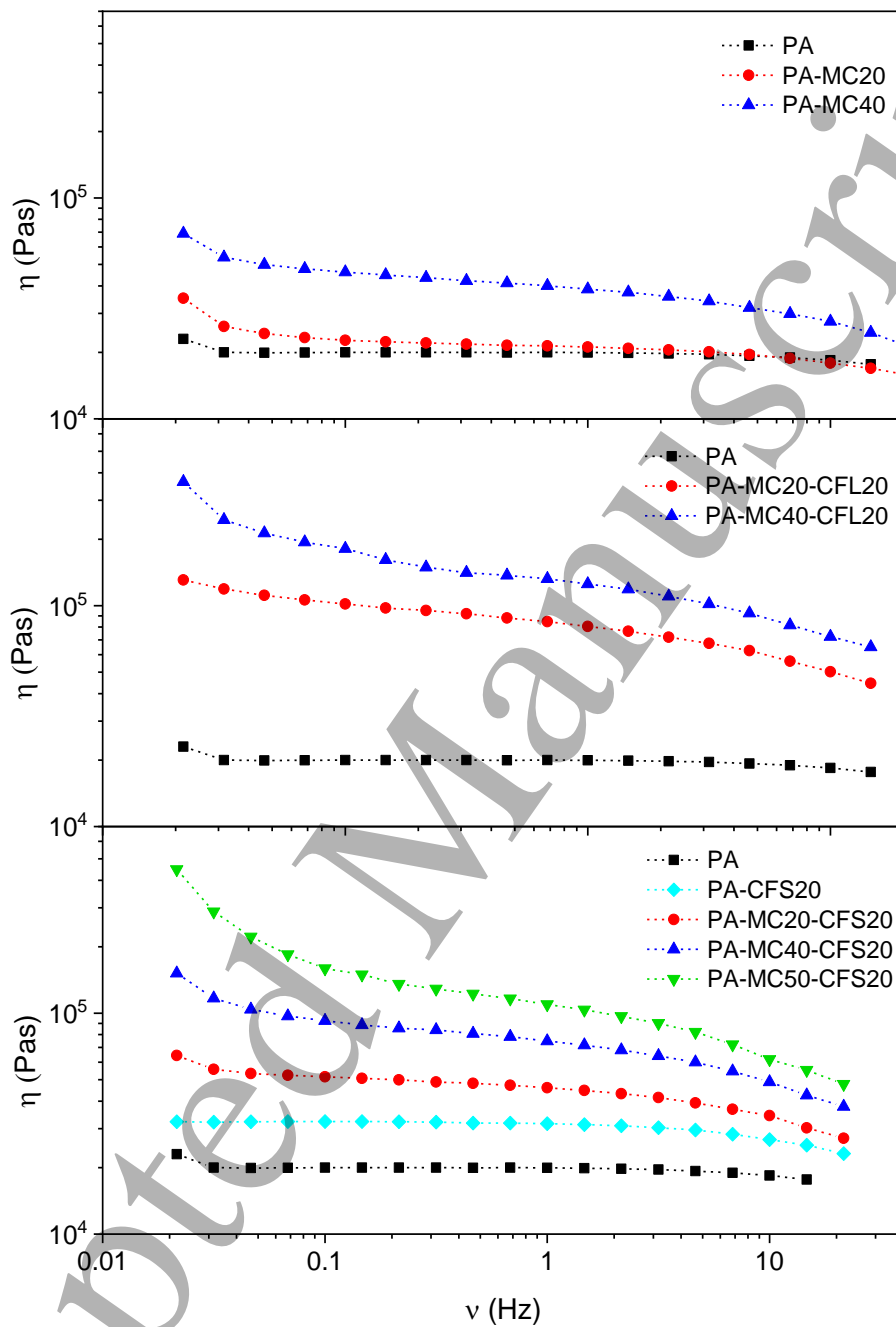


Figure 12. Results of the dynamic rheological test. Values of viscosity as a function of the applied frequency for some representative compositions (parallel plate; gap 1.5 mm; diameter 8 mm; 190 °C; N₂) (adapted from [148]).

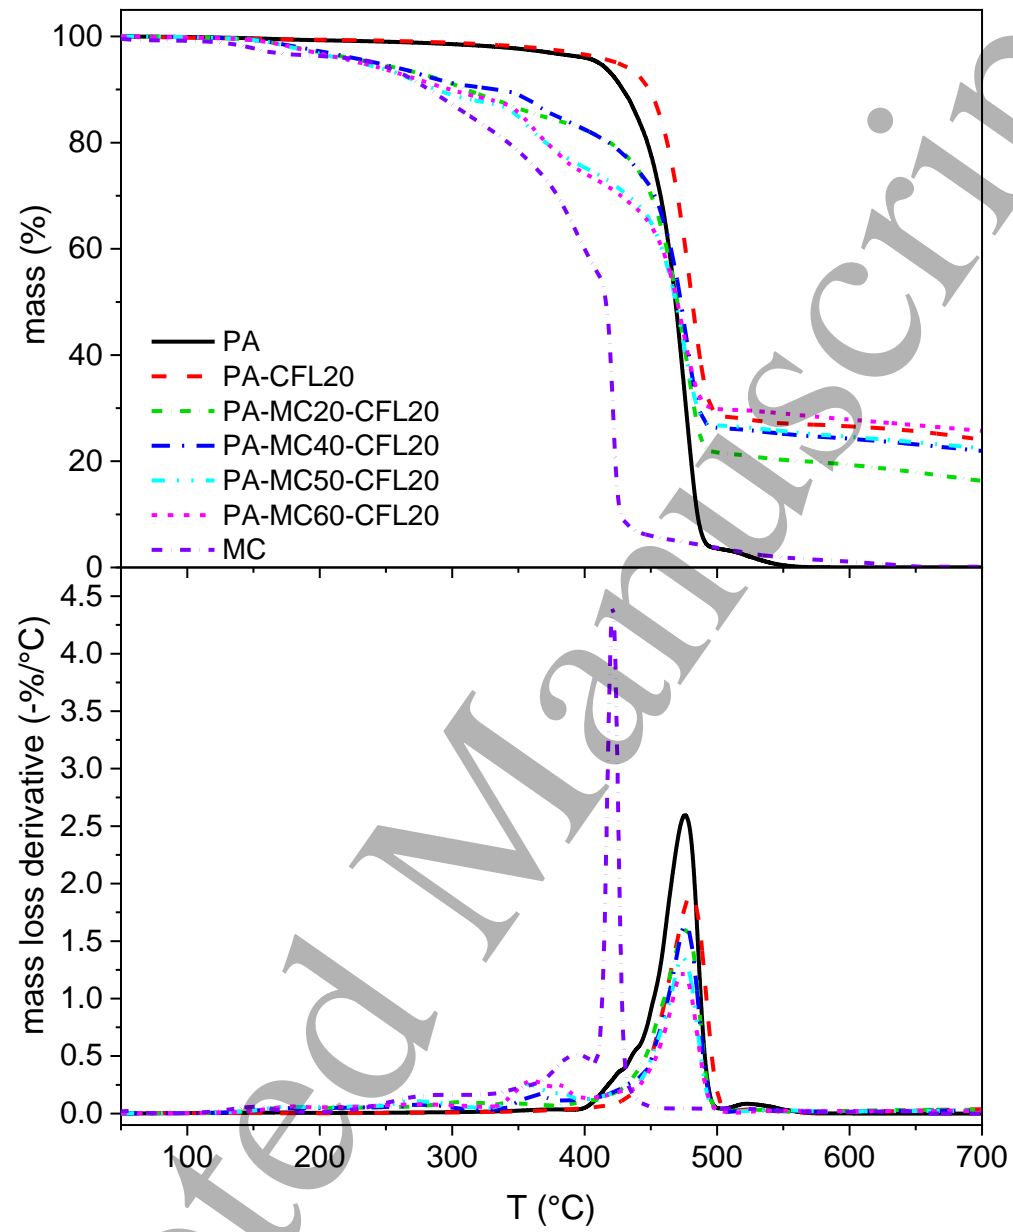

(a)

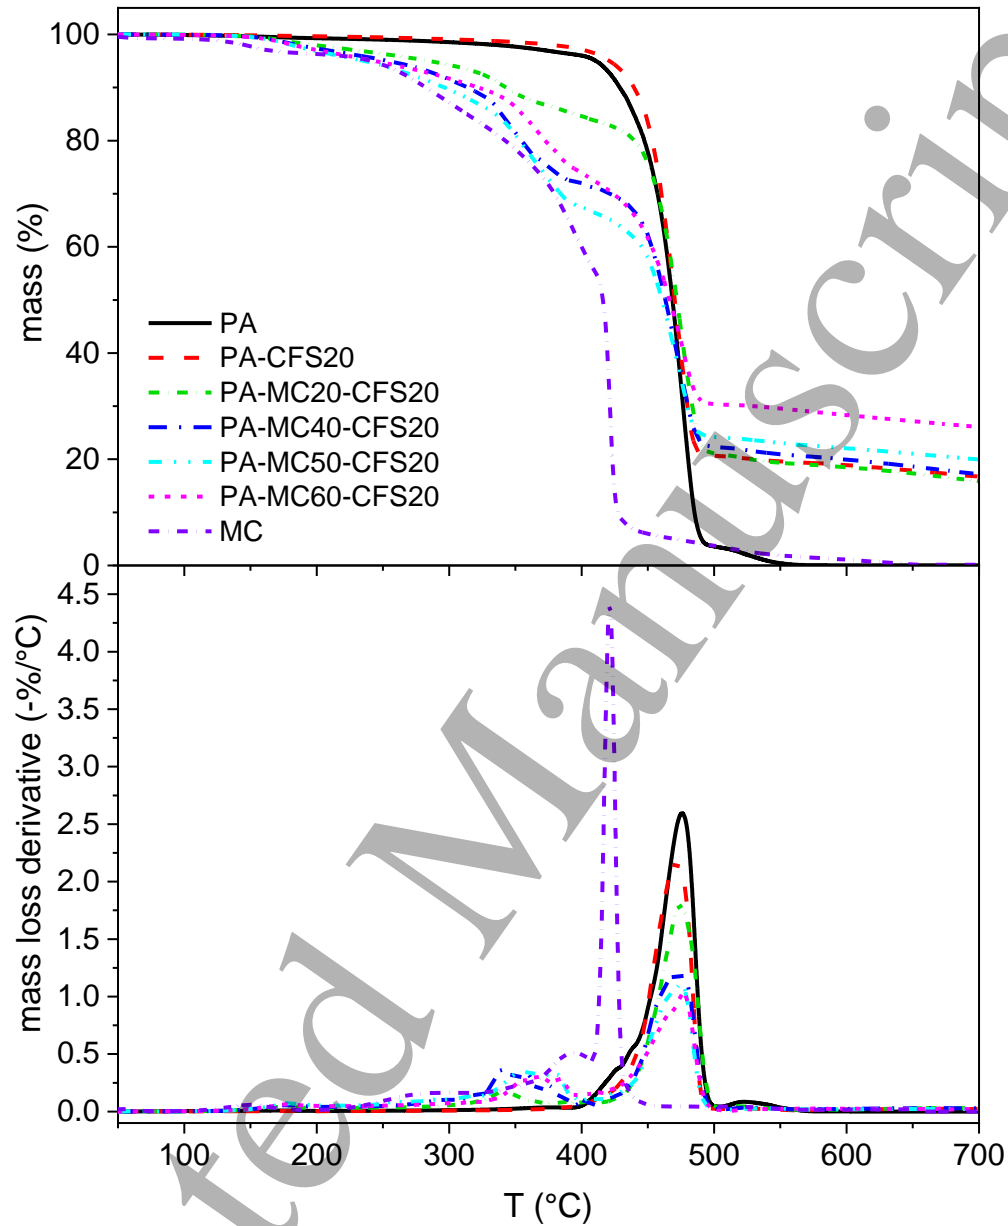

(b)

Figure 13. TGA thermograms of the samples (a) PA-MC x -CFL20; (b) PA-MC x -CFS20 (10 $^{\circ}\text{C}/\text{min}$; N_2 flow = 15 ml/min) (adapted from [148]).

Another interesting parameter of composites containing a PCM is thermal conductivity. A greater thermal conductivity helps homogenizing the temperature of the whole composite mass during heating or cooling, thereby improving the heat exchange efficiency. Figure 14 shows the values of thermal conductivity of some selected compositions determined through laser flash analysis (LFA). As expected,

the introduction of carbon fibers increases the thermal conductivity. For the samples containing carbon fibers and MC, the thermal conductivity shows a maximum at 40 °C, while approaching the melting temperature of the PCM. This phenomenon, observed elsewhere in the literature [72], is more evident for the samples containing CFS; this suggests that the effective PCM content is higher for these samples compared to the CFL-reinforced ones, which is consistent with the DSC and TGA results.

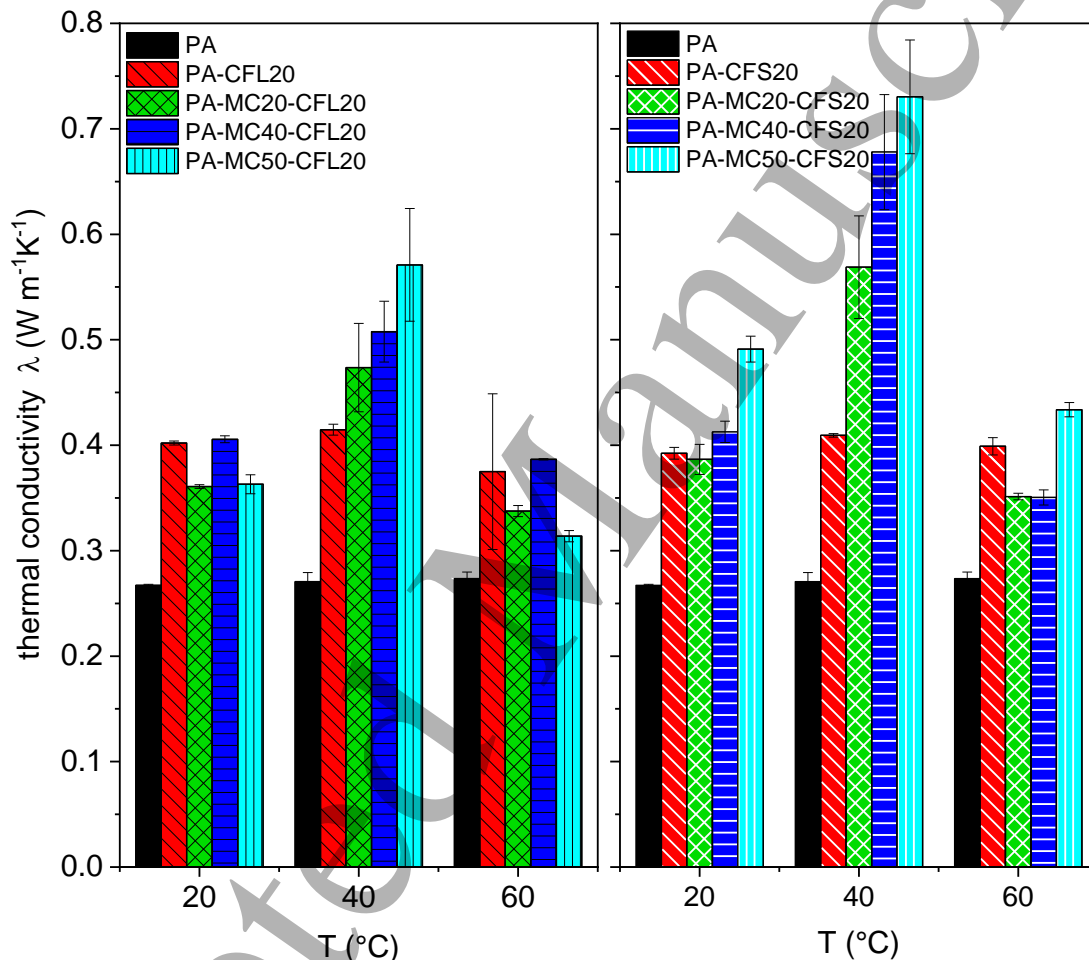


Figure 14. Results of the LFA test on the samples PA, PA-CFL20, PA-MC_x-CFL20 and PA-MC_x-CFS20. Thermal conductivity as a function of temperature (data from [148]).

Finally, Figure 15 shows the effect of CFS, CFL and MC on the tensile elastic modulus and strength of the prepared composites. The introduction of MC decreases the elastic modulus, while the addition of the carbon fibers increases it. This effect is more evident for CFL than for CFS, because the greater load transfer length determines a higher stiffening and reinforcing capability, as thoroughly reported in the literature [156, 157]. Similar considerations can be made for σ_{MAX} , which decreases with an increase in the MC content and increase with the carbon fiber concentration.

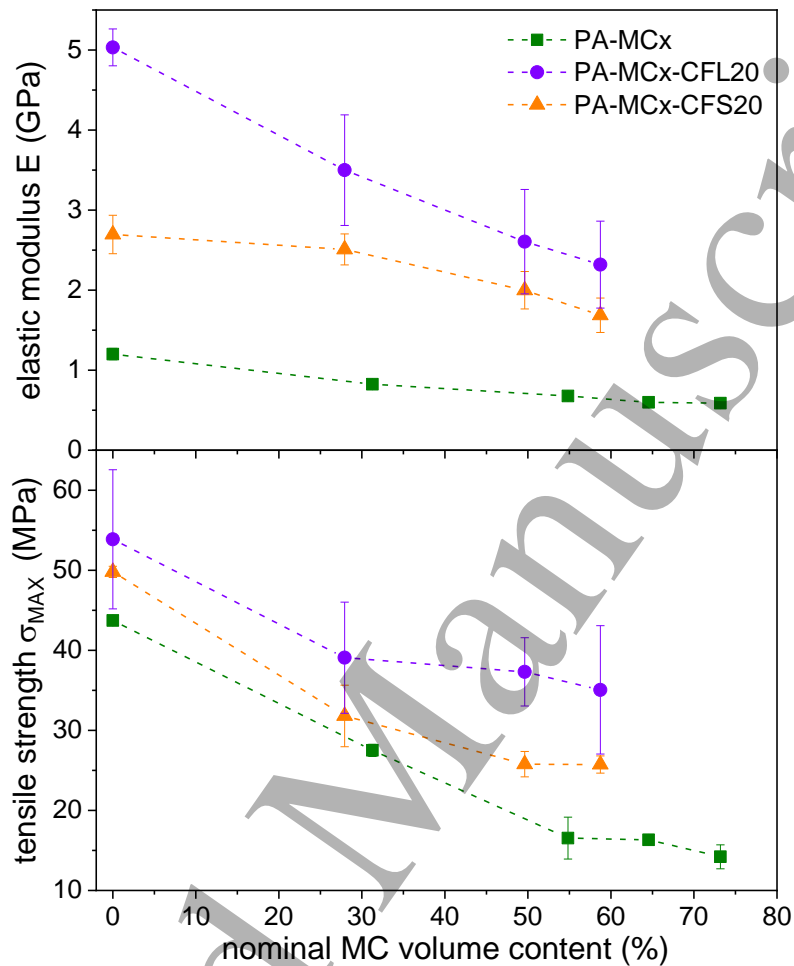


Figure 15. Results of the tensile tests. Elastic modulus and maximum stress as a function of the nominal (initial) MC volume fraction for the composites with a carbon fiber content of 0 wt% and 20 wt% (data from [148]).

In conclusion, the processing conditions applied for the production of these discontinuous-fiber composites were milder than those employed to produce the continuous-fiber laminates described in Par. 4.1, which reduces the degradation of the PCM and results in a higher final relative phase change enthalpy. However, also for these composites the paraffin degradation is not negligible and is more evident for samples reinforced with longer fibers, which cause a higher increase in viscosity. For the mechanical properties, also in this case quasi-static tensile tests highlight a decrease in elastic modulus and maximum stress upon PCM addition, while carbon fibers positively contribute to increase the elastic modulus.

4.3. Case study 3: reactive thermoplastic resin as a matrix for multifunctional carbon-fiber laminates

This case study presents a different approach to produce thermoplastic laminates containing a PCM. This approach aims at preserving the integrity of paraffin microcapsules by avoiding the high-temperature processing of highly viscous molten polymer [158, 159]. It is made possible by adopting the newly developed thermoplastic resin Elium® (Arkema, Lacq, France), provided as low-viscosity liquid and processable as a thermosetting resin.

This technique is nowadays applicable only to some selected polymer formulations and not to the majority of the most common thermoplastic polymer matrices. Nevertheless, it is a powerful and effective method that is worth investigating to produce post-thermoformable PCM-enhanced composites containing continuous reinforcing fibers.

These composites were prepared at room temperature, by mixing the reactive resin precursor (EL) with the paraffin microcapsules (MC) presented in Par. 4.1 and 4.2 in different weight fractions (0 wt%, 20 wt%, 30 wt% and 40 wt%), and by using the mixtures as matrices to prepare laminates through hand-layup and vacuum bagging techniques. The prepared laminates were labeled EL-CF, EL-MC20-CF, EL-MC30-CF and EL-MC40-CF, according to the nominal MC weight fraction in the matrix. The OM micrographs of the polished cross sections of the laminates are presented in Figure 16. As for the laminates presented in Par. 4.1, the MC phase is preferentially located in the interlaminar region, due to the different dimensions of carbon fibers (average diameter 7 μm) and microcapsules (average diameter 20 μm). Moreover, the MC concentration in the interlaminar region does not increase considerably with the MC content, but what is evidently seen increasing is the thickness of the interlaminar region, and thus that of the whole laminate. This indicates that the increase in MC content causes a rise in viscosity of the EL/MC mixtures, which flow out of the CF fabric slower and with more difficulty, thereby causing a final higher matrix weight (and volume) fraction. Therefore, the fiber volume fraction (ϑ_f) decrease with increasing initial MC content. This is appreciable from quantitative data of fiber volume fraction (Table 6), calculated with TGA, DSC, and density results (the details of the calculations are reported in [158]). Conversely, the volume fraction of voids (ϑ_v) generally increases with the MC content.

The decrease in ϑ_f is the main reason for the decrease in mechanical performance, as observable from the data of flexural modulus, stress and strain at break reported in Figure 17. The elastic modulus decreases with an increase in the MC content, but this is partially due to the decreasing fiber volume fraction. The flexural strength follows the same trend, and this is probably due to the presence of additional failure mechanisms such as delamination and failure in the zone subjected to compression, as appreciable from a comparison between the load-displacement curves (reported in [158]). While the

neat EL-CF laminate is subjected to a sudden failure after the maximum load, the laminates containing MC are subjected to a progressive failure and present a drop-plateau sequence after the maximum load. The damage was observed starting either in the mid-upper zone, subjected to compression, or in the interlaminar zone. This failure mode, commonly reported for woven fabric composites [160], is typical of materials with a tensile in-plane strength considerably higher than the interlaminar shear strength, which is likely the case for these laminates.

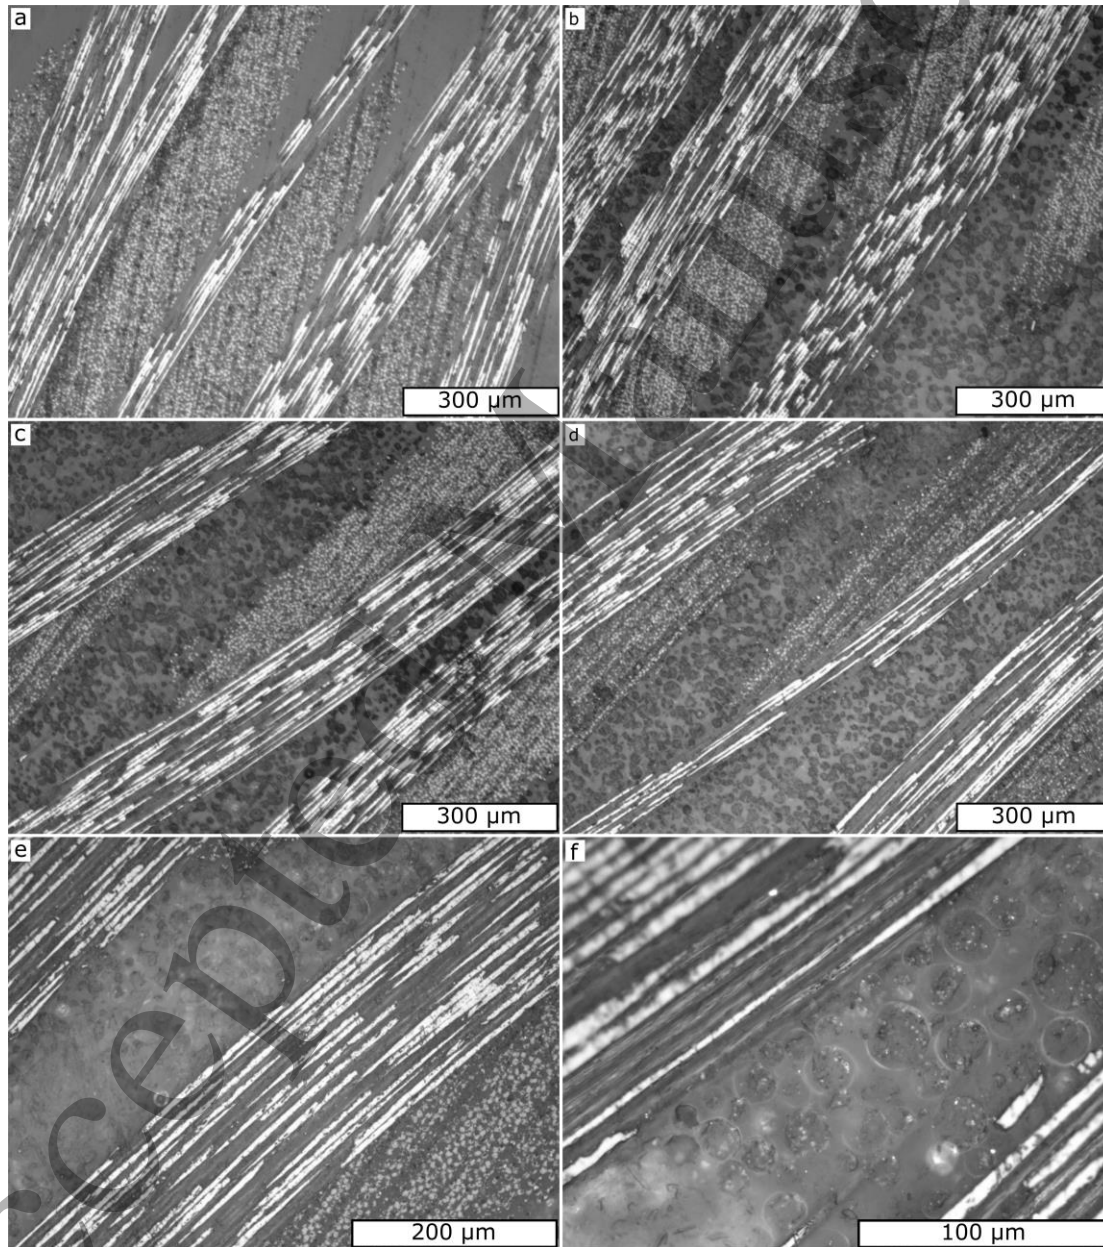


Figure 16. Optical microscope micrographs of the polished cross section of the laminates (a) EL-CF; (b) EL-MC20-CF; (c) EL-MC30-CF; (d) EL-MC40-CF; (e) and (f) EL-MC30-CF, higher magnification.

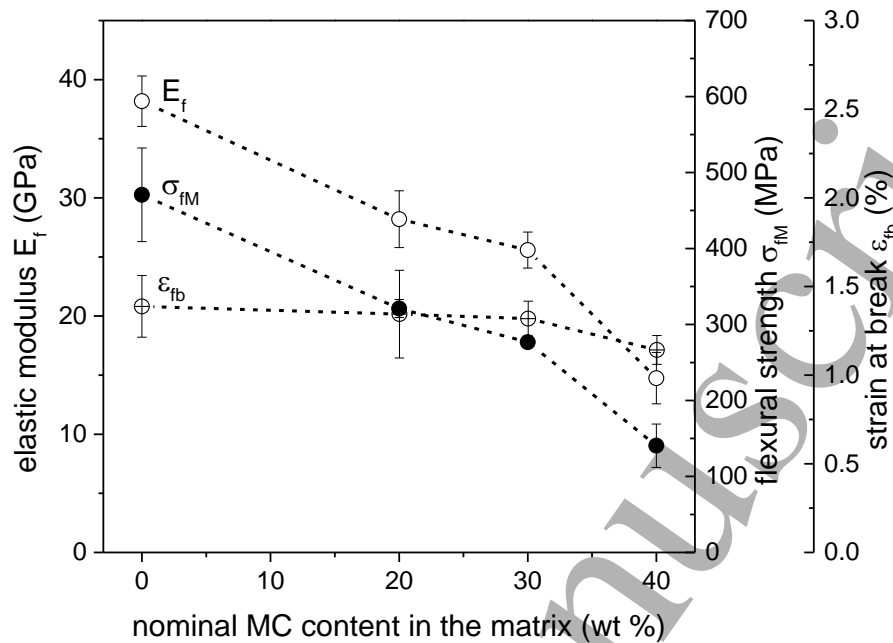


Figure 17. Results of the three-point bending tests on the samples EL-MCx-CF as a function of the nominal MC content in the matrix (data from [158]).

Conversely, the thermal and TES properties strongly increase with the MC content. The DSC thermograms (Figure 18) show the PCM melting peak in the heating scan at approx. 45 °C and crystallization peak in the cooling scan at approx. 30 °C, as observed for the previously reported Case Studies. The position of these peaks is not remarkably affected by the MC content, and the same is true for the glass transition temperature of the EL matrix, located at approx. 100 °C. On the other hand, the phase change enthalpy increases with the MC amount, as observable from the intensity increase of the melting and crystallization peaks. The developed enthalpy reaches 66.8 J/g for the sample EL-MC40-CF, which is remarkably higher than that measured on other thermoplastic composites with the same initial MC fraction. This indicates that the processing conditions of this reactive thermoplastic resin are suitable to avoid damage to the microcapsules and retain the heat storage ability of the paraffinic core, unlike the traditional thermoplastic matrices presented so far.

This is at the basis of the improved thermal management performance evidenced through a test with a thermal camera. This test was performed by heating the laminates in an oven at 70 °C and letting them cool to room temperature while measuring their surface temperature with an infrared thermal camera. Figure 19 reports the values of temperature as a function of time during the cooling stage. In the MC-enhanced laminates, the temperature trend shows plateau-like regions caused by the latent heat released during PCM crystallization, which increases the time to reach room temperature considerably.

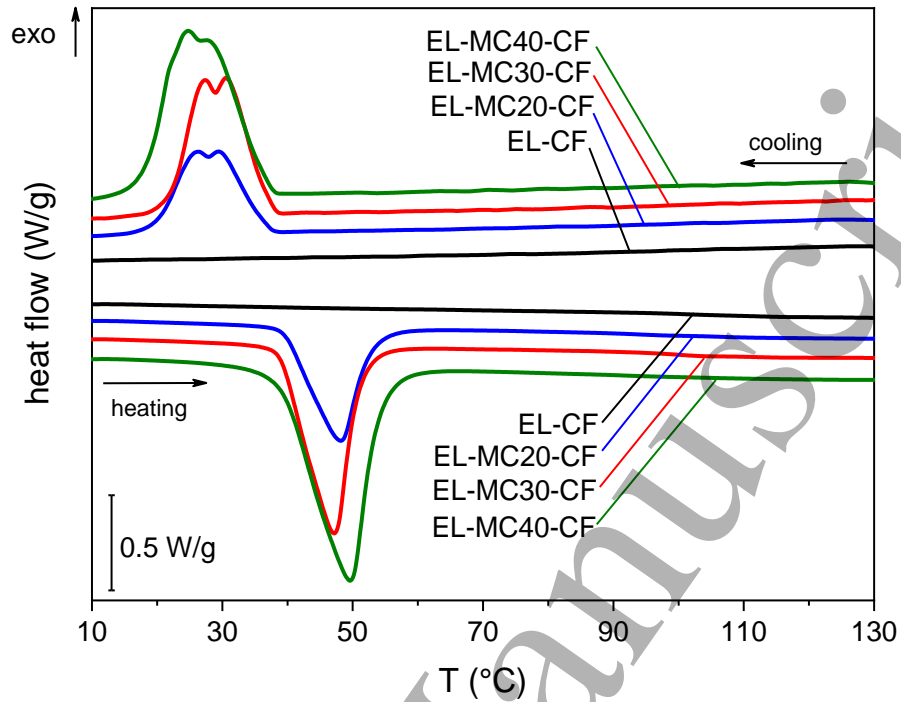


Figure 18. DSC thermograms of the samples EL-MC x -CF (10 °C/min; N₂ flow = 100 ml/min) (data from [158]).

Table 6. Results of the DSC tests and volume composition of the samples EL-MC x -CF (data from [158]).

Sample	ϑ_v (vol%)	ϑ_f (vol%)	ϑ_{MC} (vol%)	T_g (°C)	T_m (°C)	ΔH_m (J/g)	T_c (°C)	ΔH_c (J/g)	ω_{MC} (wt%)
MC	-	-	1	-	45.0	208.2	29.8	208.2	100
EL	1.6 ± 2.1	56.7 ± 1.6	0	101.0	-	-	-	-	-
EL-MC20-CF	2.2 ± 1.3	35.6 ± 0.6	20.95 ± 0.19	102.5	46.6	30.2	27.5	31.6	14.5
EL-MC30-CF	1.2 ± 3.2	27.4 ± 1.9	30.41 ± 0.07	99.6	45.3	45.9	29.5	45.6	22.1
EL-MC40-CF	5.2 ± 2.4	25.0 ± 1.2	40.93 ± 0.04	98.6	46.4	66.8	27.4	65.6	32.1

T_g = glass transition temperature of the PCM (°C); T_m = melting temperature of the PCM (°C); ΔH_m = PCM melting enthalpy (J/g); T_c = crystallization temperature of the PCM (°C); ΔH_c = PCM crystallization enthalpy (J/g); ω_{MC} = experimental weight fraction of microcapsules (wt%); ϑ_v = voids volume fraction (vol%); ϑ_f = fiber volume fraction (vol%); ϑ_{MC} = MC volume fraction (vol%).

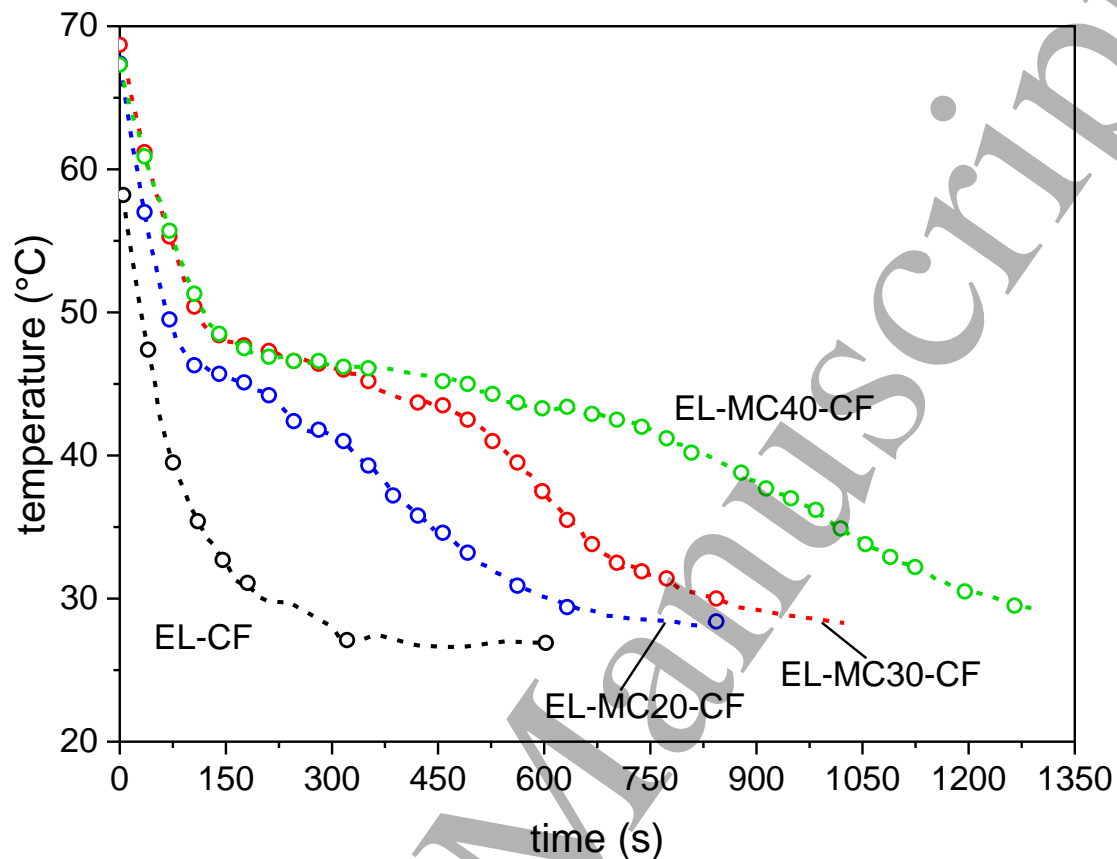


Figure 19. Thermal camera tests on the samples EL-MCx-CF. Temperature as a function of time during cooling to room temperature (in-plane dimensions 90 x 120 mm²) (adapted from [158]).

Finally, the prepared laminates were subjected to an in-depth characterization through dynamic-mechanical analysis (DMA). Three testing modes were investigated, namely single-frequency scans, multifrequency scans and heating-cooling cycles. The trends of the storage modulus E' and the loss modulus E'' acquired during single-frequency scans are illustrated in Figure 20. To facilitate the comparison, the values of E' of each laminate have been normalized to the value at 0 °C. The storage modulus of all laminates shows a marked decrease at the glass transition of the EL matrix, where E'' shows a peak. The laminates containing MC shows an additional transition at the PCM melting temperature, and the drop of E' is more evident at high MC contents. Interestingly, the correlation between the drop amplitude and the MC weight fraction or the melting enthalpy is linear, with R^2 values higher than 0.98. Another DMA parameter that correlates linearly with the melting enthalpy is the area under the $\tan\delta$ peak (reported in [159]). This implies that the DSC test allows one to predict, to a certain extent, the trend of the viscoelastic properties of the composite in the temperature range around the PCM phase change.

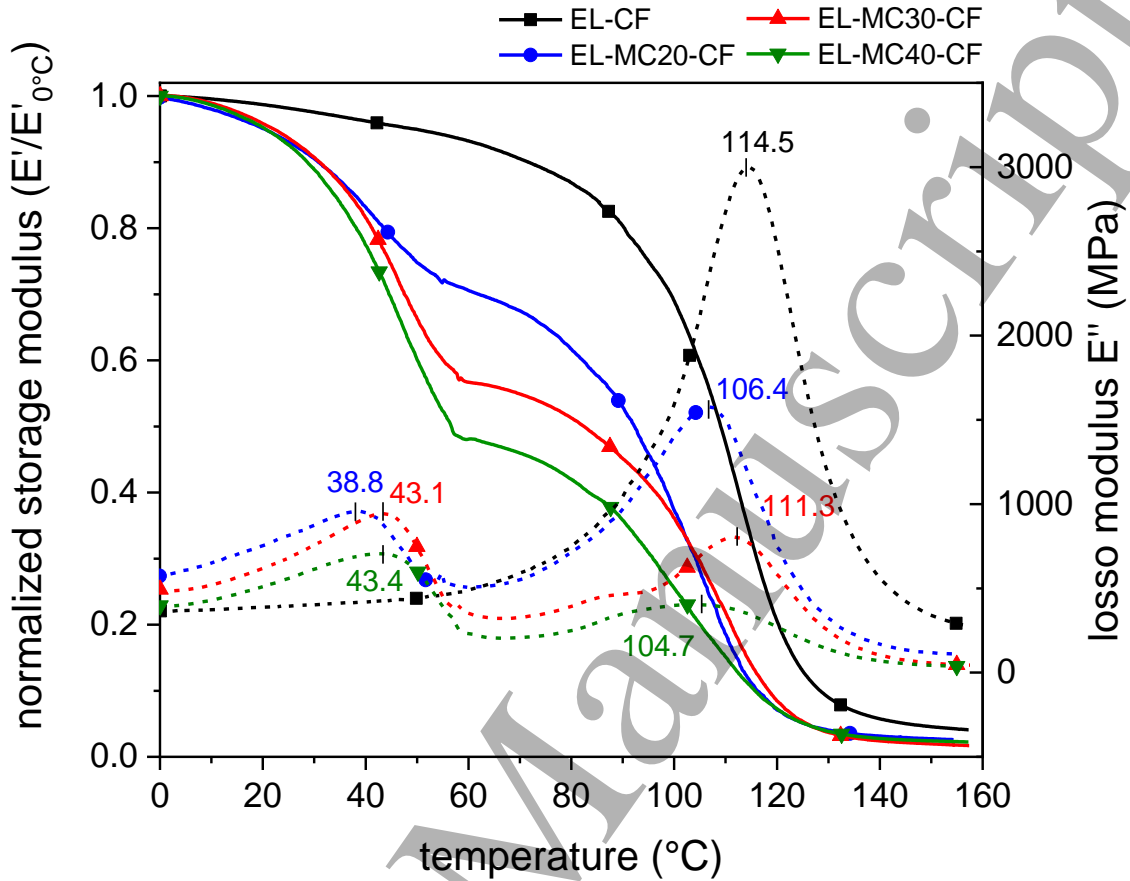


Figure 20. Results of the DMA tests on the samples EL-MC_x-CF. The reported values represent the peak temperatures. (a) normalized storage modulus E' (solid lines) and loss modulus E'' (dashed lines) (single cantilever; 1 Hz; 3 °C/min) (adapted from [158] and [159]).

As structural TES composites must withstand repeated thermal cycles around the phase change temperature of the PCM, DMA tests were performed not only on heating, but also on cooling, between -40 °C and 60 °C. This is not a common approach as no other studies can be found in the literature that analyze the trend of viscoelastic parameters of PCM-enhanced polymers on cooling, to the best of the authors' knowledge. Figure 21 illustrates the trends of E' during a heating-cooling-heating scan performed at 3 °C/min on the three prepared MC-containing laminates. The absolute values of E' decrease with an increase in the MC weight fraction, which was expected from the decreasing values of the elastic modulus (Figure 17). The decreasing step of E' at the PCM melting is almost completely recovered on cooling, as it reaches 90-95% of the initial value. The recovery happens with a certain hysteresis, as the crystallization is found at lower temperatures than the melting, as also observed in DSC tests, due to reasons related both to thermal inertia and to the thermodynamics of crystallization. The trends of E'' and $\tan\delta$ (reported in [159]) also show that the peak on cooling (crystallization) is found

approx. 30 °C lower than the melting peak. From these findings, DMA test appears as a powerful technique to evaluate material stiffness during phase transition of PCM, especially combined with DSC analysis (for a better comparison, the same rate of heating/cooling is suggested).

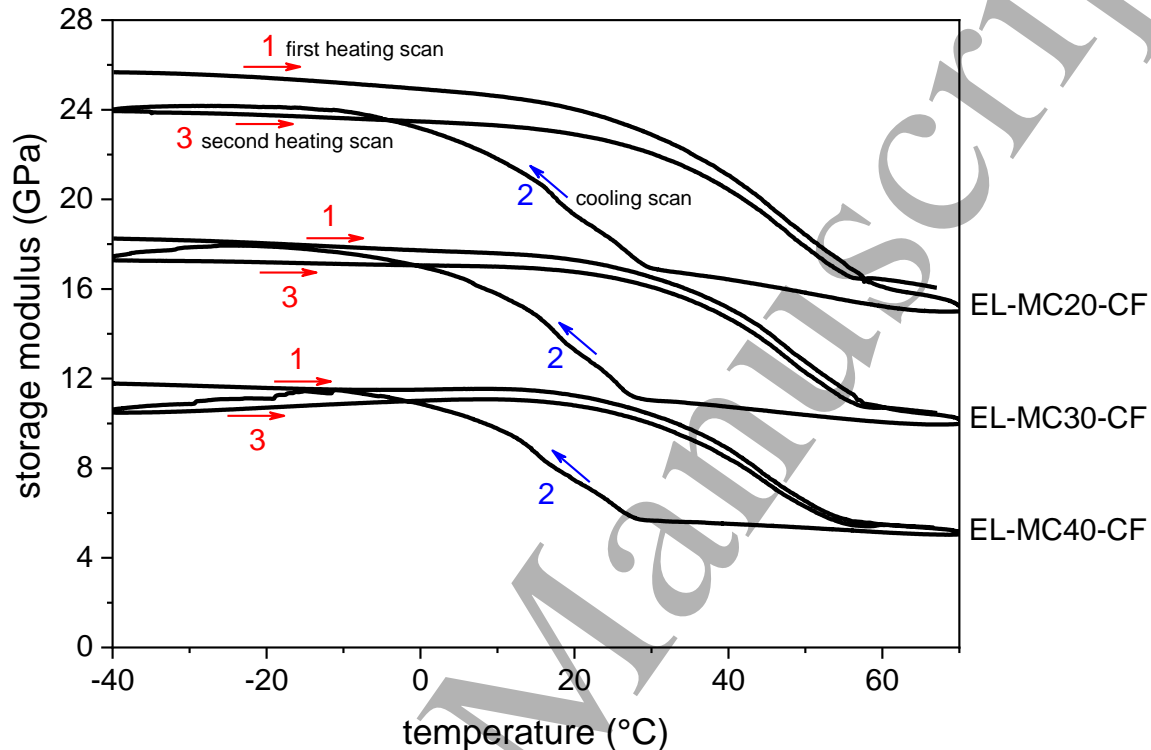


Figure 21. DMA heating (1)-cooling (2)-heating (3) scans on the samples EL-MCx-CF: values of E' in the temperature range around the phase change temperature of the PCM (single cantilever; 1 Hz; 3 °C/min) (adapted from [158] and [159]).

Finally, multifrequency DMA analysis was performed to assess the effect of frequency on the PCM melting and the glass transition of the EL resin. Figure 22 presents the results of the sample EL-MC30-CF. The shift of the signals towards higher temperature with increasing frequency is observable not only at the glass transition of the EL resin, as commonly observed in polymer composites, but also at the PCM melting. For this transition, the frequency sensitivity is higher below the peak temperature than above it, as after the peak temperature the curves are almost overlapped. This suggests that when the core is completely molten the dependence of the signals on frequency weakens considerably.

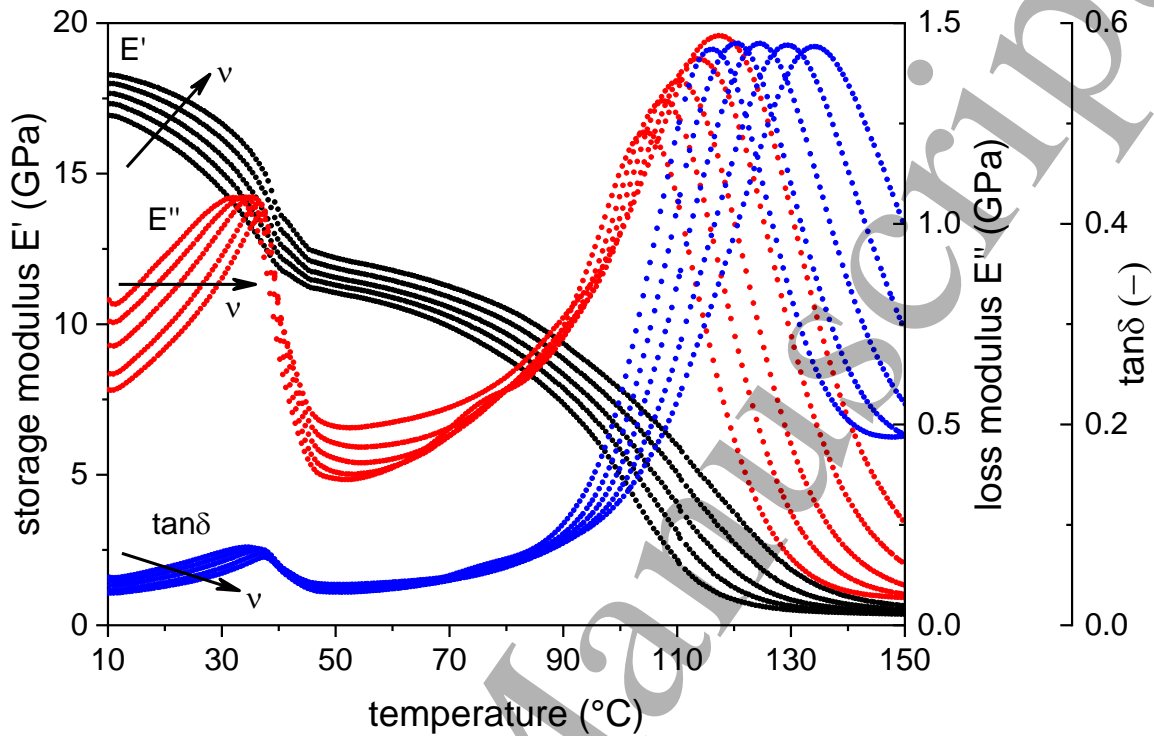


Figure 22. Representative DMA multifrequency thermograms of the sample EL-MC30-CF (single cantilever; 0.3-1-3-10-30 Hz; 0.3 °C/min) (adapted from [158] and [159]).

5. Conclusions and future perspectives

This review introduced the main concepts of thermal energy storage (TES) and summarized the most widely used phase change materials (PCMs), with a special focus on organic solid-liquid PCMs and their thermal management applications at low-medium temperatures (0-100 °C). It then explored the approach of embedding TES and thermal management functionalities in structural and semistructural materials, through the development of multifunctional polymer composites that could find applications where weight saving and temperature management are equally important, such as in the transportation and portable electronic fields. Moreover, PCMs embedded in polymer composites could also be useful to produce anti-icing structures for wind blades, to thermally protect the composite itself, whose mechanical properties could degrade with a temperature increase.

The concept of structural TES composites was elucidated in the second part of the review, dedicated to the presentation of three case studies. The characterization of the glass/polyamide laminates (Section 4.1) evidenced that the microcapsules are more suitable than CNT-stabilized paraffin

(ParCNT) to be compounded with a traditional thermoplastic matrix, due to their higher thermal resistance. However, the melt-compounding and the two hot-pressing operations damage the microcapsule shells considerably, thereby causing paraffin leakage and degradation and diminishing the total final phase change enthalpy. A remarkable improvement of the final TES properties was obtained by reinforcing the PA-based composites with discontinuous carbon fibers, as described in Section 4.2. This was possible because this strategy allows avoiding one of the two hot-pressing steps, but this approach is only applicable to discontinuous fiber composites. Further increases in the mechanical and TES properties were achieved by using a reactive thermoplastic matrix, as reported in Section 4.3. Such resin allows mild conditions in all the processing steps, which do not cause PCM degradation.

Future work should focus on finding shape-stabilizing agents that also enhance the thermal degradation resistance of the PCM and the thermal conductivity of the composite, since the use of an appropriate shape-stabilizing filler could be a powerful and low-cost alternative to microencapsulation. Moreover, a deeper investigation should be carried out on studying and optimizing the mechanical and physical properties of the microcapsules, such as the size, mechanical strength and stiffness of the shell, and adhesion with the surrounding matrix. Furthermore, DMA revealed a promising tool to investigate the effect of the PCM melting and crystallization on the properties of the host composite, in combination with DSC, and therefore it would be worth exploring the use of this test more in depth. Moreover, it will be fundamental to investigate the quasi-static mechanical properties of the PCM-containing composites above the melting temperature of the PCMs for a better definition of the overall performance in the working temperature range. A key factor will be the proper definition of an adequate balance between the increase in TES properties and the decrease in mechanical properties, especially in the thermal transition interval.

References

- [1] I. Dincer, M.A. Egan, Heat Storage: A Unique Solution For Energy Systems 1ed., Springer International Publishing, 2018.
- [2] G.A. Lane, Solar Heat Storage Latent Heat Materials, Volume 1: Background and Scientific Principles, CRC Press, 6000 Broken Sound Parkway NW, Suite 300, Boca Raton, FL 33487-2742, 1983.
- [3] I. Dincer, M.A. Rosen, Thermal Energy Storage. Systems and Applications, 2 ed., John Wiley and Sons, Ltd., Chichester, West Sussex, PO19 8SQ, United Kingdom, 2011.
- [4] S. Kalaiselvam, R. Parameshwaran, Thermal energy storage technologies for sustainability: systems design, assessment, and applications, Academic Press - Elsevier, 32 Jamestown Road, London NW1 7BY, UK, 2014.
- [5] L.F. Cabeza, Advances in Thermal Energy Storage Systems: Methods and Applications, Woodhead Publishing, 80 High Street, Sawston, Cambridge, CB22 3HJ, UK, 2014.

- [6] J. Zhang, H.-H. Zhang, Y.-L. He, W.-Q. Tao, A comprehensive review on advances and applications of industrial heat pumps based on the practices in China, *Appl. Energy* 178 (2016) 800-825. <https://www.doi.org/10.1016/j.apenergy.2016.06.049>
- [7] N. Sheng, C. Zhu, H. Sakai, T. Akiyama, T. Nomura, Synthesis of Al-25 wt% Si@Al₂O₃@Cu microcapsules as phase change materials for high temperature thermal energy storage, *Solar Energy Materials & Solar Cells* 191 (2019) 141–147. <https://www.doi.org/10.1016/j.solmat.2018.11.013>
- [8] M. Ostry, P. Charvat, Materials for advanced heat storage in buildings, 11th International Conference on Modern Building Materials, Structures and Techniques (MBMST 2013), *Procedia Engineering*, Vilnius, Lithuania, 2013, pp. 837-843. <https://www.doi.org/10.1016/j.proeng.2013.04.106>
- [9] C. Cherif, N.H.A. Tran, M. Kirsten, H. Bruenig, R. Vogel, Environmentally friendly and highly productive bi-component melt spinning of thermoregulated smart polymer fibres with high latent heat capacity, *Express Polymer Letters* 12(3) (2018) 203-214. <https://www.doi.org/10.3144/expresspolymlett.2018.19>
- [10] R. Kandasamy, X.-Q. Wang, A.S. Mujumdar, Application of phase change materials in thermal management of electronics, *Applied Thermal Engineering* 27(17-18) (2007) 2822-2832. <https://www.doi.org/10.1016/j.applthermaleng.2006.12.013>
- [11] A. Safari, R. Saidur, F.A. Sulaiman, Y. Xu, J. Dong, A review on supercooling of Phase Change Materials in thermal energy storage systems, *Renewable and Sustainable Energy Reviews* 70 (2017) 905-919. <https://www.doi.org/10.1016/j.rser.2016.11.272>
- [12] K. Pielichowska, K. Pielichowski, Phase change materials for thermal energy storage, *Progress in materials science* 65 (2014) 67-123. <https://www.doi.org/10.1016/j.pmatsci.2014.03.005>
- [13] P.H. Feng, B.C. Zhao, R.Z. Wang, Thermophysical heat storage for cooling, heating, and power generation: A review, *Applied Thermal Engineering* 166 (2020).
- [14] S.M. Hasnain, Review on sustainable thermal energy storage technologies, Part I: heat storage materials and techniques, *Energy Conversion and Management* 39(11) (1998) 1127-1138. [https://www.doi.org/10.1016/S0196-8904\(98\)00025-9](https://www.doi.org/10.1016/S0196-8904(98)00025-9)
- [15] G. Mohan, M.B. Venkataraman, J. Coventry, Sensible energy storage options for concentrating solar power plants operating above 600 degrees C, *Renew. Sust. Energ. Rev.* 107 (2019) 319-337.
- [16] H. Panchal, J. Patel, S. Chaudhary, A comprehensive review of solar cooker with sensible and latent heat storage materials, *International Journal of Ambient Energy* 40(3) (2019) 329-334.
- [17] D. Aydin, S.P. Casey, S. Riffat, The latest advancements on thermochemical heat storage systems, *Renewable and Sustainable Energy Reviews* 41 (2015) 356-367. <https://www.doi.org/10.1016/j.rser.2014.08.054>
- [18] A.J. Carrillo, J. Gonzalez-Aguilar, M. Romero, J.M. Coronado, Solar Energy on Demand: A Review on High Temperature Thermochemical Heat Storage Systems and Materials, *Chemical Reviews* 119(7) (2019) 4777-4816.
- [19] S. Vasta, V. Brancato, D. La Rosa, V. Palomba, G. Restuccia, A. Sapienza, A. Frazzica, Adsorption Heat Storage: State-of-the-Art and Future Perspectives, *Nanomaterials (Basel)* 8(7) (2018). <https://www.doi.org/10.3390/nano8070522>
- [20] H. Jarimi, D. Aydin, Z. Yanan, G. Ozankaya, X. Chen, S. Riffat, Review on the recent progress of thermochemical materials and processes for solar thermal energy storage and industrial waste heat recovery, *International Journal of Low-Carbon Technologies* 14(1) (2019) 44-69. <https://www.doi.org/10.1093/ijlct/cty052>
- [21] R.J. Clark, A. Mehrabadi, M. Farid, State of the art on salt hydrate thermochemical energy storage systems for use in building applications, *Journal of Energy Storage* 27 (2020).
- [22] B. Zalba, J.M. Marin, L.F. Cabeza, H. Mehling, Review on thermal energy storage with phase change: materials, heat transfer analysis and applications, *Applied Thermal Engineering* 23 (2003) 251-283. [https://www.doi.org/10.1016/S1359-4311\(02\)00192-8](https://www.doi.org/10.1016/S1359-4311(02)00192-8)
- [23] M.M. Farid, A.M. Khudhair, S.A.K. Razack, S. Al-Hallaj, A review on phase change energy storage: Materials and applications, *Energy Conversion and Management* 45(9-10) (2004) 1597-1615. <https://www.doi.org/10.1016/j.enconman.2003.09.015>

- [24] H. Akeiber, P. Nejat, M.Z.A. Majid, M.A. Wahid, F. Jomehzadeh, I. Zeynali Famileh, J.K. Calautit, B.R. Hughes, S.A. Zaki, A review on phase change material (PCM) for sustainable passive cooling in building envelopes, *Renewable and Sustainable Energy Reviews* 60 (2016) 1470-1497. <https://www.doi.org/10.1016/j.rser.2016.03.036>
- [25] Y. Konuklu, M. Ostry, H.O. Paksoy, P. Charvat, Review on using microencapsulated phase change materials (PCM) in building applications, *Energy and Buildings* 106 (2015) 134-155. <https://www.doi.org/10.1016/j.enbuild.2015.07.019>
- [26] A.S. Fleischer, *Thermal Energy Storage using Phase Change Materials - Fundamentals and Applications*, Series SpringerBriefs in Thermal Engineering and Applied Science. Springer, Heidelberg, Germany, 2015. <https://www.doi.org/10.1007/978-3-319-20922-7>
- [27] I. Dincer, H.S. Hamut, N. Javani, *Thermal Management of Electric Vehicle Battery Systems*, John Wiley & Sons 2017.
- [28] W. Yuan, X. Yang, G. Zhang, X. Li, A thermal conductive composite phase change material with enhanced volume resistivity by introducing silicon carbide for battery thermal management, *Applied Thermal Engineering* 144 (2018) 551-557. <https://www.doi.org/10.1016/j.applthermaleng.2018.07.095>
- [29] A. Lazrak, J.-F. Fourmigué, J.-F. Robin, An innovative practical battery thermal management system based on phase change materials: Numerical and experimental investigations, *Applied Thermal Engineering* 128 (2018) 20-32. <https://www.doi.org/10.1016/j.applthermaleng.2017.08.172>
- [30] X. Bao, Y. Tian, L. Yuan, H. Cui, W. Tang, W.H. Fung, H. Qi, Development of high performance PCM cement composites for passive solar buildings, *Energy and Buildings* 194 (2019) 33-45. <https://www.doi.org/10.1016/j.enbuild.2019.04.011>
- [31] Z.A. Qureshi, H.M. Ali, S. Khushnood, Recent advances on thermal conductivity enhancement of phase change materials for energy storage system: A review, *International Journal of Heat and Mass Transfer* 127 (2018) 838-856. <https://www.doi.org/10.1016/j.ijheatmasstransfer.2018.08.049>
- [32] Y. Lin, Y. Jia, G. Alva, G. Fang, Review on thermal conductivity enhancement, thermal properties and applications of phase change materials in thermal energy storage, *Renewable and Sustainable Energy Reviews* 82 (2018) 2730-2742. <https://www.doi.org/10.1016/j.rser.2017.10.002>
- [33] X. Huang, Y.X. Lin, G. Alva, G.Y. Fang, Thermal properties and thermal conductivity enhancement of composite phase change materials using myristyl alcohol/metal foam for solar thermal storage, *Sol. Energy Mater. Sol. Cells* 170 (2017) 68-76. <https://www.doi.org/10.1016/j.solmat.2017.05.059>
- [34] V. Kapsalis, D. Karamanis, Solar thermal energy storage and heat pumps with phase change materials, *Applied Thermal Engineering* 99 (2016) 1212-1224. <https://www.doi.org/10.1016/j.applthermaleng.2016.01.071>
- [35] D. Rigotti, A. Dorigato, A. Pegoretti, 3D printable thermoplastic polyurethane blends with thermal energy storage/release capabilities, *Materials Today Communications* 15 (2018) 228-235. <https://www.doi.org/10.1016/j.mtcomm.2018.03.009>
- [36] A. Abhat, low temperature latent heat thermal energy storage: Heat storage materials, *Solar Energy* 30(4) (1983) 313-332. [https://www.doi.org/https://doi.org/10.1016/0038-092X\(83\)90186-X](https://www.doi.org/https://doi.org/10.1016/0038-092X(83)90186-X)
- [37] Q. Zhang, J. Liu, Anisotropic thermal conductivity and photodriven phase change composite based on RT100 infiltrated carbon nanotube array, *Sol. Energy Mater. Sol. Cells* 190 (2019) 1-5. <https://www.doi.org/10.1016/j.solmat.2018.10.010>
- [38] Y. Lin, C. Zhu, G. Fang, Synthesis and properties of microencapsulated stearic acid/silica composites with graphene oxide for improving thermal conductivity as novel solar thermal storage materials, *Sol. Energy Mater. Sol. Cells* 189 (2019) 197-205. <https://www.doi.org/10.1016/j.solmat.2018.10.005>
- [39] Y. Zhu, Y. Chi, S. Liang, X. Luo, K. Chen, C. Tian, J. Wang, L. Zhang, Novel metal coated nanoencapsulated phase change materials with high thermal conductivity for thermal energy storage, *Sol. Energy Mater. Sol. Cells* 176 (2018) 212-221. <https://www.doi.org/10.1016/j.solmat.2017.12.006>
- [40] M.J. Mochane, A.S. Luyt, The effect of expanded graphite on the thermal stability, latent heat, and flammability properties of EVA/wax phase change blends, *Polymer Engineering & Science* 55(6) (2015) 1255-1262. <https://www.doi.org/10.1002/pen.24063>

- [41] Y. Cai, Y. Hu, L. Song, Q. Kong, R. Yang, Y. Zhang, Z. Chen, W. Fan, Preparation and flammability of high density polyethylene/paraffin/organophilic montmorillonite hybrids as a form stable phase change material, *Energy Conversion and Management* 48(2) (2007) 462-469. <https://www.doi.org/10.1016/j.enconman.2006.06.021>
- [42] L. Bayés-García, L. Ventolà, R. Cordobilla, R. Benages, T. Calvet, M.A. Cuevas-Diarte, Phase Change Materials (PCM) microcapsules with different shell compositions: Preparation, characterization and thermal stability, *Sol. Energy Mater. Sol. Cells* 94(7) (2010) 1235-1240. <https://www.doi.org/10.1016/j.solmat.2010.03.014>
- [43] A. Hassan, M. Shakeel Laghari, Y. Rashid, Micro-Encapsulated Phase Change Materials: A Review of Encapsulation, Safety and Thermal Characteristics, *Sustainability* 8(10) (2016) 1046/1-1046/32. <https://www.doi.org/10.3390/su8101046>
- [44] N. Sarier, E. Onder, Organic phase change materials and their textile applications: An overview, *Thermochimica Acta* 540 (2012) 7-60. <https://www.doi.org/10.1016/j.tca.2012.04.013>
- [45] R.K. Sharma, P. Ganesan, V.V. Tyagi, H.S.C. Metselaar, S.C. Sandaran, Developments in organic solid-liquid phase change materials and their applications in thermal energy storage, *Energy Conversion and Management* 95 (2015) 193-228. <https://www.doi.org/10.1016/j.enconman.2015.01.084>
- [46] S. Kahwaji, M.B. Johnson, A.C. Kheirabadi, D. Groulx, M.A. White, A comprehensive study of properties of paraffin phase change materials for solar thermal energy storage and thermal management applications, *Energy* 162 (2018) 1169-1182. <https://www.doi.org/10.1016/j.energy.2018.08.068>
- [47] A.B. Rezaie, M. Montazer, One-step fabrication of fatty acids/nano copper/polyester shape-stable composite phase change material for thermal energy management and storage, *Appl. Energy* 228 (2018) 1911-1920. <https://www.doi.org/10.1016/j.apenergy.2018.07.041>
- [48] A. Kylili, P.A. Fokaides, Life Cycle Assessment (LCA) of Phase Change Materials (PCMs) for building applications: A review, *Journal of Building Engineering* 6 (2016) 133-143. <https://www.doi.org/10.1016/j.jobbe.2016.02.008>
- [49] A. Sari, A. Biçer, C. Alkan, Poly(Styrene-Co-Maleic Anhydride)-Graft-Fatty Acids as Novel Solid-Solid PCMs for Thermal Energy Storage, *Polymer Engineering & Science* 59(s2 - special issue: Applied Polymers) (2019) E337-E347. <https://www.doi.org/10.1002/pen.25064>
- [50] S. Sundararajan, A. Kumar, B.C. Chakraborty, A.B. Samui, P.S. Kulkarni, Poly(ethylene glycol) (PEG)-modified epoxy phase-change polymer with dual properties of thermal storage and vibration damping, *Sustainable Energy & Fuels* 2(3) (2018) 688-697. <https://www.doi.org/10.1039/c7se00552k>
- [51] K. Król, B. Macherzyńska, K. Pielichowska, Acrylic bone cements modified with poly(ethylene glycol)-based biocompatible phase-change materials, *Journal of Applied Polymer Science* 133(36) (2016). <https://www.doi.org/10.1002/app.43898>
- [52] L.-l. Zou, X. Chen, Y.-t. Wu, X. Wang, C.-f. Ma, Experimental study of thermophysical properties and thermal stability of quaternary nitrate molten salts for thermal energy storage, *Sol. Energy Mater. Sol. Cells* 190 (2019) 12-19. <https://www.doi.org/10.1016/j.solmat.2018.10.013>
- [53] N. Xie, J. Luo, Z. Li, Z. Huang, X. Gao, Y. Fang, Z. Zhang, Salt hydrate/expanded vermiculite composite as a form-stable phase change material for building energy storage, *Sol. Energy Mater. Sol. Cells* 189 (2019) 33-42. <https://www.doi.org/10.1016/j.solmat.2018.09.016>
- [54] T. Khadiran, M.Z. Hussein, Z. Zainal, R. Rusli, Encapsulation techniques for organic phase change materials as thermal energy storage medium: A review, *Sol. Energy Mater. Sol. Cells* 143 (2015) 78-98. <https://www.doi.org/10.1016/j.solmat.2015.06.039>
- [55] Y. Cui, J. Xie, J. Liu, S. Pan, Review of Phase Change Materials Integrated in Building Walls for Energy Saving, *Procedia Engineering* 121 (2015) 763-770. <https://www.doi.org/10.1016/j.proeng.2015.09.027>
- [56] H. Peng, D. Zhang, X. Ling, Y. Li, Y. Wang, Q. Yu, X. She, Y. Li, Y. Ding, *n*-Alkanes phase change materials and their microencapsulation for thermal energy storage: a critical review, *Energy & Fuels* 32(7) (2018) 7262-7293. <https://www.doi.org/10.1021/acs.energyfuels.8b01347>

- [57] A. Jamekhorshid, S.M. Sadrameli, M. Farid, A review of microencapsulation methods of phase change materials (PCMs) as a thermal energy storage (TES) medium, *Renewable and Sustainable Energy Reviews* 31 (2014) 531-542. <https://www.doi.org/10.1016/j.rser.2013.12.033>
- [58] C.Y. Zhao, G.H. Zhang, Review on microencapsulated phase change materials (MEPCMs): Fabrication, characterization and applications, *Renewable and Sustainable Energy Reviews* 15(8) (2011) 3813-3832. <https://www.doi.org/10.1016/j.rser.2011.07.019>
- [59] V.V. Tyagi, S.C. Kaushik, S.K. Tyagi, T. Akiyama, Development of phase change materials based microencapsulated technology for buildings: A review, *Renewable and Sustainable Energy Reviews* 15(2) (2011) 1373-1391. <https://www.doi.org/10.1016/j.rser.2010.10.006>
- [60] S. Freitas, H.P. Merkle, B. Gander, Microencapsulation by solvent extraction/evaporation: reviewing the state of the art of microsphere preparation process technology, *J Control Release* 102(2) (2005) 313-32. <https://www.doi.org/10.1016/j.jconrel.2004.10.015>
- [61] L.Y. Wang, P.S. Tsai, Y.M. Yang, Preparation of silica microspheres encapsulating phase-change material by sol-gel method in O/W emulsion, *J Microencapsul* 23(1) (2006) 3-14. <https://www.doi.org/10.1080/02652040500286045>
- [62] R. Ciriminna, M. Sciortino, G. Alonzo, A. de Schrijver, M. Pagliaro, From Molecules to Systems: Sol-Gel Microencapsulation in Silica-Based Materials, *Chemical Reviews* 111(2) (2011) 765–789. <https://www.doi.org/10.1021/cr100161x>
- [63] H. Zhang, X. Wang, D. Wu, Silica encapsulation of *n*-octadecane via sol-gel process: a novel microencapsulated phase-change material with enhanced thermal conductivity and performance, *J Colloid Interface Sci* 343(1) (2010) 246-55. <https://www.doi.org/10.1016/j.jcis.2009.11.036>
- [64] Z. Chen, L. Cao, G. Fang, F. Shan, Synthesis and Characterization of Microencapsulated Paraffin Microcapsules as Shape-Stabilized Thermal Energy Storage Materials, *Nanoscale and Microscale Thermophysical Engineering* 17(2) (2013) 112-123. <https://www.doi.org/10.1080/15567265.2012.761305>
- [65] F. Tang, L. Liu, G. Alva, Y. Jia, G. Fang, Synthesis and properties of microencapsulated octadecane with silica shell as shape-stabilized thermal energy storage materials, *Sol. Energy Mater. Sol. Cells* 160 (2017) 1-6. <https://www.doi.org/10.1016/j.solmat.2016.10.014>
- [66] M.M. Umair, Y. Zhang, K. Iqbal, S. Zhang, B. Tang, Novel strategies and supporting materials applied to shape-stabilize organic phase change materials for thermal energy storage—A review, *Appl. Energy* 235 (2019) 846-873. <https://www.doi.org/10.1016/j.apenergy.2018.11.017>
- [67] P. Zhang, X. Xiao, Z.W. Ma, A review of the composite phase change materials: Fabrication, characterization, mathematical modeling and application to performance enhancement, *Appl. Energy* 165 (2016) 472-510. <https://www.doi.org/10.1016/j.apenergy.2015.12.043>
- [68] Y. Xia, H. Zhang, P. Huang, C. Huang, F. Xu, Y. Zou, H. Chu, E. Yan, L. Sun, Graphene-oxide-induced lamellar structures used to fabricate novel composite solid-solid phase change materials for thermal energy storage, *Chemical Engineering Journal* 362 (2019) 909-920. <https://www.doi.org/10.1016/j.cej.2019.01.097>
- [69] P. Zhang, Y. Hu, L. Song, J. Ni, W. Xing, J. Wang, Effect of expanded graphite on properties of high-density polyethylene/paraffin composite with intumescent flame retardant as a shape-stabilized phase change material, *Sol. Energy Mater. Sol. Cells* 94(2) (2010) 360-365. <https://www.doi.org/10.1016/j.solmat.2009.10.014>
- [70] A. Sari, A. Karaipekli, Thermal conductivity and latent heat thermal energy storage characteristics of paraffin/expanded graphite composite as phase change material, *Applied Thermal Engineering* 27(8-9) (2007) 1271-1277. <https://www.doi.org/10.1016/j.applthermaleng.2006.11.004>
- [71] K. Biswas, J. Lu, P. Soroushian, S. Shrestha, Combined experimental and numerical evaluation of a prototype nano-PCM enhanced wallboard, *Appl. Energy* 131 (2014) 517-529. <https://www.doi.org/10.1016/j.apenergy.2014.02.047>
- [72] X. Fang, L.W. Fan, Q. Ding, X.L. Yao, Y.Y. Wu, J.F. Hou, X. Wang, Z.T. Yu, G.H. Cheng, Y.C. Hu, Thermal energy storage performance of paraffin-based composite phase change materials filled with hexagonal boron nitride nanosheets, *Energy Conversion and Management* 80 (2014) 103-109. <https://www.doi.org/10.1016/j.enconman.2014.01.016>

- [73] K. Resch-Fauster, M. Feuchter, Thermo-physical characteristics, mechanical performance and long-term stability of high temperature latent heat storages based on paraffin-polymer compounds, *Thermochimica Acta* 663 (2018) 34-45. <https://www.doi.org/10.1016/j.tca.2018.03.004>
- [74] A. Dorigato, M.V. Ciampolillo, A. Cataldi, M. Bersani, A. Pegoretti, Polyethylene wax/EPDM blends as shape-stabilized phase change materials for thermal energy storage, *Rubber Chemistry and Technology* 90(3) (2017) 575-584. <https://www.doi.org/10.5254/rct.82.83719>
- [75] A. Dorigato, P. Canclini, S.H. Unterberger, A. Pegoretti, Phase changing nanocomposites for low temperature thermal energy storage and release, *Express Polymer Letters* 11(9) (2017) 738-752. <https://www.doi.org/10.3144/expresspolymlett.2017.71>
- [76] L. Cao, F. Tang, G. Fang, Synthesis and characterization of microencapsulated paraffin with titanium dioxide shell as shape-stabilized thermal energy storage materials in buildings, *Energy and Buildings* 72 (2014) 31-37. <https://www.doi.org/10.1016/j.enbuild.2013.12.028>
- [77] K. Iqbal, A. Khan, D. Sun, M. Ashraf, A. Rehman, F. Safdar, A. Basit, H.S. Maqsood, Phase change materials, their synthesis and application in textiles — a review, *The Journal of The Textile Institute* 110(4) (2019) 625-638. <https://www.doi.org/10.1080/00405000.2018.1548088>
- [78] S.C. Fok, W. Shen, F.L. Tan, Cooling of portable hand-held electronic devices using phase change materials in finned heat sinks, *International Journal of Thermal Sciences* 49(1) (2010) 109-117. <https://www.doi.org/10.1016/j.ijthermalsci.2009.06.011>
- [79] A.M. Goitandia, M.B. Miguel, A.M. Babiano, O.G. Miguel, Use of phase change materials to delay icing or to cause de-icing in wind-driven power generators, *Gamesa Innovation & Technology*, Sarriguren, Navarra (ES), 2018.
- [80] S. Singh, K.K. Gaikwad, Y.S. Lee, Phase change materials for advanced cooling packaging, *Environmental Chemistry Letters* 16(3) (2018) 845-859. <https://www.doi.org/10.1007/s10311-018-0726-7>
- [81] X. Cao, X. Dai, J. Liu, Building energy-consumption status worldwide and the state-of-the-art technologies for zero-energy buildings during the past decade, *Energy and Buildings* 128 (2016) 198-213. <https://www.doi.org/10.1016/j.enbuild.2016.06.089>
- [82] M. Kenisarin, K. Mahkamov, Passive thermal control in residential buildings using phase change materials, *Renewable and Sustainable Energy Reviews* 55 (2016) 371-398. <https://www.doi.org/10.1016/j.rser.2015.10.128>
- [83] D. Feldman, D. Banu, DSC analysis for the evaluation of an energy storing wallboard, *Thermochimica Acta* 272 (1996) 243-251.
- [84] S. Scalat, D. Banu, D. Hawes, J. Paris, F. Haghghata, D. Feldman, Full scale thermal testing of latent heat storage in wallboard, *Sol. Energy Mater. Sol. Cells* 44 (1996) 49-61.
- [85] Q. Wang, C.Y. Zhao, Parametric investigations of using a PCM curtain for energy efficient buildings, *Energy and Buildings* 94 (2015) 33-42. <https://www.doi.org/10.1016/j.enbuild.2015.02.024>
- [86] B. Savija, Smart Crack Control in Concrete through Use of Phase Change Materials (PCMs): A Review, *Materials (Basel)* 11(5) (2018). <https://www.doi.org/10.3390/ma11050654>
- [87] K. Lin, Y. Zhang, X. Xu, H. Di, R. Yang, P. Qin, Experimental study of under-floor electric heating system with shape-stabilized PCM plates, *Energy and Buildings* 37(3) (2005) 215-220. <https://www.doi.org/10.1016/j.enbuild.2004.06.017>
- [88] J. Zhou, Y. Cui, H. Yao, J. Ma, H. Ren, Nanocapsules containing binary phase change material obtained via miniemulsion polymerization with reactive emulsifier: Synthesis, characterization, and application in fabric finishing, *Polymer Engineering & Science* 59(s2) (2019) E42-E51. <https://www.doi.org/10.1002/pen.24951>
- [89] S. Mondal, Phase change materials for smart textiles – An overview, *Applied Thermal Engineering* 28(11-12) (2008) 1536-1550. <https://www.doi.org/10.1016/j.applthermaleng.2007.08.009>
- [90] K. Iqbal, D. Sun, Development of thermal stable multifilament yarn containing micro-encapsulated phase change materials, *Fibers and Polymers* 16(5) (2015) 1156-1162. <https://www.doi.org/10.1007/s12221-015-1156-9>

- [91] S.K. Sahoo, M.K. Das, P. Rath, Application of TCE-PCM based heat sinks for cooling of electronic components: A review, *Renewable and Sustainable Energy Reviews* 59 (2016) 550-582.
<https://www.doi.org/10.1016/j.rser.2015.12.238>
- [92] F.L. Tan, C.P. Tso, Cooling of mobile electronic devices using phase change materials, *Applied Thermal Engineering* 24(2-3) (2004) 159-169.
<https://www.doi.org/10.1016/j.applthermaleng.2003.09.005>
- [93] Y. Tomizawa, K. Sasaki, A. Kuroda, R. Takeda, Y. Kaito, Experimental and numerical study on phase change material (PCM) for thermal management of mobile devices, *Applied Thermal Engineering* 98 (2016) 320-329. <https://www.doi.org/10.1016/j.applthermaleng.2015.12.056>
- [94] L. Ianniciello, P.H. Biwolé, P. Achard, Electric vehicles batteries thermal management systems employing phase change materials, *Journal of Power Sources* 378 (2018) 383-403.
<https://www.doi.org/10.1016/j.jpowsour.2017.12.071>
- [95] S. Al Hallaj, J.R. Selman, A Novel Thermal Management System for Electric Vehicle Batteries Using Phase-Change Material, *Journal of The Electrochemical Society* 147 (9) (2000) 3231-3236.
- [96] P. Goli, S. Legedza, A. Dhar, R. Salgado, J. Renteria, A.A. Balandin, Graphene-enhanced hybrid phase change materials for thermal management of Li-ion batteries, *Journal of Power Sources* 248 (2014) 37-43. <https://www.doi.org/10.1016/j.jpowsour.2013.08.135>
- [97] D. Zou, X. Liu, R. He, S. Zhu, J. Bao, J. Guo, Z. Hu, B. Wang, Preparation of a novel composite phase change material (PCM) and its locally enhanced heat transfer for power battery module, *Energy Conversion and Management* 180 (2019) 1196-1202.
<https://www.doi.org/10.1016/j.enconman.2018.11.064>
- [98] K. Friedrich, Routes for achieving multifunctionality in reinforced polymers and composite structures, in: K. Friedrich, U. Breuer (Eds.), *Multifunctionality of Polymer Composites: Challenges and New Solutions*, Elsevier, Waltham, MA, US, 2015, pp. 3-41. <https://www.doi.org/10.1016/b978-0-323-26434-1.00001-5>
- [99] L.E. Asp, E.S. Greenhalgh, Structural power composites, *Composites Science and Technology* 101 (2014) 41-61. <https://www.doi.org/10.1016/j.compscitech.2014.06.020>
- [100] G. Fredi, S. Jeschke, A. Boulaoued, J. Wallenstein, M. Rashidi, F. Liu, R. Harnden, D. Zenkert, J. Hagberg, G. Lindbergh, P. Johansson, L. Stievano, L.E. Asp, Graphitic microstructure and performance of carbon fibre Li-ion battery electrodes, *Multifunctional Materials* 1(1) (2018).
<https://www.doi.org/10.1088/2399-7532/aab707>
- [101] B.D. Agarwal, L.J. Broutman, K. Chandrashekhara, *Analysis and Performance of Fiber Composites*, 4 ed., John Wiley and Sons, Inc.2018.
- [102] T. Carlson, *Multifunctional Composite Materials. Design, Manufacture and Experimental Characterisation*. Doctoral thesis, Department of Engineering Sciences and Mathematics, Materials Science., Luleå University of Technology, Luleå, Sweden, 2013.
- [103] R.F. Gibson, A review of recent research on mechanics of multifunctional composite materials and structures, *Composite Structures* 92(12) (2010) 2793-2810.
<https://www.doi.org/10.1016/j.compstruct.2010.05.003>
- [104] F.C. Campbell, *Structural Composite Materials*, ASM International, Materials Park, Ohio, US, 2010.
- [105] R. Petrucci, L. Torre, Filled Polymer Composites, in: C.F. Jasso-Gastinel, J.M. Kenny (Eds.), *Modification of Polymer Properties*, Elsevier, Chadds Ford, PA, USA, 2017, pp. 23-46.
<https://www.doi.org/10.1016/b978-0-323-44353-1.00002-6>
- [106] M. Biron, *Thermoplastics And Thermoplastic Composites*, Elsevier, Ltd, Oxford, UK, 2013.
<https://www.doi.org/10.1016/B978-1-4557-7898-0.00001-9>
- [107] P. Attar, J. Galos, A.S. Best, A.P. Mouritz, Compression properties of multifunctional composite structures with embedded lithium-ion polymer batteries, *Composite Structures* 237 (2020).
- [108] J. Galos, A.S. Best, A.P. Mouritz, Multifunctional sandwich composites containing embedded lithium-ion polymer batteries under bending loads, *Materials & Design* 185 (2020).

- [109] J. Kim, S. Torquato, Multifunctional composites for elastic and electromagnetic wave propagation, *Proceedings of the National Academy of Sciences of the United States of America* 117(16) (2020) 8764-8774.
- [110] J. Nasser, L. Groo, L.S. Zhang, H. Sodano, Laser induced graphene fibers for multifunctional aramid fiber reinforced composite, *Carbon* 158 (2020) 146-156.
- [111] P.H. Parsania, J.P. Patel, Fabrication and physicochemical properties of glass fabric-multifunctional epoxy resin composite, *Polymer Bulletin* 77(4) (2020) 1667-1679.
- [112] B. Ribeiro, J.A.R. Corredor, M.L. Costa, E.C. Botelho, M.C. Rezende, Multifunctional Characteristics of Glass Fiber-Reinforced Epoxy Polymer Composites with Multiwalled Carbon Nanotube Buckypaper Interlayer, *Polymer Engineering and Science* 60(4) (2020) 740-751.
- [113] M. Zhang, L. Ding, J. Zheng, L.B. Liu, H. Alsulami, M.A. Kutbi, J.L. Xu, Surface modification of carbon fibers with hydrophilic Fe₃O₄ nanoparticles for nickel-based multifunctional composites, *Appl. Surf. Sci.* 509 (2020).
- [114] Y.Q. Zhao, D.N. Zhao, T. Zhang, H.F. Li, B.M. Zhang, Z.C. Zhang, Preparation and multifunctional performance of carbon fiber-reinforced plastic composites for laminated structural batteries, *Polymer Composites* (In Press.).
- [115] A. Steiner, A. Mladek, Reducing the energy consumption for comfort and thermal conditioning in EVs, 2017 Twelfth International Conference on Ecological Vehicles and Renewable Energies, Ieee, New York, 2017.
- [116] J. Jagemont, N. Omar, P. Van den Bossche, J. Mierlo, Phase-change materials (PCM) for automotive applications: A review, *Applied Thermal Engineering* 132 (2018) 308-320.
<https://www.doi.org/10.1016/j.applthermaleng.2017.12.097>
- [117] A. Katunin, Thermal fatigue of polymeric composites under repeated loading, *Journal of Reinforced Plastics and Composites* 31(15) (2012) 1037-1044.
<https://www.doi.org/10.1177/0731684412452679>
- [118] J.A. Casado, F. Gutiérrez-Solana, I. Carrascal, S. Diego, J.A. Polanco, D. Hernández, Fatigue behavior enhancement of short fiber glass reinforced polyamide by adding phase change materials, *Composites Part B: Engineering* 93 (2016) 115-122.
<https://www.doi.org/10.1016/j.compositesb.2016.02.059>
- [119] M.J. Kreder, J. Alvarenga, P. Kim, J. Aizenberg, Design of anti-icing surfaces: smooth, textured or slippery?, *Nature Reviews Materials* 1(1) (2016). <https://www.doi.org/10.1038/natrevmats.2015.3>
- [120] K. Zhu, X. Li, J. Su, H. Li, Y. Zhao, X. Yuan, Improvement of anti-icing properties of low surface energy coatings by introducing phase-change microcapsules, *Polymer Engineering & Science* 58(6) (2018) 973-979. <https://www.doi.org/10.1002/pen.24654>
- [121] V.D. Cao, S. Pilehvar, C. Salas-Bringas, A.M. Szcotok, L. Valentini, M. Carmona, J.F. Rodriguez, A.-L. Kjøniksen, Influence of microcapsule size and shell polarity on thermal and mechanical properties of thermoregulating geopolymers concrete for passive building applications, *Energy Conversion and Management* 164 (2018) 198-209.
<https://www.doi.org/10.1016/j.enconman.2018.02.076>
- [122] F. Chen, M. Wolcott, Polyethylene/paraffin binary composites for phase change material energy storage in building: A morphology, thermal properties, and paraffin leakage study, *Sol. Energy Mater. Sol. Cells* 137 (2015) 79-85. <https://www.doi.org/10.1016/j.solmat.2015.01.010>
- [123] F. Chen, M.P. Wolcott, Miscibility studies of paraffin/polyethylene blends as form-stable phase change materials, *European Polymer Journal* 52 (2014) 44-52.
<https://www.doi.org/10.1016/j.eurpolymj.2013.09.027>
- [124] K. Resch-Fauster, F. Hengstberger, C. Zauner, S. Holper, Overheating protection of solar thermal façades with latent heat storages based on paraffin-polymer compounds, *Energy and Buildings* 169 (2018) 254-259. <https://www.doi.org/10.1016/j.enbuild.2018.03.068>
- [125] X.X. Zhang, X.C. Wang, X.M. Tao, K.L. Yick, Energy storage polymer/MicroPCMs blended chips and thermo-regulated fiber, *Journal of Materials Science* 40 (2005) 3729– 3734.
<https://www.doi.org/10.1007/s10853-005-3314-8>

- [126] I. Krupa, Z. Nógellová, Z. Špitalský, I. Janigová, B. Boh, B. Sumiga, A. Kleinová, M. Karkri, M.A. AlMaadeed, Phase change materials based on high-density polyethylene filled with microencapsulated paraffin wax, *Energy Conversion and Management* 87 (2014) 400-409.
<https://www.doi.org/10.1016/j.enconman.2014.06.061>
- [127] J.-F. Su, Y.-H. Zhao, X.-Y. Wang, H. Dong, S.B. Wang, Effect of interface debonding on the thermal conductivity of microencapsulated-paraffin filled epoxy matrix composites, *Compos. Pt. A- Appl. Sci. Manuf.* 43(3) (2012) 325-332. <https://www.doi.org/10.1016/j.compositesa.2011.12.003>
- [128] J.-F. Su, X.-Y. Wang, Z. Huang, Y.-H. Zhao, X.-Y. Yuan, Thermal conductivity of microPCMs-filled epoxy matrix composites, *Colloid and Polymer Science* 289(14) (2011) 1535-1542.
<https://www.doi.org/10.1007/s00396-011-2478-9>
- [129] P. Sobolciak, M. Mrlík, M.A. Al-Maadeed, I. Krupa, Calorimetric and dynamic mechanical behavior of phase change materials based on paraffin wax supported by expanded graphite, *Thermochimica Acta* 617 (2015) 111-119. <https://www.doi.org/10.1016/j.tca.2015.08.026>
- [130] P. Sobolciak, M. Karkri, M.A. Al-Maaded, I. Krupa, Thermal characterization of phase change materials based on linear low-density polyethylene, paraffin wax and expanded graphite, *Renew. Energy* 88 (2016) 372-382. <https://www.doi.org/10.1016/j.renene.2015.11.056>
- [131] W. Wu, W. Wu, S. Wang, Form-stable and thermally induced flexible composite phase change material for thermal energy storage and thermal management applications, *Appl. Energy* 236 (2019) 10-21. <https://www.doi.org/10.1016/j.apenergy.2018.11.071>
- [132] R. Wirtz, A. Fuchs, V. Narla, Y. Shen, T. Zhao, Y. Jiang, A Multi-functional graphite/epoxy-based thermal energy storage composite for temperature control of sensors and electronics, University of Nevada, Reno Reno, Nevada, 89557 USA, 2003, pp. 1-9.
- [133] O. Mesalhy, K. Lafdi, A. Elgafy, Carbon foam matrices saturated with PCM for thermal protection purposes, *Carbon* 44(10) (2006) 2080-2088. <https://www.doi.org/10.1016/j.carbon.2005.12.019>
- [134] Y. Zhong, Q. Guo, S. Li, J. Shi, L. Liu, Heat transfer enhancement of paraffin wax using graphite foam for thermal energy storage, *Sol. Energy Mater. Sol. Cells* 94(6) (2010) 1011-1014.
<https://www.doi.org/10.1016/j.solmat.2010.02.004>
- [135] P. Jana, V. Fierro, A. Pizzi, A. Celzard, Thermal conductivity improvement of composite carbon foams based on tannin-based disordered carbon matrix and graphite fillers, *Materials & Design* 83 (2015) 635-643. <https://www.doi.org/10.1016/j.matdes.2015.06.057>
- [136] S. Yoo, E. Kandare, R. Shanks, M.A. Al-Maadeed, A. Afaghi Khatibi, Thermophysical Properties of Multifunctional Glass Fibre Reinforced Polymer Composites Incorporating Phase Change Materials, *Thermochimica Acta* 642 (2016) 25-31. <https://www.doi.org/10.1016/j.tca.2016.09.003>
- [137] S. Yoo, E. Kandare, G. Mahendrarajah, M.A. Al-Maadeed, A.A. Khatibi, Mechanical and thermal characterisation of multifunctional composites incorporating phase change materials, *J. Compos Mater.* 51(18) (2017) 2631-2642. <https://www.doi.org/10.1177/0021998316673894>
- [138] S. Yoo, E. Kandare, R. Shanks, A.A. Khatibi, Viscoelastic characterization of multifunctional composites incorporated with microencapsulated phase change materials in: Elsevier (Ed.) International Conference of Materials Processing and Characterization (ICPMC), 2017.
- [139] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Wax confinement with carbon nanotubes for phase changing epoxy blends, *Polymers* 9(9) (2017) 405/1-405/16.
<https://www.doi.org/10.3390/polym9090405>
- [140] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Multifunctional epoxy/carbon fiber laminates for thermal energy storage and release, *Composites Science and Technology* 158 (2018) 101-111.
<https://www.doi.org/10.1016/j.compscitech.2018.02.005>
- [141] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Thermal Energy Storage with Polymer Composites, in: K. Kalaitzidou (Ed.) American Society for Composites 2019 - Thirty-Fourth Technical Conference Atlanta, GA, US, 2019. <https://www.doi.org/10.12783/asc34/31370>
- [142] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Effect of phase change microcapsules on the thermo-mechanical, fracture and heat storage properties of unidirectional carbon/epoxy laminates, *Polymer Testing* 91 (2020) 106747/1-106747/16.
<https://www.doi.org/https://doi.org/10.1016/j.polymertesting.2020.106747>

- [143] G. Fredi, F. Simon, D. Sychev, I. Melnyk, A. Janke, C. Scheffler, C. Zimmerer, Bioinspired Polydopamine Coating as an Adhesion Enhancer Between Paraffin Microcapsules and an Epoxy Matrix, *ACS Omega* 5 (2020) 19639–19653. <https://www.doi.org/10.1021/acsomega.0c02271>
- [144] A. Dorigato, G. Fredi, A. Pegoretti, Application of the thermal energy storage concept to novel epoxy/short carbon fiber composites., *Journal of applied polymer science* 136(21) (2019) 47434/1-47434/9. <https://www.doi.org/10.1002/app.47434>
- [145] G. Fredi, S. Dirè, E. Callone, R. Ceccato, F. Mondadori, A. Pegoretti, Docosane-organosilica microcapsules for structural composites with thermal energy storage/release capability, *Materials* 12 (2019) 1286/1-1286/26. <https://www.doi.org/10.3390/ma12081286>
- [146] G. Fredi, A. Dorigato, A. Pegoretti, Multifunctional glass fiber/polyamide composites with thermal energy storage/release capability, *eXPRESS polymer letters* 12(4) (2018) 349-364. <https://www.doi.org/10.3144/expresspolymlett.2018.30>
- [147] A. Dorigato, G. Fredi, A. Pegoretti, Novel phase change materials using thermoplastic composites, *AIP Conference Proceedings of the 9th International Conference “Times of Polymers and Composites” (TOP)*. 2018, pp. 020044/1-020044/4. <https://www.doi.org/10.1063/1.5045906>
- [148] G. Fredi, A. Dorigato, S. Unterberger, N. Artuso, A. Pegoretti, Discontinuous carbon fiber/polyamide composites with microencapsulated paraffin for thermal energy storage., *Journal of applied polymer science* 136(16) (2019) 47408/1-47408/14. <https://www.doi.org/10.1002/app.47408>
- [149] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Multifunctional polymer composites reinforced with discontinuous carbon fibers for thermal energy storage, *ECCM 2018 - 18th European Conference on Composite Materials*, Megaron Athens International Conference Centre (MAICC), Athens, Greece, 2020.
- [150] A. Dorigato, G. Fredi, T. Meneghini, A. Pegoretti, Thermo-mechanical behaviour of thermoplastic composite laminates with thermal energy storage/release capability *ECCM 2018 - 18th European Conference on Composite Materials*, Megaron Athens International Conference Centre (MAICC), Athens, Greece, 2020.
- [151] A. Dorigato, G. Fredi, M. Negri, A. Pegoretti, Thermo-mechanical behaviour of novel wood laminae-thermoplastic starch biodegradable composites with thermal energy storage/release capability, *Frontiers in Materials* 6 (2019) 1-12. <https://www.doi.org/10.3389/fmats.2019.00076>
- [152] M.M. Rueda, M.-C. Auscher, R. Fulchiron, T. Périé, G. Martin, P. Sonntag, P. Cassagnau, Rheology and applications of highly filled polymers: a review of current understanding, *Progress in Polymer Science* 66 (2017) 22-53. <https://www.doi.org/10.1016/j.progpolymsci.2016.12.007>
- [153] G. Fredi, A. Dorigato, L. Fambri, A. Pegoretti, Detailed experimental and theoretical investigation of the thermo-mechanical properties of epoxy composites containing paraffin microcapsules for thermal management *Polymer Engineering and Science* 60 (2020) 1202–1220. <https://www.doi.org/10.1002/PEN.25374>
- [154] A. Dorigato, D. Rigotti, A. Pegoretti, Thermoplastic Polyurethane Blends With Thermal Energy Storage/Release Capability, *Frontiers in Materials* 5 (2018). <https://www.doi.org/10.3389/fmats.2018.00058>
- [155] G. Fredi, H. Brünig, R. Vogel, C. Scheffler, Melt-spun polypropylene filaments containing paraffin microcapsules for multifunctional hybrid yarns and smart thermoregulating thermoplastic composites, *EXPRESS polymer letters* 13(12) (2019) 1071–1087. <https://www.doi.org/10.3144/expresspolymlett.2019.93>
- [156] F. Rezaei, R. Yunus, N.A. Ibrahim, Effect of fiber length on thermomechanical properties of short carbon fiber reinforced polypropylene composites, *Materials & Design* 30(2) (2009) 260-263. <https://www.doi.org/10.1016/j.matdes.2008.05.005>
- [157] S.-Y. Fu, B. Lauke, Effects of fiber length and fiber orientation distributions on the tensile strength of short-fiber-reinforced polymers, *Composites Science and Technology* 56 (1996) 1179-1190. [https://www.doi.org/10.1016/S0266-3538\(96\)00072-3](https://www.doi.org/10.1016/S0266-3538(96)00072-3)
- [158] G. Fredi, A. Dorigato, A. Pegoretti, Novel reactive thermoplastic resin as a matrix for laminates containing phase change microcapsules, *Polymer Composites* 40(9) (2019) 3711-3724. <https://www.doi.org/10.1002/pc.25233>

- 1
2
3 [159] G. Fredi, A. Dorigato, A. Pegoretti, Dynamic-mechanical response of carbon fiber laminates with
4 a reactive thermoplastic resin containing phase change microcapsules, *Mechanics of Time-Dependent*
5 *Materials* 24(3) (2020) 395-418. <https://www.doi.org/10.1007/s11043-019-09427-y>
6 [160] M. Abdel Ghafaar, A.A. Mazen, N.A. El-Mahallawy, Behavior of woven fabric reinforced epoxy
7 composites under bending and compressive loads, *Journal of Engineering Sciences* 34(2) (2006) 453-
8 469.
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60